


Sample Name: Poly(1,2-butadiene), α,ω -bis(hydroxy)-terminated

Sample #: P9493-Bd2OH

Structure:

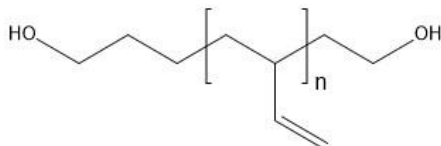

Composition:

$M_n \times 10^3$	PDI
0.80	1.04

1,2 addition >85%

Synthesis Procedure:

1,2-rich microstructure addition dihydroxy terminated polybutadiene was prepared by anionic living polymerization (by lithium naphthalene) of butadiene in polar solvent such as THF at 0 °C followed by termination with ethylene oxide

Characterization:


The molecular weight and polydispersity index (PDI) are obtained by size exclusion chromatography (SEC) in THF. SEC analysis was performed on a Varian liquid chromatograph equipped with refractive and UV light scattering detectors. Three SEC columns from Supelco (G6000-4000-2000 HXL) were used with triple detectors from Viscotek Co.

Functionality: functionality of the obtained polymer was determined by reacting polymer in dried non quantity of acetic anhydride in the presence of pyridine as a catalyst and the liberated COOH was titrated by acid-base titration.

Solubility:


Hydroxy terminated polybutadiene is soluble in THF, toluene, hexane, cyclohexane and CHCl_3 . It precipitates from methanol, ethanol, and water.

HNMR spectrum of the Product:

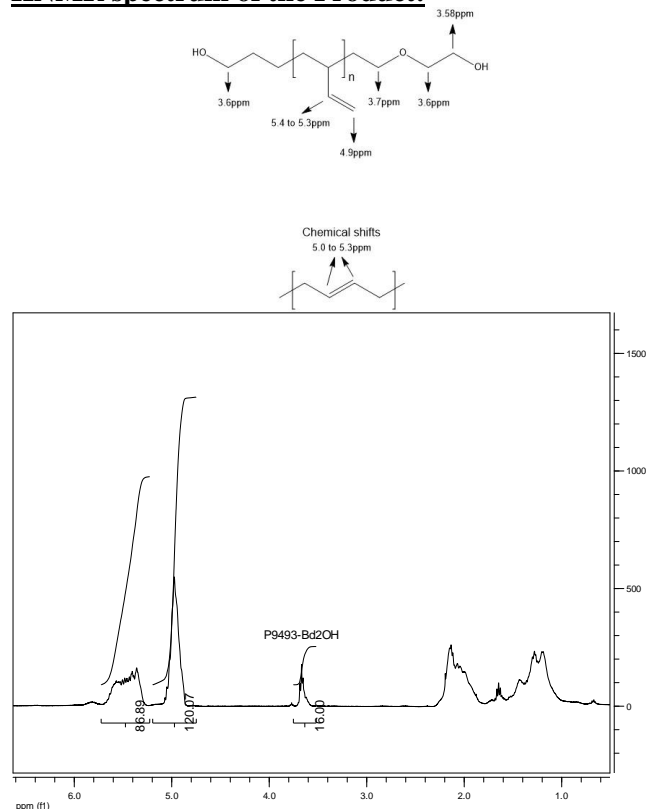

SEC profile of the Sample:

P9493-Bd2OH (rich in 1,2 addition)

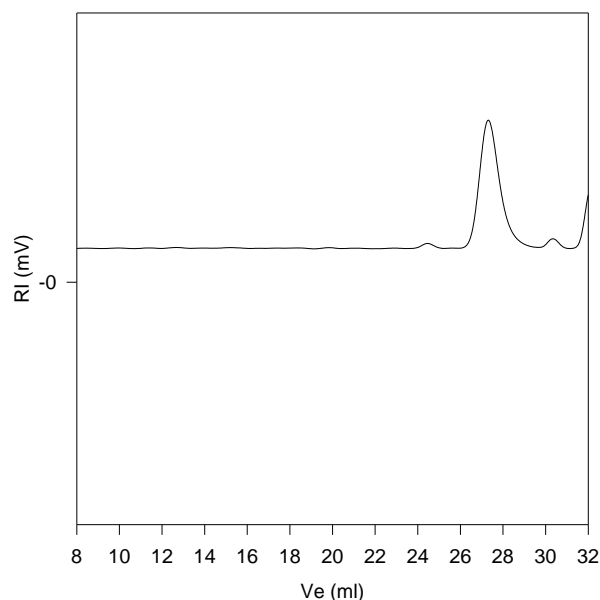

Size Exclusion Chromatography of polystyrene;

— $M_n = 800$, $M_w = 850$, $M_w/M_n = 1.04$