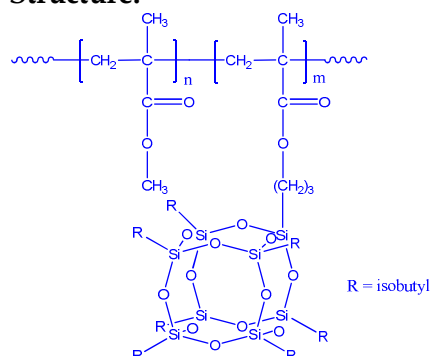


Sample Name:

Poly(methyl methacrylate-b-isobutyl-POSS methacrylate)

Sample #: P9725A-MMAPOSSMA**Structure:****Composition:**

Mn × 10 ³ MMA-b-POSSMA	PDI
9.0-b-150.0	2.4
T _g (°C) for MMA block:	T _g (°C) for POSSMA block:

Synthesis Procedure: Poly(Methyl methacrylate-b-isobutyl-POSS methacrylate) block copolymer is synthesized by living anionic polymerization with sequence addition of methyl methacrylate followed by addition of POSS methacrylate monomer. The obtained polymer was precipitation in methanol.

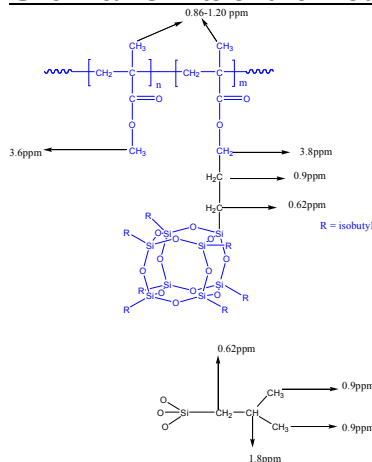
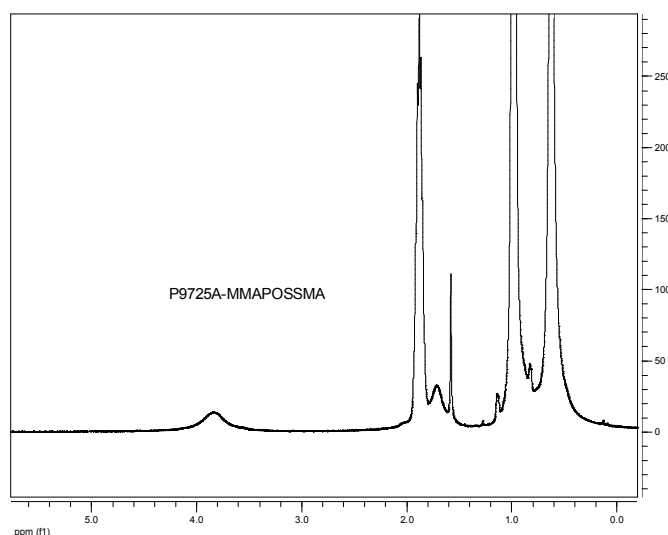
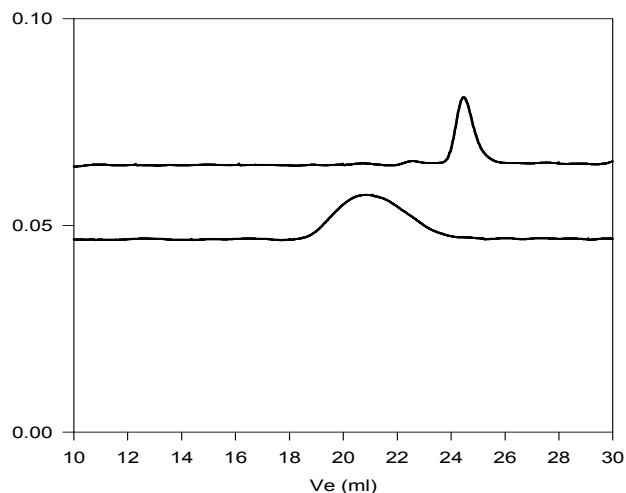
Characterization:

Polymer was analyzed by size exclusion chromatography (SEC) to obtain the molecular weight and polydispersity index (PDI). The final block copolymer composition was calculated from HNMR.

Thermal analysis was carried out using TA Q100 DSC. The mid point of the thermal transition is considered as glass transition temperature (T_g).

Solubility:

Polymer is soluble in THF and toluene. It is precipitated into methanol.

Chemical Shifts of the Products:**¹H-NMR Spectrum of the block copolymer:****SEC of the block copolymer:****P9725A-MMAPOSSMA**

— Poly(methyl methacrylate): M_n=9000, M_w=10500, M_w/M_n=1.15
 — Block Copolymer MMA(9000)-b-POSSMA(150,000), M_w/M_n=2.4

Thermal analysis of the P9725A- MMAPOSSMA

Thermal analysis of the samples was carried out on a TA Q100 differential scanning calorimeter at a heating rate of 10°C/min. The midpoint of the slope change of the heat flow plot of the second heating scan was considered as the glass transition temperature (T_g).

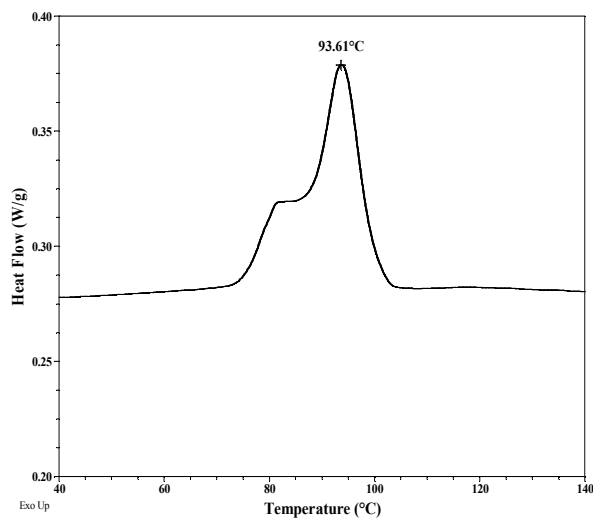
Melting and crystallization curve for the sample

The melting temperature (T_m) was taken as the maximum of the endothermic peak where as the crystallization temperature (T_c) was considered as the minimum of the exothermic peak.

Thermal analysis results at a glance:

Sample	T_m (°C)	T_c (°C)	T_g (°C)
MMA block	-	-	Not distinct
POSSMA block	146 & 290	94	-

Crystallization curve for POSSMA block:



Melting curve for POSSMA block:

