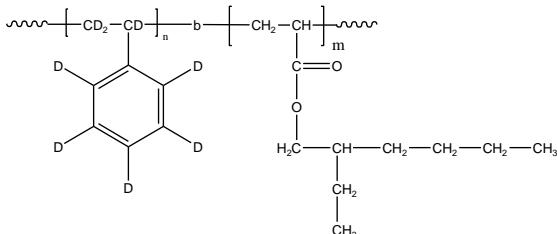


Sample Name:**Deuterated polystyrene (d8)- poly 2-ethylhexylacrylate(protonated)**

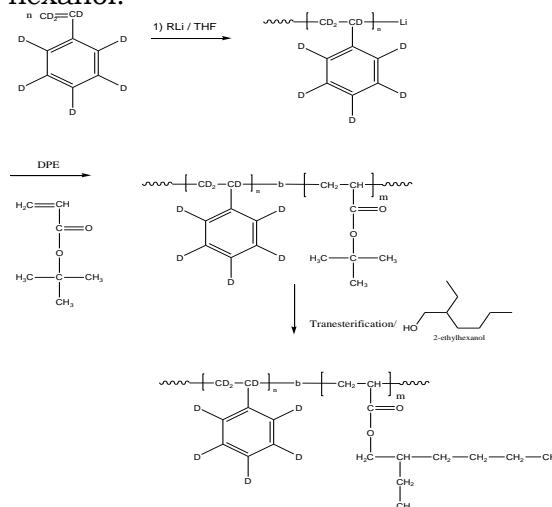
Sample #: P9747-dPSEtHA

Structure:**Composition:**

Mn × 10 ³	PDI
10.0-b-2.0	1. 09
Tg for dPS block: 83 °C	2EtHA: Not distinct

Synthesis Procedure:

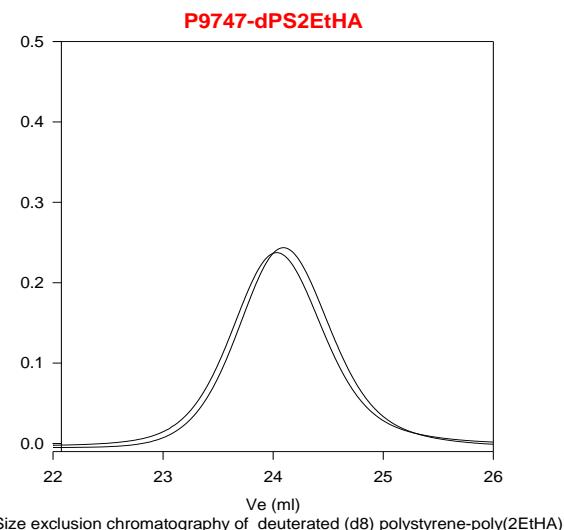
Deuterated poly(styrene (D8)-b-t-butyl acrylate) is prepared by living anionic polymerization in THF at -78 °C using sec.BuLi initiator in the presence of LiCl. Deuterated Polystyrene macroanions were end capped with a unit of diphenyl ethylene (DPE) before adding tert.butylacrylate (tBuA) monomer. For further details please consult our publication.¹⁻⁵ TRhe obtained polymer transesterified in presence of 2 ethyl hexanol.

**Characterization:**

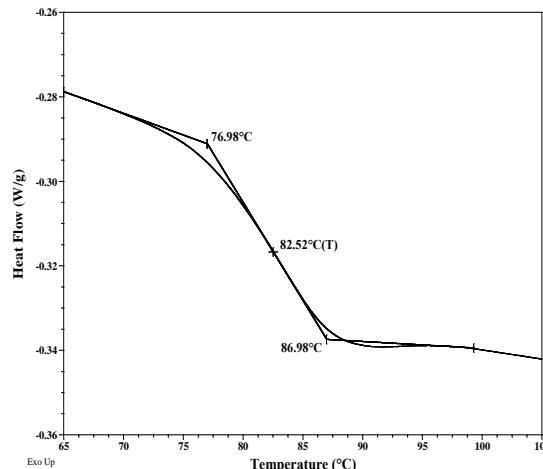
The molecular weight and polydispersity index (PDI) are obtained by size exclusion chromatography (SEC) in THF. SEC analysis was performed on a Varian liquid chromatograph equipped with refractive and UV light scattering detectors from Viscotek Co. Three SEC columns from Supelco (G6000-4000-2000 HXL) were used.

Thermal analysis of the samples was carried out using a differential scanning calorimeter (TA Q100) at a heating rate of 10°C/min. The inflection glass transition temperature (T_g) has been considered.

Solubility: Deuterated polystyrene-b-2-ethyl hexylacrylate is soluble in THF, dioxane, toluene, benzene and CHCl₃. It precipitates from methanol/water.

SEC of the product:

Size exclusion chromatography of deuterated (d8) polystyrene-poly(2EtHA)

— Deuterated Polystyrene, $M_n=10000$, $M_w=10800$, PI=1.08— Mn: dPS Mn 10,000-b-2EtHA (2,000) M_w/M_n 1.09**Thermogram for dPS block:****References for further information:**

1. S. K. Varshney, R. Fayt, Ph. Teyssie, and J.P. Hautekeer US Patent 5,264,527 (1993)
2. Ph. Teyssie, Ph. Bayard, R. Jerome, S. K. Varshney, and J. S. Wang, "35th IUPAC International Union of Pure & Applied Chemistry International Symposium on Macromolecules" 1994, 67.
3. Ph. Teyssie, R. Fayt, J. P. Hautekeer, C. Jacobs, R. Jerome, L. Leemans and S. K. Varshney *Makromolekular Chemie, Macromol. Symp.*, 1990, 32, 61-73.
4. S. K. Varshney, J. P. Hautekeer, R. Fayt, R. Jerome, and Ph.Teyssie *Macromolecules*, 1990, 23, 2618-2622.
5. R. Jerome, R. Forte, S. K. Varshney, R. Fayt, and Ph. Teyssie "The Anionic Polymerization of Alkylacrylates:A Challenge" in the Recent Advances in Mechanistic and Synthetic Aspects of Polymerization: M. Fontanaille and A. Guyot Ed., NATO ASI Series C 215, 101 (1987), CA Vol. 108, 12, 094992.