

Product Profile

Identification

Product Name: Poly(methyl methacrylate), electronic grade, Syndiotactic (SYNDIO > HETERO>ISO)

CAS Number: 9011-14-7


Product Lot Number: PMMA-30K

Synonym(s):

Syndiotactic PMMA, Syndiotactic methyl methacrylate polymer, Syndiotactic poly(methyl methacrylate)

Linear Formula: $(C_5H_8O_2)_n$

Product Chemical Architecture:



Composition:

Mn x 10 ³	Mw/Mn (PDI)	Microstructure of Polymer by ¹ H NMR (<i>syn:hetero:iso</i>)
30.0	1.08	Syndio > 85%

Method of Synthesis Using Grignard catalyst

Solubility in different solvents


THF	√		
CHCl ₃	√	Acetone	√
Toluene-Hot	√		

Purification of Polymer: By solvent-non solvent process using EDTA and filtration to remove inorganic salt.

Validation of Architecture:


A. Gel Permeation Chromatography (GPC), SEC- Profile

PMMA-30K

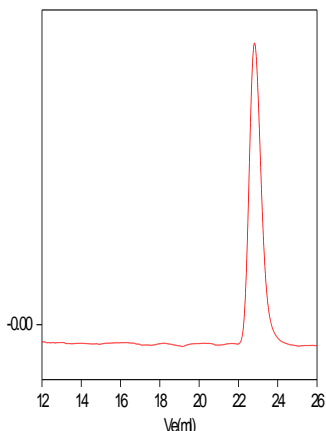


Size exclusion chromatography of poly(methyl methacrylate):
M_n=30,000, M_w=32,500, M_z=35,700 M_w/M_n=1.08

B. NMR (HNMR) of polymer:

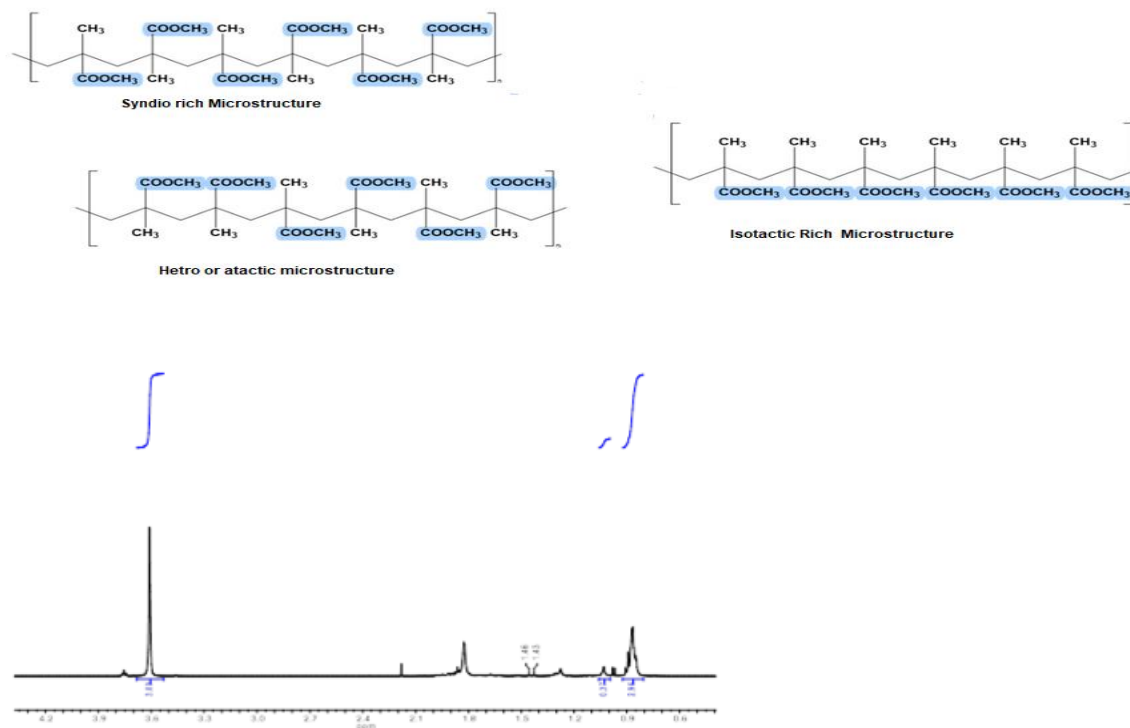

C. DSC thermogram (2nd heating scan, 10°C/min):

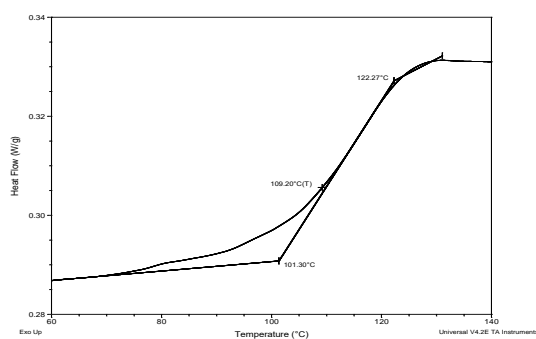

D. Summary of DSC results for PMMA of different tacticity:

PMMA microstructure	Tacticity Syndio : Iso : Hetero	T_g (°C)
Syndiotactic >79%	79 : 19 : 2	120
Syndiotactic >85%	86 : 0 : 14	123
Isotactic >97%	0 : 97 : 3	44
Atactic	56 : 6 : 38	97