


Sample Name: Poly (N-Isopropyl Acrylamide)

Sample #: P16044A-NIPAM

Structure:

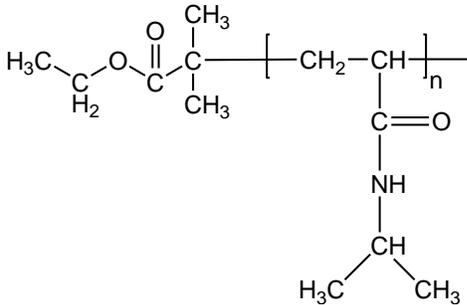

Composition:

$M_n \times 10^3$	PDI
246.0	2.7

Synthesis Procedure:

Poly (N-isopropyl acrylamide) was prepared by ATRP polymerization process.


Characterization:

The polymer was characterized by SEC in DMF and ^1H NMR.


Purification of polymer:

Unreacted monomer was removed by dissolving the product in cold water, followed by warming the solution. The polymer separated out. This procedure was applied 2 times to remove the un-reacted monomer. The obtained polymer was dissolved in acetone and fractionated from hexane.

^1H NMR spectrum of the polymer:

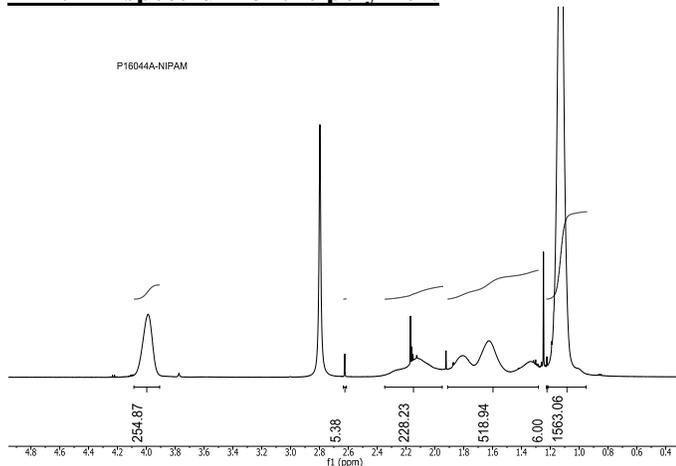


m, m isocontents
1.9 and 1.7
while r contents : 1.6ppm

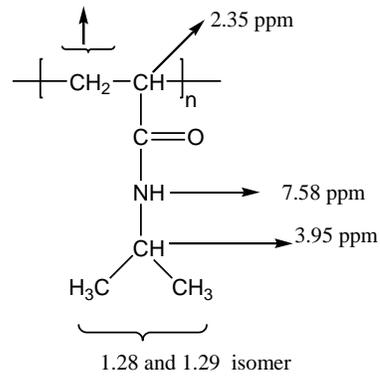

SEC elugram of the polymer in DMF:

P16044A-NIPAM

Conc (mg/mL)	4.0289
dn/dc (mL/g)	0.0770
Method	PS80k-May-25-2016-0000.vcm
Solvent	DMF w 0.023M LiBr
Column	PSS

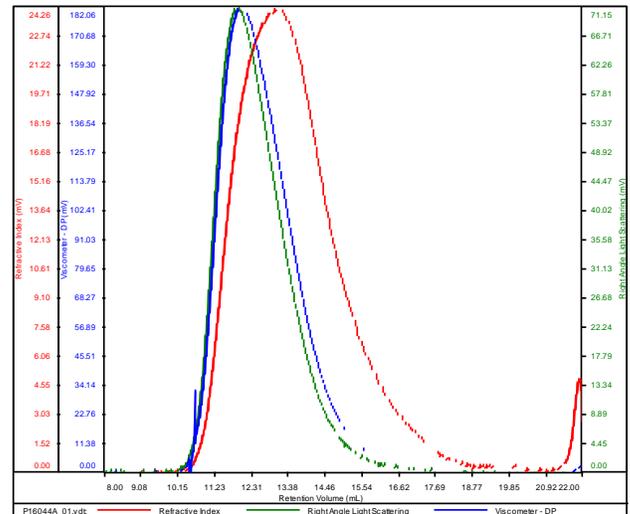

Sample	M_n	M_w	M_p	M_w/M_n	IV
P16044A_01.vcl	246,041	660,246	545,874	2.683	1.1940