


Sample Name: Poly (methyl methacrylate)
Isotactic Form

Sample #: P40484B-iMMA

Structure:

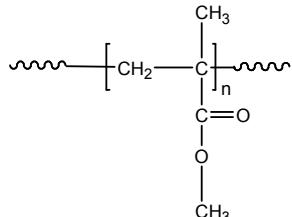

Composition:

Mn x 10 ³	18.0
PDI	1.18
S:H:I	2:4:94
Tg	53 °C

Synthesis Procedure:


The polymer was synthesized by anionic polymerization process.

Characterization:

The product was characterized by size exclusion chromatography (SEC) and ¹H NMR.

Thermal analysis was performed on TA Instruments Q100 differential scanning calorimeter (DSC) under a nitrogen atmosphere. The glass transition temperature (T_g) of the polymer was measured at a scan rate of 10°C/min shortly after creating thermal history of the sample.


HNMR of the Polymer :

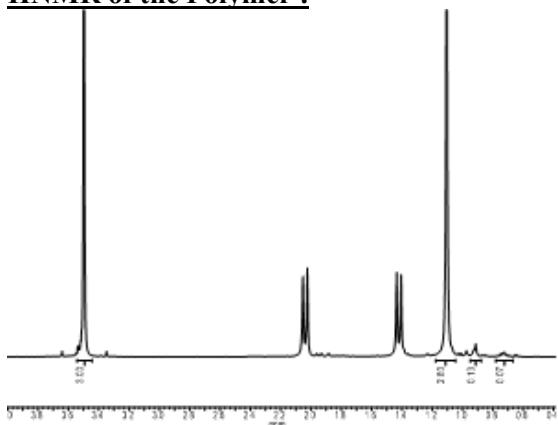

SEC of the Homopolymer:


P40484B-iMMA isotactic rich

Concentration (mg/mL)	8.093
Sample dn/dc (mL/g)	0.0940
Method File	PS80K-Feb2017-0000.vcm
Column Set	3k PL 1113-6300
Solvent	THF

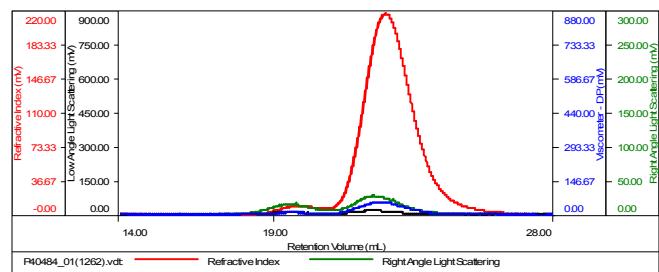

Sample	M _h (Da)	M _w (Da)	M _w /M _h	I/V(dL/g)	M _p (Da)
P40484_01(1262).vdt	18,012	21,367	1.186	0.3274	18,286

DSC thermogram (2nd heating scan, 10°C/min):

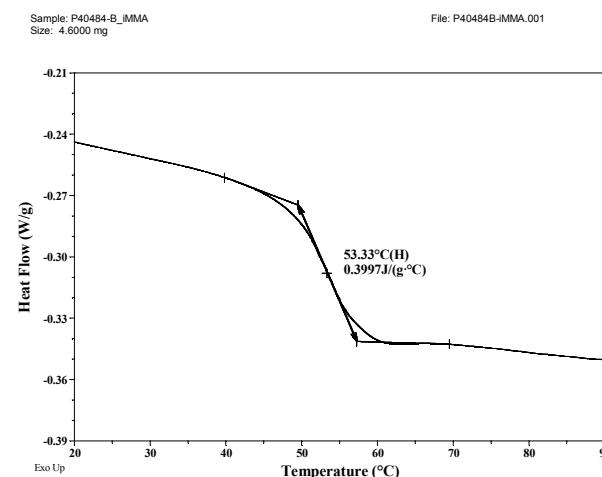

Summary of DSC results for PMMA of different tacticity:

PMMA microstructure	Tacticity Syndio : Iso : Hetero	T _g (°C)
Syndiotactic >79%	79 : 19 : 2	120
Syndiotactic >85%	86 : 0 : 14	123
Isotactic >97%	0 : 97 : 3	44
Atactic	56 : 6 : 38	97

References for further information:

S. K. Varshney, R. Fayt, Ph. Teyssie, US Patent 5,629,393, 1997