


Sample Name: Poly(styrene-b-methyl methacrylate)
(polymethylmethacrylate rich in atactic)

Sample #: P19374-SMMA

Structure:

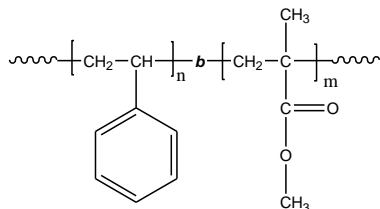

Composition:

Mn x 10 ³ S-b-MMA	PDI
217.0-b-104.5	1.7
S:h:I	40:53:7

Synthesis Procedure:

Poly(styrene-b-methyl methacrylate) is prepared by living anionic polymerization in THF at -78 °C using sec.BuLi initiator in the presence of LiCl. Polystyrene macroanions were end capped with a unit of diphenyl ethylene (DPE) before adding methylmethacrylate (MMA) monomer. For further details please see our published articles.¹⁻⁵


Characterization:

An aliquot of the anionic polystyrene block was terminated before addition of MMA and analyzed by size exclusion chromatography (SEC) to obtain the molecular weight and polydispersity index (PDI). The final block copolymer composition was calculated from ¹H-NMR spectroscopy by comparing the peak area of the poly(methyl methacrylate) protons (eg. -OCH₃ at 3.6ppm) with the of aromatic protons of polystyrene at 6.3-7.2 ppm. Copolymer PDI is determined by SEC.

Solubility:

Poly(methyl methacrylate) is soluble in THF, CHCl₃, toluene and dioxane. The polymer precipitates from hexanes, methanol and ethanol.


¹H-NMR Spectrum of the Sample:

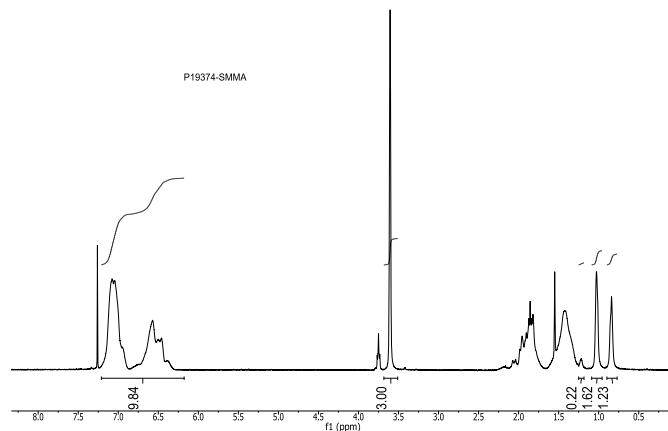

SEC elugram of the Sample:

P19374-SMMA

Conc	5.6520
dn/dc	0.1310
Solvent	DMF w 0.023M LiBr
Flow Rate	0.7000
Method	PS100k_2017-Oct11-0000.vcm

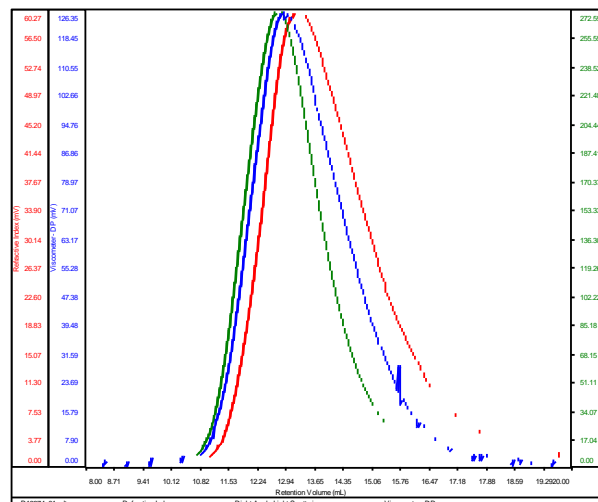

Sample	Mn	Mw	Mp	Mw/Mn	IV
P19374_01.vdt	321,353	559,906	617,004	1.742	0.6957

References for further information:

1. S. K. Varshney, R. Fayt, Ph. Teyssie, and J.P. Hautekeer US Patent 5,264,527 (1993)
2. Ph. Teyssie, Ph. Bayard, R. Jerome, S. K. Varshney, and J. S. Wang, 35th IUPAC International Union of Pure & Applied Chemistry International Symposium on Macromolecules" 1994, 67.
3. Ph. Teyssie, R. Fayt, J. P. Hautekeer, C. Jacobs, R. Jerome, L. Leemans and S. K. Varshney *Makromolekular Chemie, Macromol. Symp.*, 1990, 32,61-73.
4. S. K. Varshney, J. P. Hautekeer, R. Fayt, R. Jerome, and Ph.Teyssie *Macromolecules*, 1990, 23, 2618-2622.