


Sample Name: Poly(styrene-b-dimethyl siloxane)

Sample #: P41339-SDMS (R=H)

Structure:

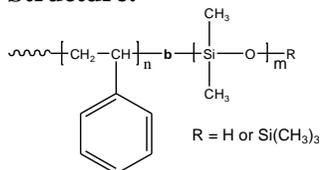

Composition:

$M_n \times 10^3$ S-b-DMS	M_w/M_n (PDI)
30.0-b-24.0	1.05
T_g for PS block: 77 °C	T_g for DMS block: -127°C (Lit. value)

Synthesis:

Poly(styrene-b-dimethyl siloxane) is prepared by living anionic polymerization with sequence addition of styrene followed by hexamethyl cyclotrisiloxane. For the details please consult the references.


Characterization:

The product was characterized by size exclusion chromatography (SEC) and ^1H NMR.

Solubility:


Poly(styrene-b-dimethyl siloxane) is soluble in CHCl_3 , toluene, and THF.

^1H NMR spectrum of the sample:

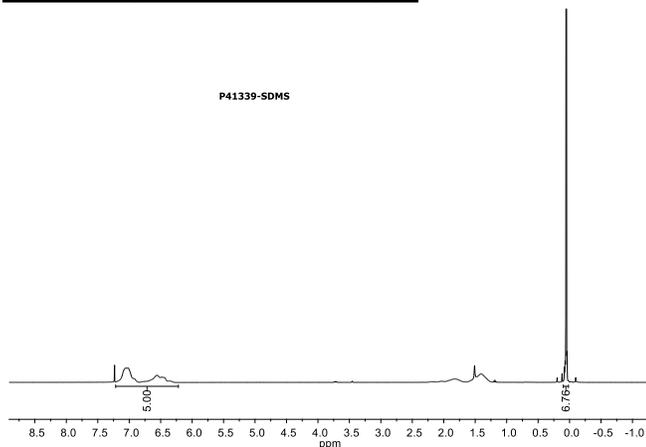

SEC profile of the block copolymer:

P41339-SDMS

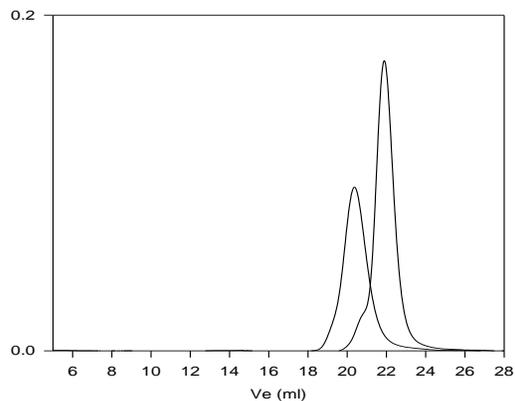


Size exclusion chromatography of poly(styrene-b-dimethylsiloxane)

— Polystyrene, $M_n=30,000$, $M_w=30,800$, $M_w/M_n=1.02$

— Poly(styrene-b-dimethylsiloxane)

M_n : PS(30,000)-b-PDMS(24,000) $M_w/M_n=1.05$

Thermogram for PS block:

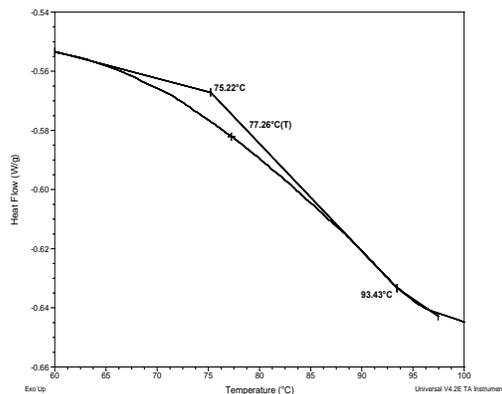

References:

- S. K. Varshney, D. N. Khanna "Hexamethylcyclotrisiloxane-Styrene Block Copolymers and their Chemical Composition" *CA Vol. 093, 26, 240325, J. Appl. Polym. Sci., 1980, 25, 2501-2511.*
- P. Bajaj, S. K. Varshney, "Morphology and Properties of Poly(Dimethylsiloxane-b-Styrene-b-Dimethylsiloxane) Polymers" *CA Vol. 093, 02, 008652, Polymer, 1980, 21, 201-206.*
- S. K. Varshney, C. L. Beatty "Synthesis and Characterization of Polymethylmethacrylate and Polydimethylsiloxane Block Copolymers Polymerizes with an Organometallic Initiator" *Org. Coat. Appl. Polym. Sci., 1981, 45, 151-157.*
- S. K. Varshney, C. L. Beatty, and P. Bajaj "Morphology and Properties of Styrene and Dimethylsiloxane Triblock and Multiblock Copolymers" *CA Vol. 098, 139, 017855, Am. Chem. Soc. Polym. Prepr., 1981, 22, 321-323.*