


Sample Name: **Deuterated Polystyrene (d₈)**

Sample #: **P41464-dPS**

Structure:

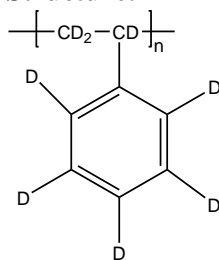


Composition:

Mn x 10 ³	PDI
25.5	3.4

Synthesis Procedure:

Deuterated polystyrene-d₈ is obtained by living anionic polymerization of styrene-d₈ as illustrated below:

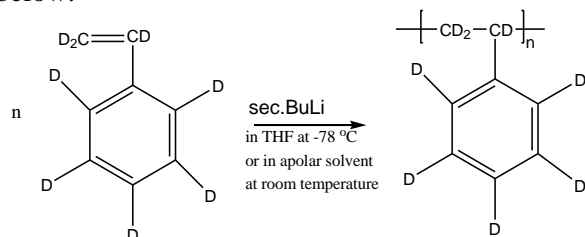

Characterization:

The molecular weight and polydispersity index (PDI) are obtained by size exclusion chromatography (SEC) in THF. SEC analysis was performed on a Varian liquid chromatograph equipped with refractive and UV light scattering detectors from Viscotek Co. Three SEC columns from Supelco (G6000-4000-2000 HXL) were used.

Solubility:


Deuterated polystyrene-d₈ is soluble in DMF, THF, toluene and CHCl₃. It precipitates from methanol, ethanol, water and hexanes.

SEC elugram of Homopolymer:

Agilent GPC/SEC Software

P41464-dPS

Chromatogram Plot

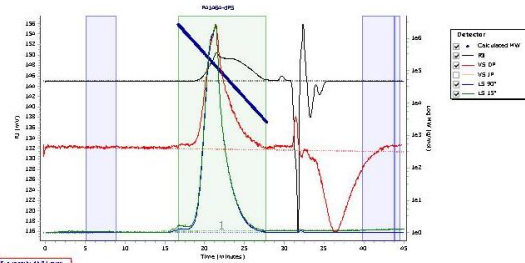

Molecular Weight Averages

Peak	Mp (g/mol)	Mn (g/mol)	Mw (g/mol)	Mz (g/mol)	Mz+1 (g/mol)	Mw (g/mol)	PDI
------	------------	------------	------------	------------	--------------	------------	-----

Peak 1	13097.3	25618	87787	207458	482361	181707	3.426
--------	---------	-------	-------	--------	--------	--------	-------