


**Sample Name:** Poly(styrene-*b*-4-vinyl pyridine)

**Sample #:** P11014A-S4VP

**Structure:**

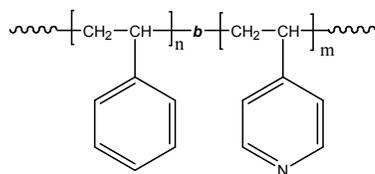

**Composition:**

$M_n \times 10^3$ S- <i>b</i> -4VP	PDI
22.0- <i>b</i> -27.0	1.18
Tg for PS block: 105 °C	Tg for 4VP block: 130°C

**Synthesis Procedure:**

Poly(styrene-*b*-4-vinyl pyridine) is prepared by living anionic polymerization in THF at -78 °C in the presence of LiCl as an additive.

**Characterization:**

An aliquot of the anionic polystyrene block was terminated before addition of 4VP and analyzed by size exclusion chromatography (SEC) to obtain the molecular weight and polydispersity index (PDI). The Block copolymer composition was then calculated from <sup>1</sup>H-NMR spectroscopy by comparing the peak area of the 2VP proton at 8.2 ppm with the peak area of the aromatic protons of polystyrene at 6.3-7.2 ppm. The composition of the block copolymer can also be determined by titration in acetic acid/HClO<sub>4</sub> using crystal violet indicator. Copolymer PDI is determined by SEC. Thermal analysis of the samples was carried out on a TA Q100 differential scanning calorimeter at a heating rate of 10°C/min. The midpoint of the slope change of the heat flow plot of the second heating scan was considered as the glass transition temperature (T<sub>g</sub>).


**Solubility:**

Poly(styrene-*b*-4 vinylpyridine) is soluble in THF, toluene, and CHCl<sub>3</sub>. The diblock copolymer can also be solubilized in methanol, ethanol depending on its composition. The polymer readily precipitates from hexanes, ether and water.

**Purification of the obtained polymer was carried out rigorously** as follows to ensure the removal of the catalyst side product:


1. Dissolved the polymer in CHCl<sub>3</sub> and wash with de-ionized distilled water to remove the any soluble organic catalyst side product.
2. Polymer extracted from water with chloroform.
3. Polymer solution in CHCl<sub>3</sub> was dried over anhydrous sodium sulfate.
4. Solution filtered and than passed through a column packed with basic Al<sub>2</sub>O<sub>3</sub>.
5. Solution concentrated on rota-evaporator
6. Solution precipitated in cold hexane and redissolved in benzene and freeze dried.
7. Final dried under vacuum for 48h at 50°C.

**<sup>1</sup>H NMR Spectrum of the Polymer**

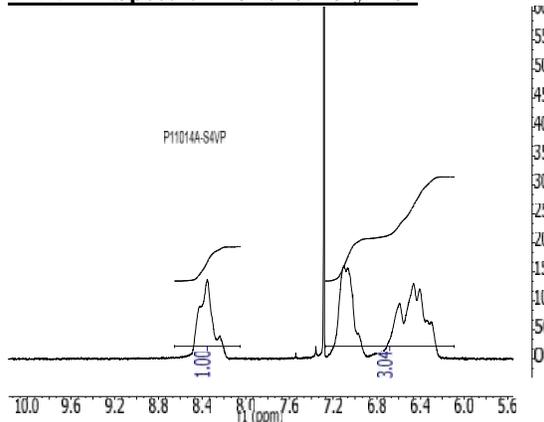


Sample ID: P11014S

Concentration (mg/mL)	11.5511
Sample dilution (x)	0.1850
Method File	PC80-Aug 20 12-0003.rtc
Column Set	3x PL 1113-G300
System	System 1

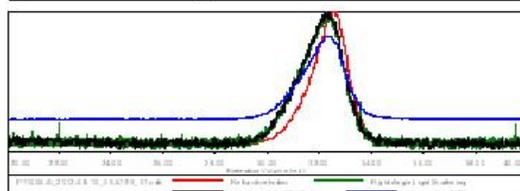


Sample	Mn (Da)	Mw (Da)	Mp (Da)	Mw/Mn	PDI (log)
P11014S	21,594	24,643	19,280	1.14	0.2205

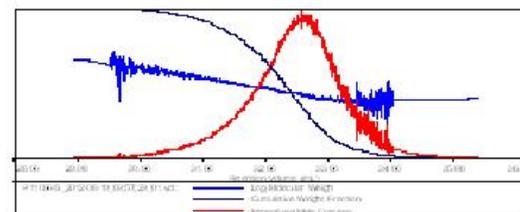

**SEC for the polymer:**

P11014A-S4VP

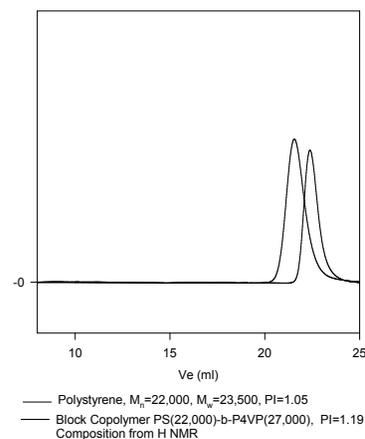

**References:**

- (1). S. K. Varshney, X. F. Zhong and A. Eisenberg *Macromolecules*, **1993**, 26, 701-706.
- (2). Z.Gao, S. K. Varshney, S. Wong, A. Eisenberg *Macromolecules*, **1994**, 27, 7923-7927.