



SEC of Sample -SMMA:

Sample ID: P11041-S


Concentration (mg/mL)	2.9412
Sample dn/dc (mL/g)	0.1850
Method File	PS80K-aug-0002.vcm
Column Set	3xPL 1113-6300
System	System 1

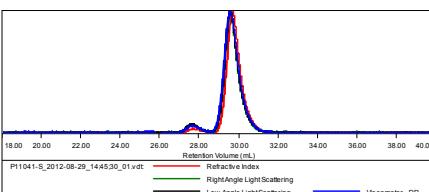

Sample	Mn (Da)	Mw (Da)	Mp (Da)	Mw/Mn	IV (dL/g)
P11041-S_2012-08-29_14:45:30_01.vdt	84,309	89,573	84,189	1.062	0.6774

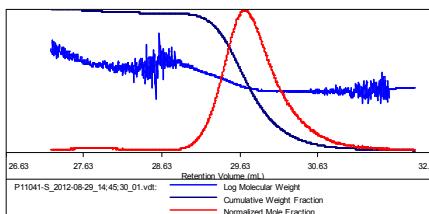


P11041-SMMA

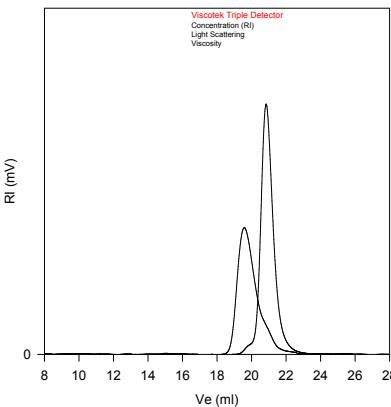

Size Exclusion Chromatography of Poly Styrene-b-MMA

— PS block $M_n = 85,000$, $M_w = 90,000$, $M_w/M_n = 1.06$
 PS-b-MMA: Mn; 85,000-b-156,000 PI: 1.35

Thermogram for the sample

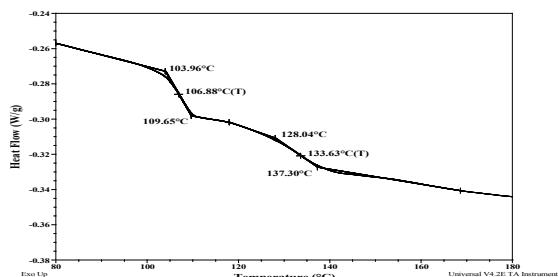

References for further information:


1. S. K. Varshney, R. Fayt, Ph. Teyssie, and J.P. Hautekeer US Patent 5,264,527 (1993)
2. Ph. Teyssie, Ph. Bayard, R. Jerome, S. K. Varshney, and J. S. Wang, *35th IUPAC International Union of Pure & Applied Chemistry International Symposium on Macromolecules* 1994, 67.
3. Ph. Teyssie, R. Fayt, J. P. Hautekeer, C. Jacobs, R. Jerome, L. Leemans and S. K. Varshney *Makromolekular Chemie, Macromol. Symp.*, 1990, 32, 61-73.
4. S. K. Varshney, J. P. Hautekeer, R. Fayt, R. Jerome, and Ph. Teyssie *Macromolecules*, 1990, 23, 2618-2622.

Sample Name: Poly(styrene-b-methyl methacrylate)

(polymethylmethacrylate rich in syndiotactic contents > 78%)

Sample #: P11041-SMMA

Structure:

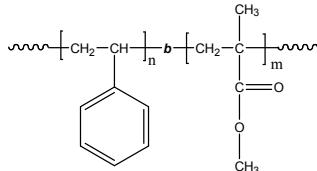

Composition:

Mn x 10 ³ S-b-MMA	PDI
85.0-b-156.0	1.35
T _g for PS block: 107°C	T _g for PMMA block: 132 °C
dn/dc in THF at 35 °C	0.1069
Mn values obtained from LS detector on line: Mn total : 304.0	

Synthesis Procedure:

By anionic process: For further details please see our published articles.¹⁻⁵

Characterization: Polymer analyzed by size exclusion chromatography (SEC) to obtain the molecular weight and polydispersity index (PDI). The final block copolymer composition was calculated from ¹H-NMR spectroscopy by comparing the peak area of the poly(methyl methacrylate) protons (eg.—OCH₃ at 3.6ppm) with of aromatic protons of polystyrene at 6.3-7.2 ppm. Copolymer PDI is determined by SEC. Thermal analysis of the samples was carried out using a differential scanning calorimeter (TA Q100) at a heating rate of 10°C/min. The inflection glass transition temperature (T_g) of the sample has been considered.

¹H-NMR Spectrum of SMMA:

