


Sample Name: Polyisobutylene

Sample #: P42429-1b

Structure:

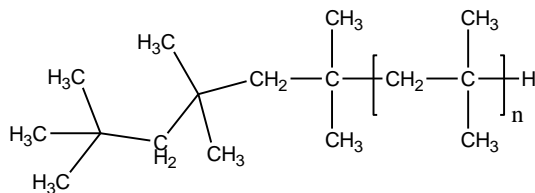


Composition:

Mn x 10 ³	PDI
856.0	1.19

Synthesis Procedure:

Polyisobutylene is synthesized by living cationic polymerization of isobutylene in hexane at $-78\text{ }^{\circ}\text{C}$ using a tin based catalyst and a 2,4,4-dimethyl pentene / HCl initiator. The reaction scheme is shown below:

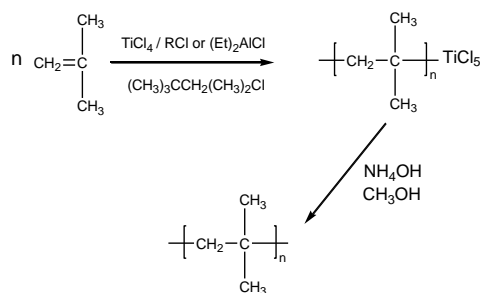


Purification:

After polymerization the catalyst residues are removed by filtration and washing with acidic water after which the pH is returned to nominal values and finally the polymer is freeze dried.

Characterization:


The molecular weight and polydispersity index (PDI) of polyisobutylene are obtained by size exclusion chromatography.

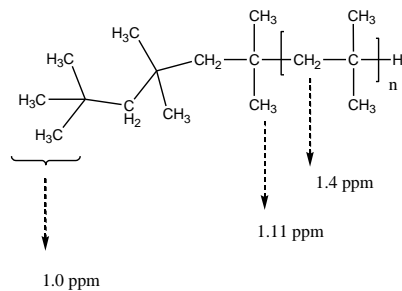

Solubility:

Polyisobutylene is soluble in THF, toluene, hexane, pentane and cyclohexane and precipitates from methanol and ethanol.

SEC elugram of the Sample:

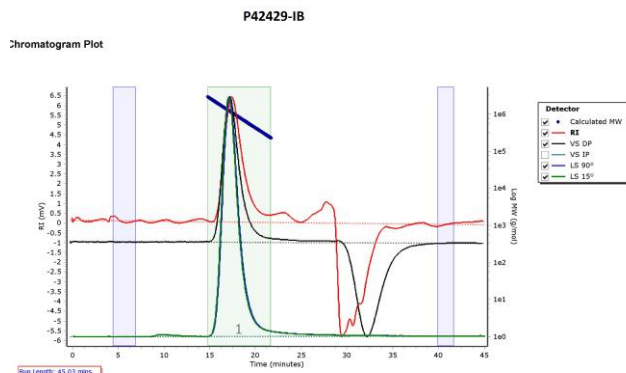

Peak	Mp (g/mol)	Mn (g/mol)	Mw (g/mol)	Mz (g/mol)	Mz+1 (g/mol)	Mv (g/mol)	PD
Peak 1	1107818	856573	1019505	1152592	1264860	1135699	1.19