


Sample Name:

**Poly(tert-butyl methacrylate), syndiotactic**

Sample#: **P43683-tBuMA**

**Structure:**

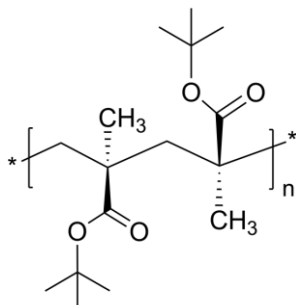

**Composition:**

Mn x 10 <sup>3</sup>	PDI
183.0	1.35

S:H:I: 54:42:4
----------------

**Synthesis Procedure:**

Poly(t-butyl methacrylate) is obtained by living anionic polymerization of t-butyl methacrylate.


**Characterization:**

The product was characterized by size exclusion chromatography (SEC) and <sup>1</sup>H-NMR spectroscopy.


**Solubility:**

Poly(tert-butylmethacrylate) is soluble in THF, CHCl<sub>3</sub>, toluene and dioxane. The polymer precipitates from cold methanol and ethanol.

**<sup>1</sup>H-NMR spectrum of the polymer:**

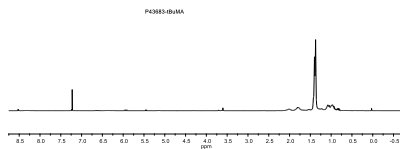


**SEC elugram of Homopolymer:**

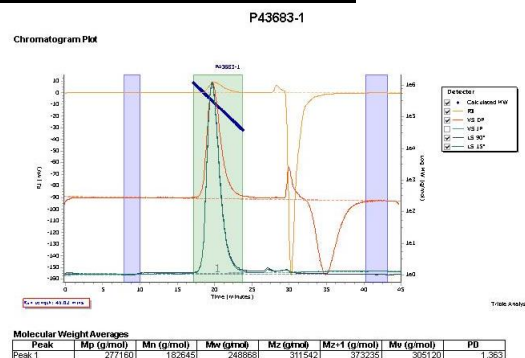

**DSC thermogram of the Product:**

Tg of poly t-butyl methacrylate as function of molecular weight

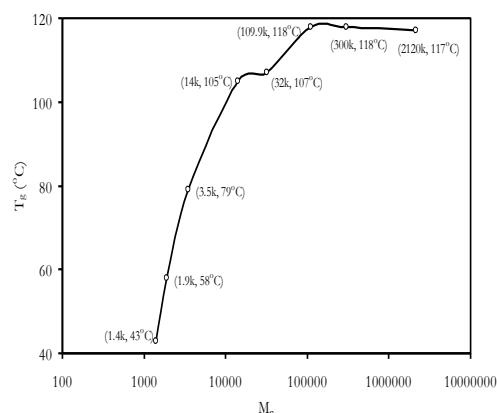

**Tg vs MW for selected poly t-butyl methacrylate:**

Mn × 10 <sup>3</sup>	Tg (°C)	Mn × 10 <sup>3</sup>	Tg (°C)
1.4	43	32	107
1.9	58	109.9	118
3.5	79	300	118
14	105	2120	117

**References for further information:**

S. K. Varshney, Z. Gao, Xing Fu Zhong, A. Eisenberg

“Effect of Lithium Chloride on the “Living” Polymerization of tert-Butylmethacrylate and Polymer Microstructure Using Monofunctional Initiators” Macromolecules, 1994, 27, 1076.