


Sample Name:

Poly(Vinyl alcohol)

Sample #: **P11283-VA**

Structure:

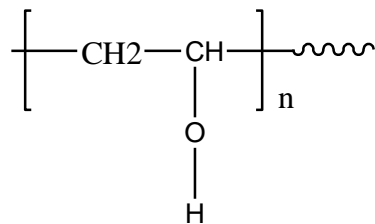


Composition:

Mn x 10 ³	PDI
37.0	1.8

Synthesis Procedure:

Poly vinyl alcohol is obtained from the hydrolysis of poly vinyl acetate under alkaline conditions. Poly vinyl acetate is obtained by free radical polymerization using iodo ethyl acetate as chain transfer reagent. Polymerization was carried out in bulk. The polymerization scheme can be illustrated as follows:

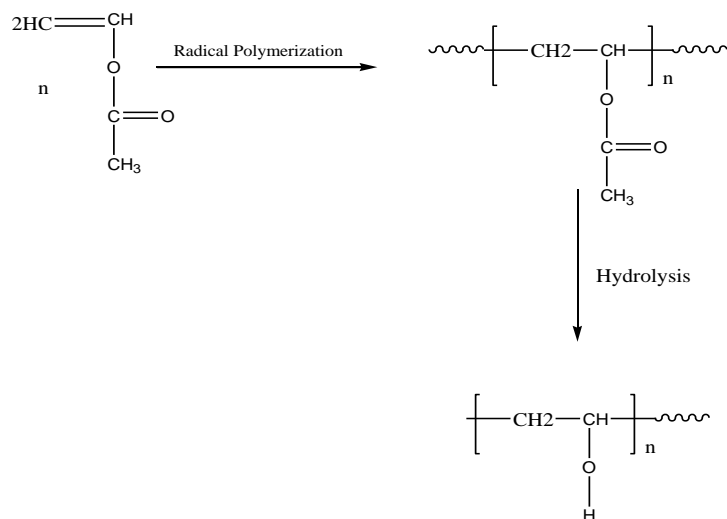

Characterization:


The molecular weight and polydispersity index (PDI) are obtained by size exclusion chromatography (SEC) in THF. SEC analysis was performed on a Varian liquid chromatograph equipped with refractive and UV light scattering detectors. Three SEC columns from Supelco (G6000-4000-2000 HXL) were used with triple detectors from Viscotek Co. ¹H NMR analysis was carried out on Varian instrument at 500MHz.

Purification:

Obtained polymer after hydrolysis of poly vinyl acetate was dissolved in methanol. Solution Filter and added to cold acetone. Poly vinyl alcohol precipitated out. It was washed with THF to remove any unreacted NaOH used in the hydrolysis. Polymer was dissolved in water and freeze dried.

SEC elugram of Homopolymer:

P11283-VAc

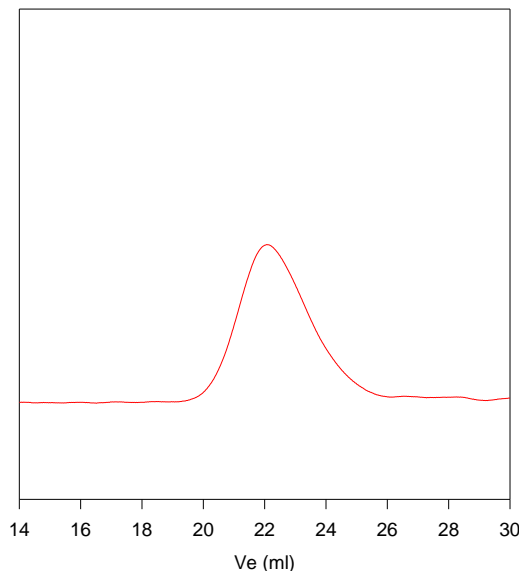

Size exclusion chromatograph of Poly vinyl acetate:

M_n=72,000 M_w=129,000 PI=1.8

dn/dc in THF: 0.033 ml/g

Data from Viscotek triple detectors.

After Hydrolysis of acetate group: Mw: 66,500 Mn : 37,000 Mw/Mn : 1.8