



Product Profile


Identification

Product Name: Poly(styrene-b-methylmethacrylate)

Product Lot Number: P8151-R-SMMA

CAS #: 25034-86-0

Product Chemical Architecture:

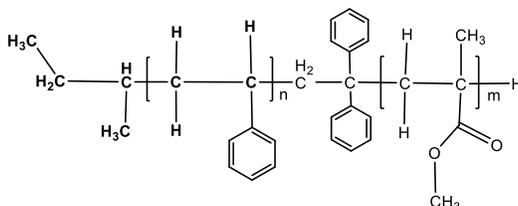

Composition:

Composition (S-b-MMA)	33,000-b-85,000
MMA mole%	71.7
Tacticity (atac, iso, syn)	PMMA > 78% syn
Mn (g/mole)	118,000
Mw (g/mole)	122,000
Mw/Mn	1.04
dn/dc (mL/g) in THF at 30 °C	0.117

Method of Synthesis

The polymer is synthesized by anionic polymerization process.

Solubility in different solvents:

THF	√	DMF	√
Alcohol	X	CHCl ₃	√
Toluene	Depends on composition	Water	X

Validation of Architecture

A. Gel Permeation Chromatography (GPC), SEC Profile:


Molecular weights were determined by Agilent Technologie 1260 Infinity II GPC/SEC System equipped with Triple detector (RI, Viscometer, RALS 90° and LS 15°) and three columns (PLgel, 7.5x300 mm, 5µm-10µm, 10⁵-10⁶Å).

THF (stabilized BHT) with 1%(v/v%) TEA was the eluent. The flow rate was 1.0 ml/min.



P8151

Chromatogram Plot

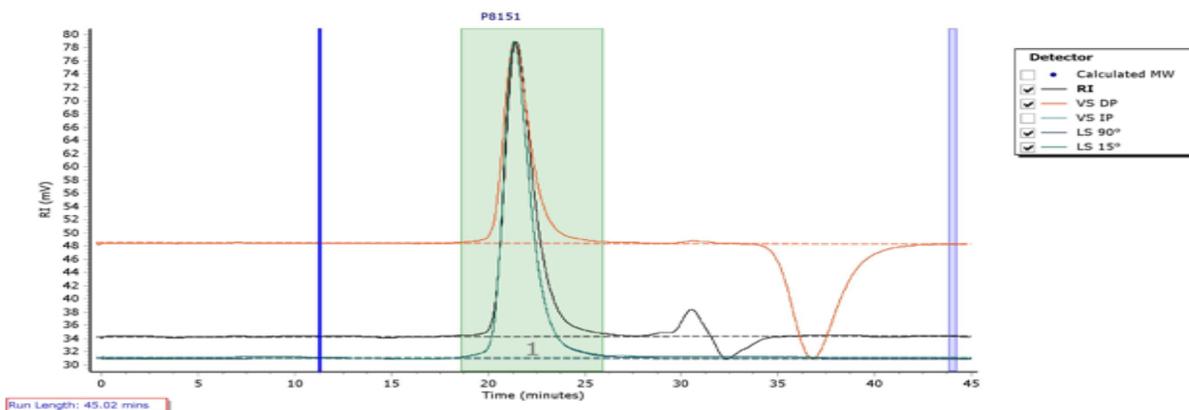

Molecular Weight Averages

Peak	Mp (g/mol)	Mn (g/mol)	Mw (g/mol)	Mz (g/mol)	Mz+1 (g/mol)	Mv (g/mol)	PD
Peak 1	129957	118262	122481	126106	129349	126093	1.036

B. NMR (H¹NMR) of SMMA

SMMA sample was dissolved in CDCl₃. ¹H NMR spectra was determined using a 500 MHz. Bruker Avance III spectrometer.

