

Product Profile


Identification

Product Name: Poly(styrene-b-methylmethacrylate)

Product Lot Number: P6000-R-SMMA

CAS #: 25034-86-0

Product Chemical Architecture:

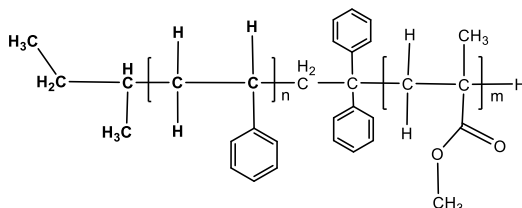

Composition:

Composition (S-b-MMA)	246,000-b-63,000
MMA mole%	20.4
Tacticity (atac, iso, syn)	PMMA > 78% syn
Mn (g/mole)	309,000
Mw (g/mole)	324,000
Mw/Mn	1.05
dn/dc (mL/g) in THF at 30 °C	0.166

Method of Synthesis

The polymer is synthesized by anionic polymerization process.

Solubility in different solvents:

THF	√	DMF	√
Alcohol	X	CHCl ₃	√
Toluene	Depends on composition	Water	X

Validation of Architecture

A. Gel Permeation Chromatography (GPC), SEC Profile:

Molecular weights were determined by Agilent Technologie 1260 Infinity II GPC/SEC System equipped with Triple detector (RI, Viscometer, RALS 90° and LS 15°) and three columns (PLgel, 7.5x300 mm, 5µm-10µm, 10⁵-10⁶Å). THF (stabilized BHT) with 1%(v/v%) TEA was the eluent. The flow rate was 1.0 ml/min.




Polymer Source,™ Inc.

Agilent GPC/SEC Software

P6000

Chromatogram Plot

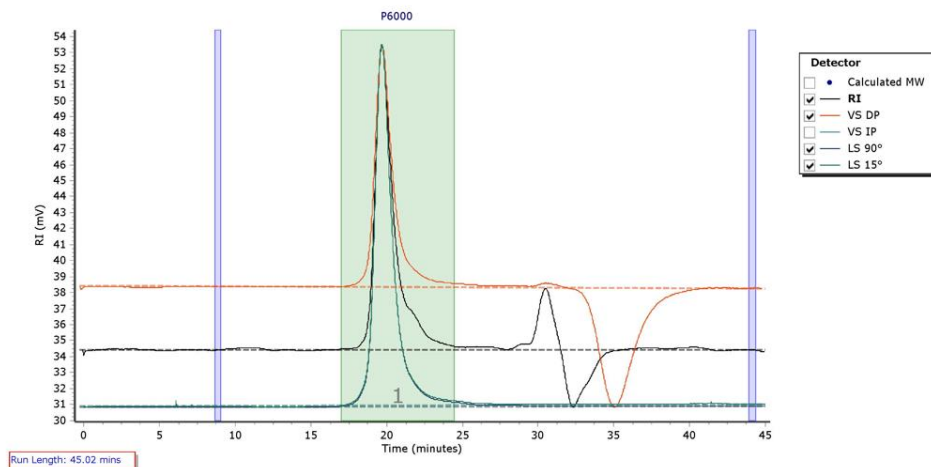


Molecular Weight Averages

Peak	Mp (g/mol)	Mn (g/mol)	Mw (g/mol)	Mz (g/mol)	Mz+1 (g/mol)	Mv (g/mol)	PD
Peak 1	350614	309167	324299	336128	345825	335083	1.049

B. NMR (¹H NMR) of SMMA

SMMA sample was dissolved in CDCl₃. ¹H NMR spectra was determined using a 500 MHz. Bruker Avance III spectrometer.

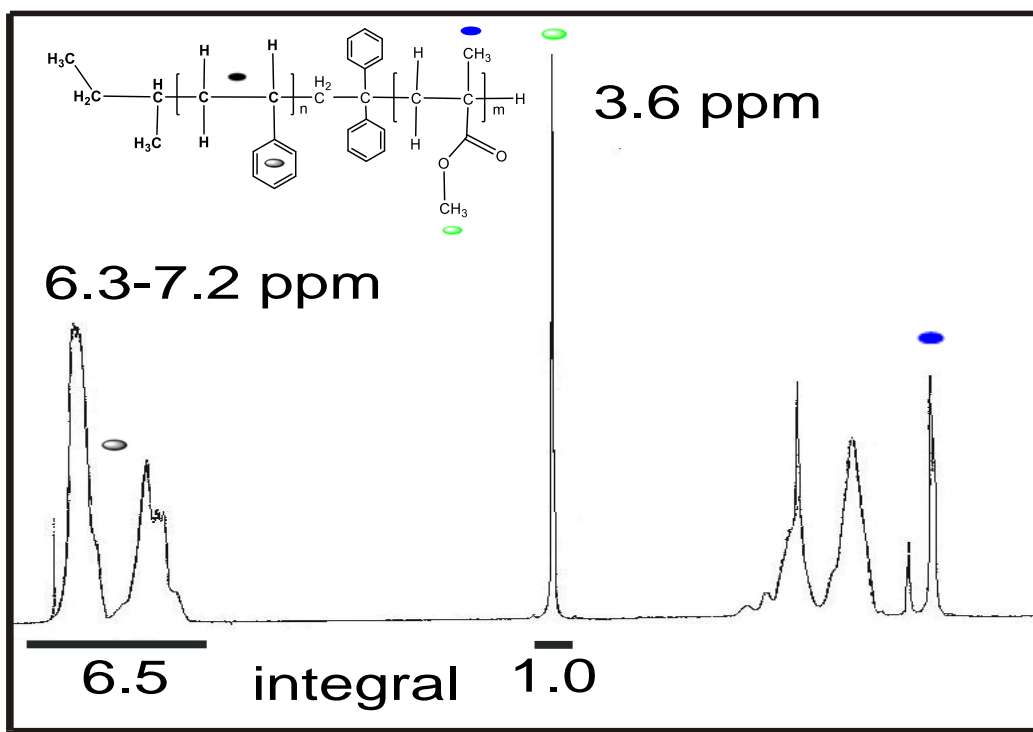

124 avenue Avro, Dorval (Montreal)
 Quebec H9P 2X8 Canada
 Phone : +1-514-421-5517 or +1-514-421-5506
support@polymersource.com
www.polymersource.ca