

## Product Profile


### Identification

**Product Name:** Poly(styrene-b-methylmethacrylate)

**Product Lot Number:** P1662-2-R-SMMA

**CAS #:** 25034-86-0

**Product Chemical Architecture:**

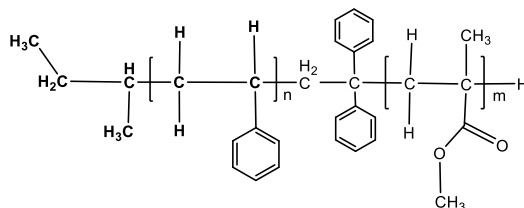

**Composition:**

<b>Composition (S-b-MMA)</b>	<b>85,000-b-19,000</b>
<b>MMA mole%</b>	<b>17.9</b>
<b>Tacticity (atac, iso, syn)</b>	<b>PMMA &gt; 78% syn</b>
<b>Mn (g/mole)</b>	<b>104,000</b>
<b>Mw (g/mole)</b>	<b>106,000</b>
<b>Mw/Mn</b>	<b>1.03</b>
<b>dn/dc (mL/g) in THF at 30 °C</b>	<b>0.168</b>

### Method of Synthesis

The polymer is synthesized by anionic polymerization process.

**Solubility in different solvents:**

THF	√	DMF	√
Alcohol	X	CHCl <sub>3</sub>	√
Toluene	<b>Depends on composition</b>	Water	X

### Validation of Architecture


#### A. Gel Permeation Chromatography (GPC), SEC Profile:

Molecular weights were determined by Agilent Technologie 1260 Infinity II GPC/SEC System equipped with Triple detector (RI, Viscometer, RALS 90° and LS 15°) and three columns (PLgel, 7.5x300 mm, 5µm-10µm, 10<sup>5</sup>-10<sup>6</sup>Å). THF (stabilized BHT) with 1%(v/v%) TEA was the eluent. The flow rate was 1.0 ml/min.



P1662-2

Chromatogram Plot

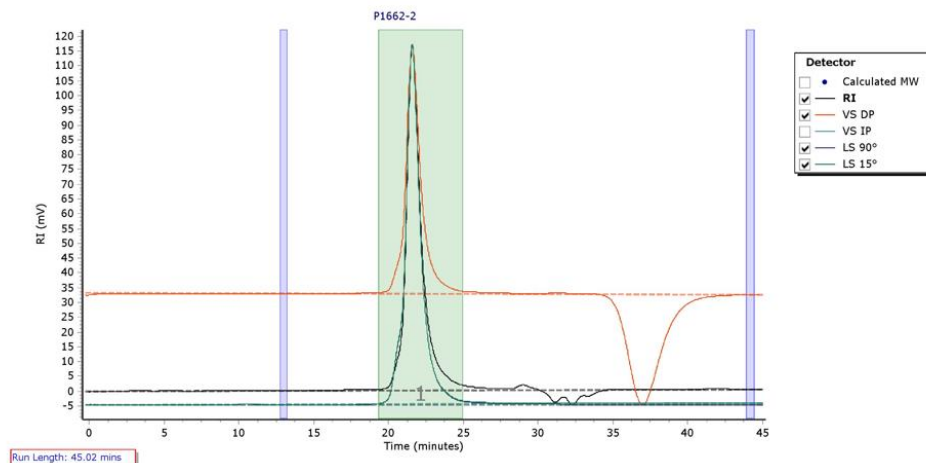

Molecular Weight Averages

Peak	Mp (g/mol)	Mn (g/mol)	Mw (g/mol)	Mz (g/mol)	Mz+1 (g/mol)	Mv (g/mol)	PD
Peak 1	110565	103732	106290	108531	110563	108114	1.025

**B. NMR ( $^1\text{H}$ NMR) of SMMA**

SMMA sample was dissolved in  $\text{CDCl}_3$ .  $^1\text{H}$  NMR spectra was determined using a 500 MHz. Bruker Avance III spectrometer.

