


## Product Profile

### Identification

**Product Name:** Poly(styrene-b-ethylene oxide)

**Product Lot Number:** P44737-SEO

**CAS #:** Not Available **Product Chemical Architecture:**

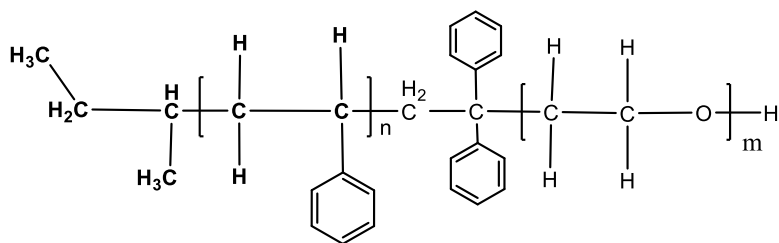

**Composition:**

Composition (S-b-EO)	1,800-b-33,500
EO mole%	95
Mn (g/mole)	35,000
Mw (g/mole)	38,000
Mw/Mn	1.09
dn/dc (mL/g) in THF at 30 °C	0.070

### Method of Synthesis

The polymer is synthesized by anionic polymerization process.

**Solubility in different solvents:**

THF	√	DMF	√
Alcohol	√	CHCl <sub>3</sub>	√
Toluene	√	Water	√

### Validation of Architecture


#### A. Gel Permeation Chromatography (GPC), SEC Profile:

Molecular weights were determined by Agilent Technologie 1260 Infinity II GPC/SEC System equipped with Triple detector (RI, Viscometer, RALS 90° and LS 15°) and three columns (PLgel, 7.5x300 mm, 5µm-10µm, 10<sup>5</sup>-10<sup>6</sup>Å). THF (stabilized BHT) with 1%(v/v%) TEA was the eluent. The flow rate was 1.0 ml/min.



Chromatogram Plot

P44737-SEO

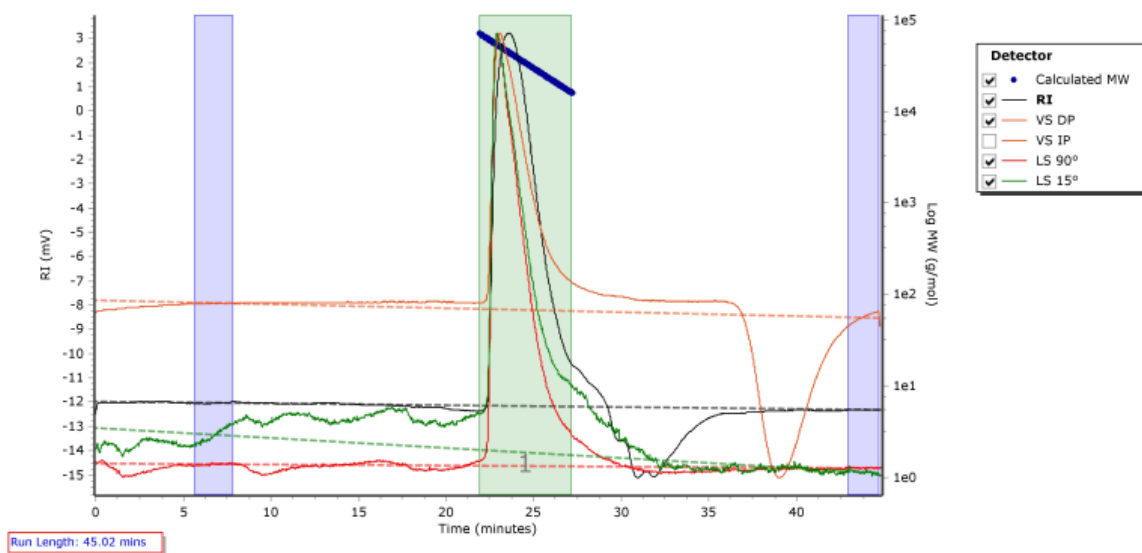

Molecular Weight Averages


Peak	Mp (g/mol)	Mn (g/mol)	Mw (g/mol)	Mz (g/mol)	Mz+1 (g/mol)	Mv (g/mol)	PD
Peak 1	44033	34736	38162	41219	43802	40832	1.099

**B. NMR (<sup>1</sup>H NMR) of SMMA**

SMMA sample was dissolved in CDCl<sub>3</sub>. <sup>1</sup>H NMR spectra was determined using a 500 MHz. Bruker Avance III spectrometer.



*Polymer Source,™ Inc.*

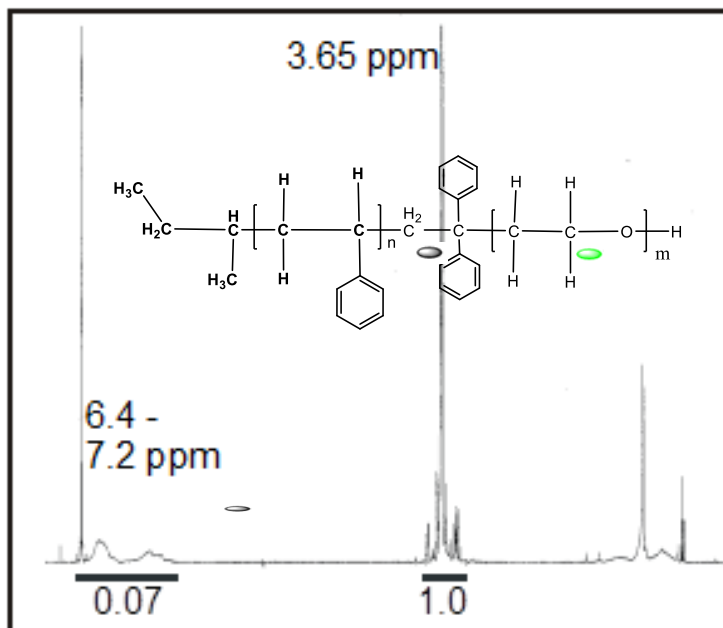

124 avenue Avro, Dorval (Montreal)  
Quebec H9P 2X8 Canada  
Phone : +1-514-421-5517 or +1-514-421-5506  
[support@polymersource.com](mailto:support@polymersource.com)  
[www.polymersource.ca](http://www.polymersource.ca)