

Product Profile


Identification

Product Name: Poly(styrene-b-ethylene oxide)

Product Lot Number: P44783-SEO

CAS #: Not Available

Chemical Architecture:

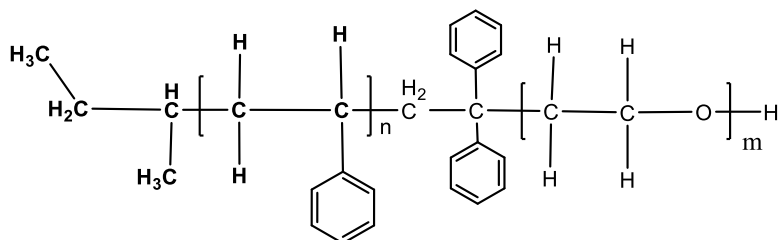

Composition:

Composition (S-b-EO)	18,000-b-37,000
EO mole%	68
Mn (g/mole)	55,000
Mw (g/mole)	62,000
Mw/Mn	1.12
dn/dc (mL/g) in THF at 30 °C	0.106

Method of Synthesis

The polymer is synthesized by anionic polymerization process.

Solubility in different solvents:


THF	√	DMF	√
Alcohol	X	CHCl ₃	√
Toluene	√	Water	X

Validation of Architecture

A. Gel Permeation Chromatography (GPC), SEC Profile:

Molecular weights were determined by Agilent Technologie 1260 Infinity II GPC/SEC System equipped with Triple detector (RI, Viscometer, RALS 90° and LS 15°) and three columns (PLgel, 7.5x300 mm, 5µm-10µm, 10⁵-10⁶Å). THF (stabilized BHT) with 1%(v/v%) TEA was the eluent. The flow rate was 1.0 ml/min.

Chromatogram Plot

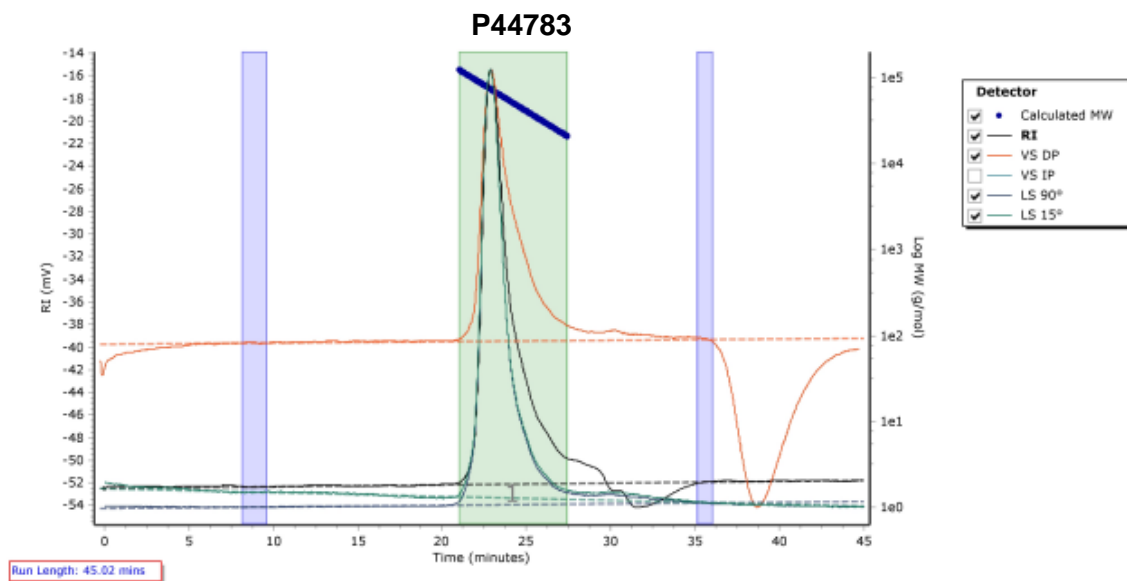

Molecular Weight Averages

Peak	Mp (g/mol)	Mn (g/mol)	Mw (g/mol)	Mz (g/mol)	Mz+1 (g/mol)	Mv (g/mol)	PD
Peak 1	72963	55404	62027	67238	71270	64944	1.12

B. NMR (H^1 NMR) of SMMA

SMMA sample was dissolved in CDCl_3 . ^1H NMR spectra was determined using a 500 MHz. Bruker Avance III spectrometer.

