


Product Profile

Identification

Product Name: Poly(glycidyl methacrylate)

Product Lot Number: P14093-R-GMA

Product Chemical Architecture:




Composition:

Mn (g/mole)	22,000
Mw (g/mole)	23,500
Mw/Mn	1.10
Tg	72°C
dn/dc (mL/g)	0.084 in THF

Method of Synthesis

Poly(glycidyl methacrylate) is obtained by living anionic /GTP polymerization of glycidyl methacrylate. The reaction scheme used for the polymer synthesis is shown below:

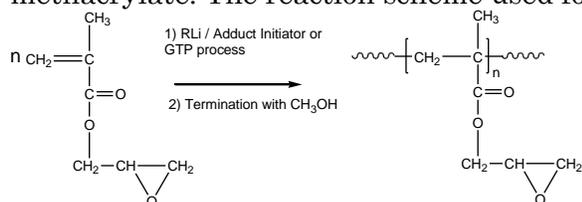

Solubility in different solvents

THF	√	Alcohol	X
1,4-dioxane	√	CHCl ₃	√


Validation of Architecture

A. Gel Permeation Chromatography (GPC), SEC- Profile:

Molecular weights were determined by Agilent Technologie 1260 Infinity II GPC/SEC System equipped with Triple detector (RI, Viscometer, RALS 90o and LS 15o) and three columns (PLgel, 7.5x300 mm, 5µm-10µm, 105-106Å). THF (stabilized BHT) with 1%(v/v%) TEA was the eluent. The flow rate was 1.0 ml/min.

P14093


Chromatogram Plot

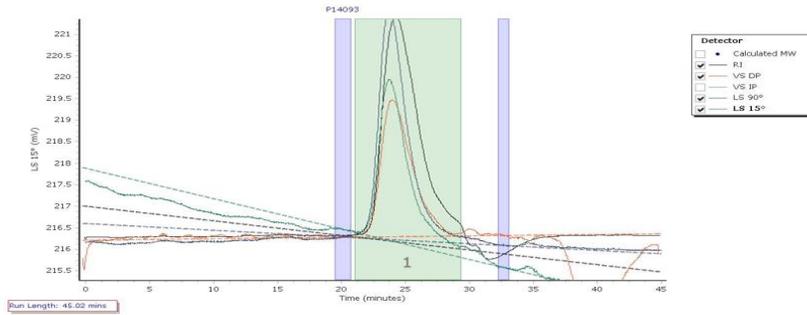

Molecular Weight Averages

Peak	Mp (g/mol)	Mn (g/mol)	Mw (g/mol)	Mz (g/mol)	Mz+1 (g/mol)	Mv (g/mol)	PD
Peak 1	25974	22234	23613	24844	25928	24896	1.062

B. 1H-NMR of the polymer

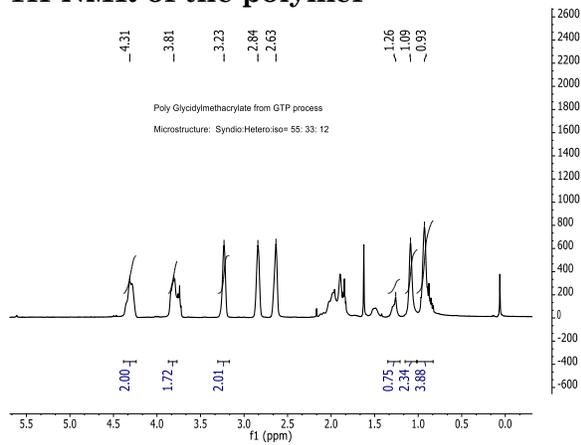

C. DSC thermogram of the polymer:

