


## Product Profile

### Identification

**Product Name:** Poly(styrene-b-ethylene oxide)

**Product Lot Number:** P44816-SEO

**CAS #:** Not Available **Product Chemical Architecture:**

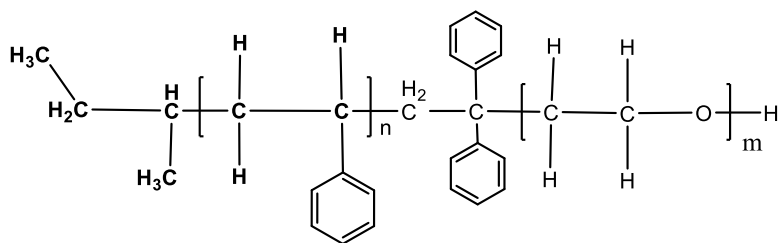

**Composition:**

Composition (S-b-EO)	29,000-b-51,000
EO mole%	64
Mn (g/mole)	80,000
Mw (g/mole)	84,000
Mw/Mn	1.05
dn/dc (mL/g) in THF at 30 °C	0.110

### Method of Synthesis

The polymer is synthesized by anionic polymerization process.

**Solubility in different solvents:**

THF	√	DMF	√
Alcohol	X	CHCl <sub>3</sub>	√
Toluene	√	Water	X

### Validation of Architecture


#### A. Gel Permeation Chromatography (GPC), SEC Profile:

Molecular weights were determined by Agilent Technologie 1260 Infinity II GPC/SEC System equipped with Triple detector (RI, Viscometer, RALS 90° and LS 15°) and three columns (PLgel, 7.5x300 mm, 5µm-10µm, 10<sup>5</sup>-10<sup>6</sup>Å). THF (stabilized BHT) with 1%(v/v%) TEA was the eluent. The flow rate was 1.0 ml/min.



Chromatogram Plot

P44816

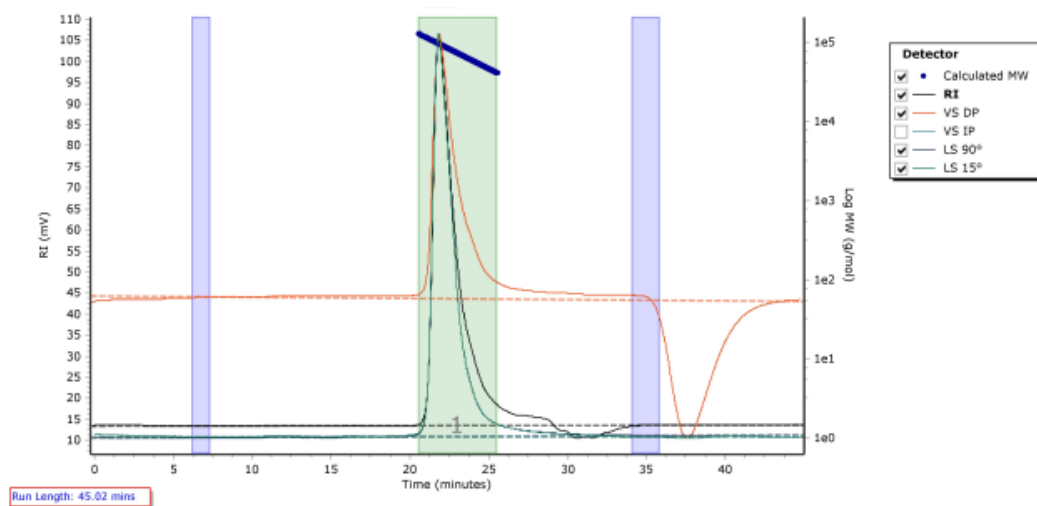


Molecular Weight Averages

Peak	Mp (g/mol)	Mn (g/mol)	Mw (g/mol)	Mz (g/mol)	Mz+1 (g/mol)	Mv (g/mol)	PD
Peak 1	95947	80234	83968	87095	89682	0	1.047

## B. NMR (H<sup>1</sup>NMR) of SMMA

SMMA sample was dissolved in CDCl<sub>3</sub>. <sup>1</sup>H NMR spectra was determined using a 500 MHz. Bruker Avance III spectrometer.

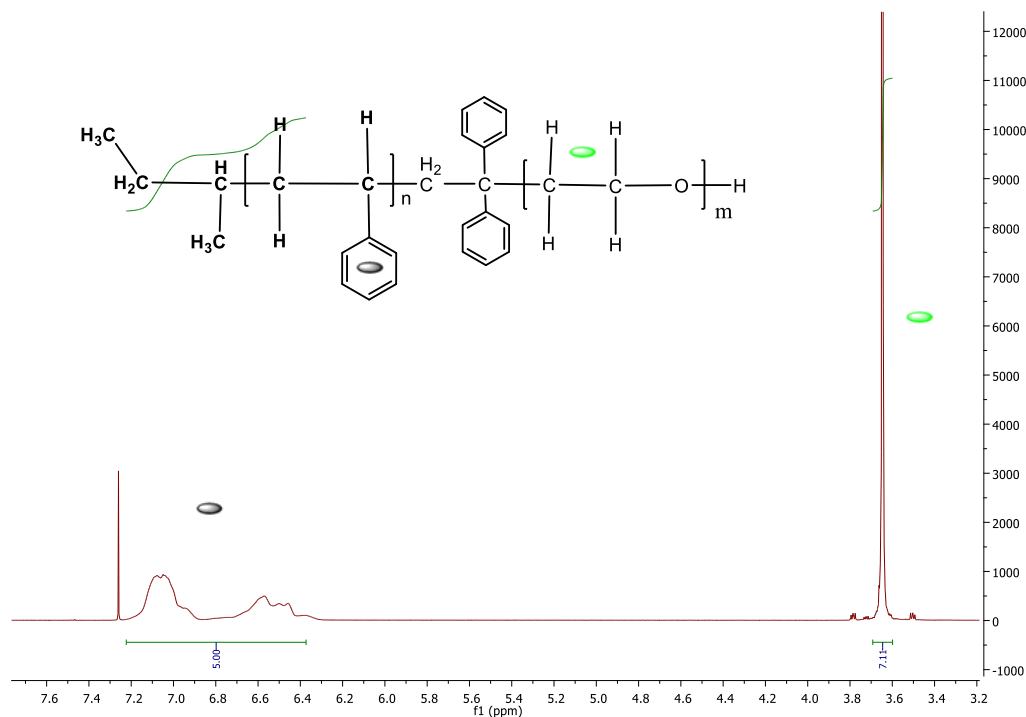

124 avenue Avro, Dorval (Montreal)  
 Quebec H9P 2X8 Canada  
 Phone : +1-514-421-5517 or +1-514-421-5506  
[support@polymersource.com](mailto:support@polymersource.com)  
[www.polymersource.ca](http://www.polymersource.ca)