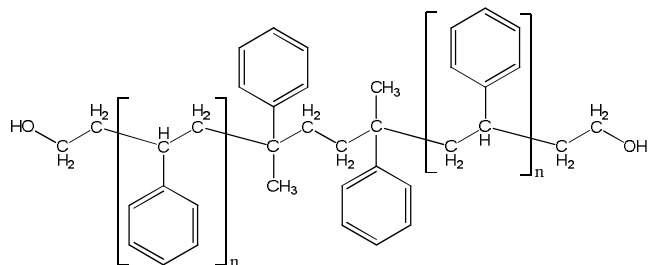


Sample Name:

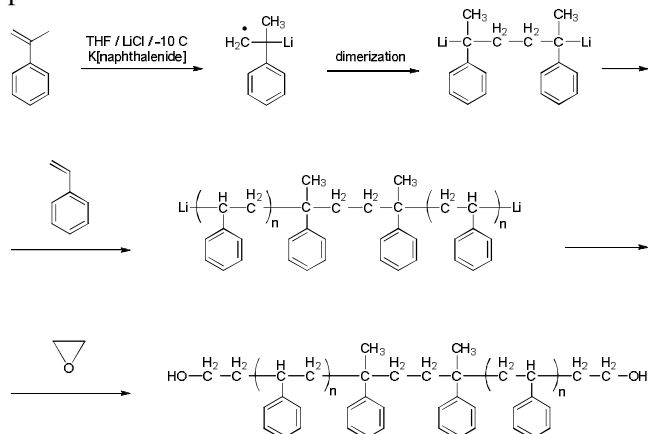
α,ω -Di(hydroxy)-terminated polystyrene,
(with α -methyl styrene dimer group in the middle of polymer chain)

Sample # P1132-S2OH**Structure:****Composition:**

$M_n \times 10^3$ (g/mol)	M_w/M_n
54.5	1.06

Synthesis procedure:

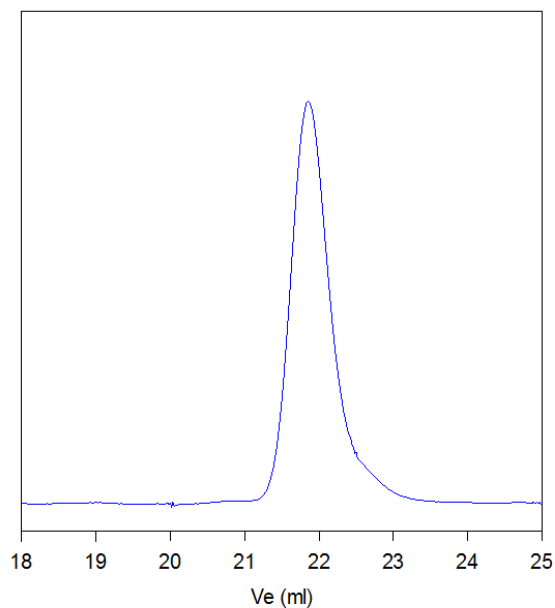
α,ω -Di(hydroxy)-terminated polystyrene was prepared by living anionic polymerization of styrene using a bifunctional initiator in THF followed by termination with ethylene oxide. The scheme of reaction is presented below:

**Characterization:**

The molecular weight and polydispersity index of the polymer were determined by size exclusion chromatography (SEC) using a Varian liquid chromatograph equipped with a UV and refractive index detectors.

Solubility:

Polystyrene is soluble in toluene, THF, chloroform; and it precipitates from cold methanol, water.

SEC elugram of the polymer:**P1132-S2OH**

Size exclusion chromatography of α,ω -dihydroxy terminated polystyrene.
 $M_n=54500$, $M_w=57500$, $M_z=61000$, $PI=1.06$, functionality=1.92.