
Product Profile

Identification

Product Name: POLY(2-VINYL PYRIDINE)
Synonym(s): P2VP
Linear Formula: $(C_7H_7N)_n$
CAS: 25014-15-7
Product Lot Number: P45773-2VP
Product Chemical Architecture:



Composition:

Mn (g/mole)	**3,500**
MW (g/mole)	**4,000**
Mw/Mn	**1.25**
dn/dc (mL/g)	**0.167 in THF**

Method of Synthesis

Poly(2-vinyl pyridine) is synthesized by living anionic polymerization of 2-vinyl pyridine using an adduct of Sec-butyllithium and diphenyl ethylene. Polymerization is carried out in THF at –78 ºC. Polymerization reaction is terminated using degassed methanol.


Solubility in different solvents

THF	√	DMF	√
Methanol	√	CHCl3	√
Toluene (Hot)	√	DMSO	√

Validation of Architecture

A. <u>Gel Permeation Chromatography (GPC), SEC- Profile:</u>


Molecular weights were determined by Agilent Technologies 1260 Infinity II GPC/SEC System equipped with Triple detector (RI, Viscometer, RALS 90º and LALS 15º) and three columns (PLgel 5 um, 10 um × 2). THF with 1% (v/v) triethylamine) was the eluent. The flow rate was 1.0 ml/min.

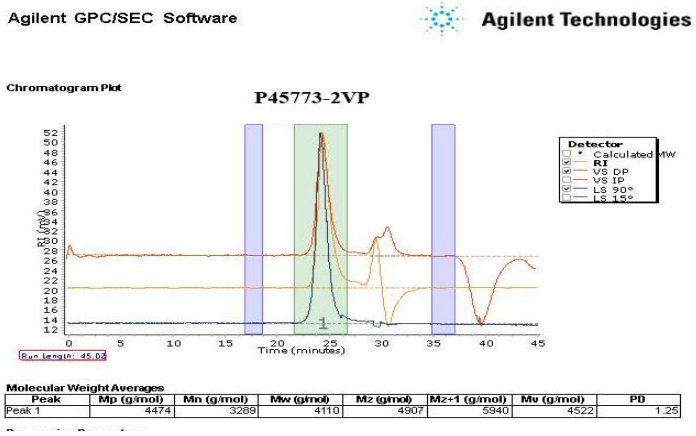


124 avenue Avro, Dorval (Montreal)
Quebec H9P 2X8 Canada
Phone : +1-514-421-5517 or +1-514-421-5506
support@polymersource.com
www.polymersource.ca

B. Thermal analysis results:

Dependence of glass transition temperature (T_g) of P2VP from its molecular weight:

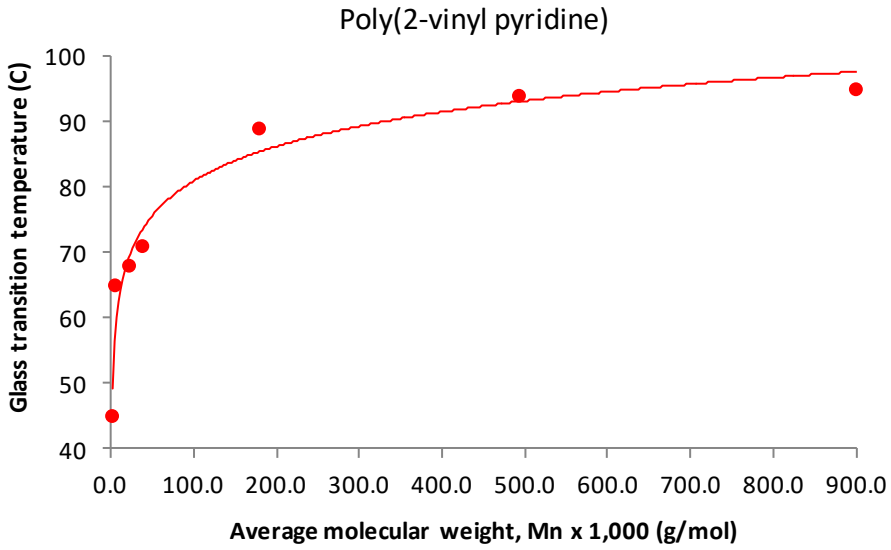

C. NMR (HNMR) OF P2VP in $CDCl_3$, general

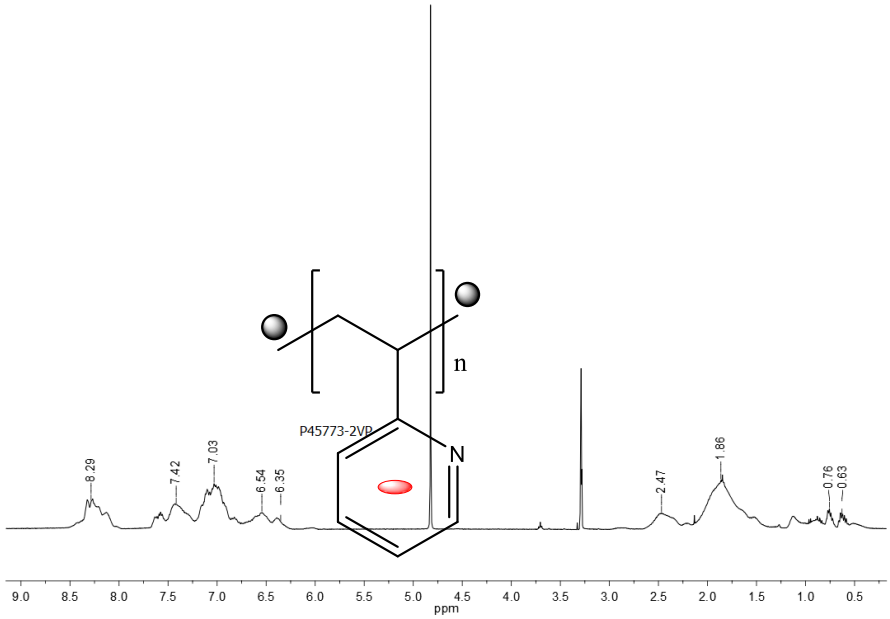

124 avenue Avro, Dorval (Montreal)
Quebec H9P 2X8 Canada
Phone : +1-514-421-5517 or +1-514-421-5506
support@polymersource.com
www.polymersource.ca