


Sample Name: Polybutadiene
(rich in 1,4 microstructure)

Sample #: P11479-Bd
1,4 rich microstructure (cis 68%, trans 27% and
1,2 contents 5%)

1,4 rich microstructure:




Composition:

$\text{Mn} \times 10^3$	PDI
98.2	1.06

Synthesis Procedure:

Polybutadiene (1,4-rich) is obtained by living anionic polymerization in toluene or cyclohexane. The reaction scheme is shown below:

1,4 addition:



Characterization:

The molecular weight and polydispersity index (PDI) are obtained by size exclusion chromatography (SEC) in THF. SEC analysis was performed on a Varian liquid chromatograph equipped with refractive and UV light scattering detectors. Three SEC columns from Supelco (G6000-4000-2000 HXL) were used with triple detectors from Viscotek Co.

Polymer microstructure can be confirmed by ^1H -NMR where the spectrum of 1,2-polybutadiene contains of 1 vinylic proton signal at 5.4 ppm and 2 vinylic protons at 5.0 ppm but the spectrum of 1,4-polybutadiene only contains vinylic signals at 5.4 ppm.


Solubility:

Polybutadiene is soluble in THF, toluene, hexane, pentane and cyclohexane and precipitates from methanol and ethanol.

SEC of the Product

Sample ID: P11479-Bd

Concentration (mg/mL)	4.4050
Sample dn/dc (mL/g)	0.1270
Method File	PS80K-May-2013-0000.vcm
Column Set	3x PL 1113-6300
System	System 1

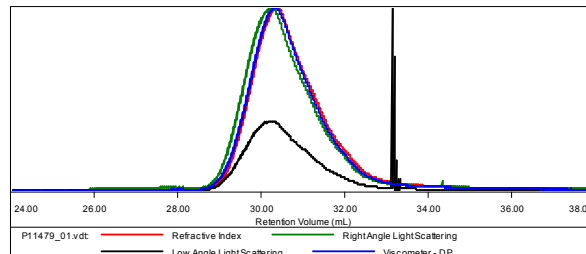

Sample	Mn	Mw	Mp	Mw/Mn	IV
P11479_01.vdt	98,201	104,695	97,597	1.066	3.0265

