


Sample Name:  
**Poly(acrylic acid) (by RAFT process)**  
 Sample #: **P14688B-AA**

Structure:

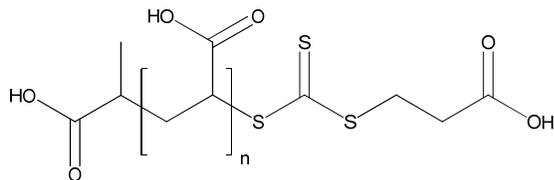


Composition:

Mw x 10 <sup>3</sup>	PDI
23.0	1.33

Synthesis Procedure:

Polyacrylic acid was synthesized by RAFT polymerization of acrylic acid using 2,2'-azobis isobutyrate (CAS 2589-57-3) as initiator and xanthate as chain transfer agent:

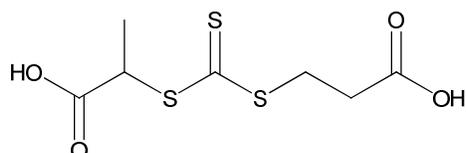

Poly(acrylic acid) synthesized was then converted to its sodium salt.



Characterization:

The molecular weight and polydispersity index (PDI) are obtained by size exclusion chromatography (SEC) in THF. For the analysis purposes of its molecular weights polyacrylic acid was converted to its n-butyl ester and characterized in THF on a Varian liquid chromatograph equipped with refractive and UV light scattering detectors. Three SEC columns from Supelco (G6000-4000-2000 HXL) were used with dual detectors model 270 from Viscotek Co.

Solubility:

Poly(acrylic acid) sodium salt is soluble in water.

**HNMR of the Poly acrylic acid run in CD3OD:**

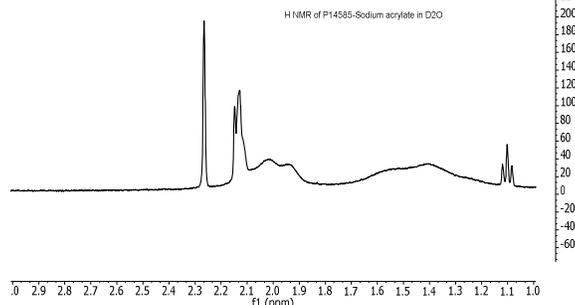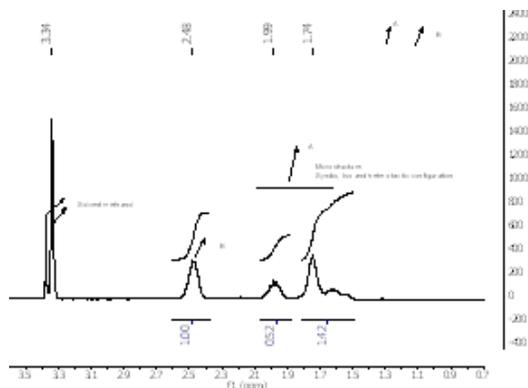


**SEC of Homopolymer Precursor for the Sodium salt**  
**SEC of the Poly n Butyl acrylate after converting PAA to**  
**PnBuA for the determination of its molecular weights**


**Poly acrylic acid Mn on the basis of above characterization:**

**SEC analysis in H2O using an aqueous**  
**buffer (NaHCO3 0.05 M, NaNO3 0.1 M, triethanolamine 0.02**  
**Sample ID: P14688-nBuA**

Concentration (mg/mL)	1.6500
Sample dn/dc (mL/g)	0.0640
Method File	PS80K-Feb25-2014-0000.vcm
Column Set	3x PL 1113-6300
System	System 1

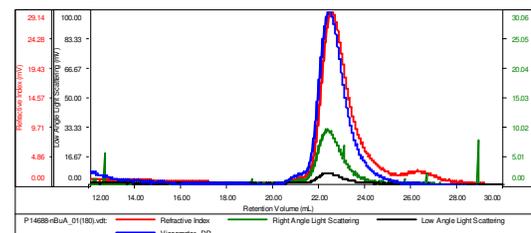

Sample	Mn	Mw	Mp	Mw/Mn	IV
P14688-nBuA_01(180).vdt	40,911	54,565	60,922	1.334	0.6529

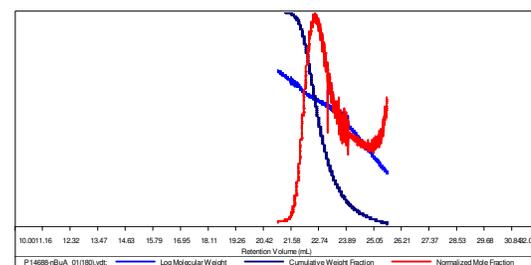

**References:**

1. Ph. Teyssie, Ph. Bayard, R. Jerome, **S. K. Varshney**, and J. S. Wang, *35th IUPAC International Union of Pure & Applied Chemistry International Symposium on Macromolecules* 1994, 67.
2. R. Fayt, R. Forte, C. Jacobs, R. Jerome, T. Ouhadi, Ph. Teyssie and **S. K. Varshney**, *Macromolecules*, 1987, 20, 1442-1444.
3. Jerome, R. Forte, **S. K. Varshney**, R. Fayt, and Ph. Teyssie, "The Anionic Polymerization of Alkylacrylates: A Challenge" in the Recent Advances in Mechanistic and Synthetic Aspects of Polymerization: M. Fontanille and A. Guyot Ed., NATO ASI Series C 215, 101 (1987), *CA Vol. 108*, 12, 094992.
4. Ph. Teyssie, R. Fayt, C. Jacobs, R. Jerome, L. Leemans, and **S. K. Varshney** *Am. Chem. Soc., Polym. Prepr.* 1988, 28, 2, 52-53