


Sample Name: Poly (methyl methacrylate)
Syndiotactic rich contents >79%
Sample #: P15007-MMA

Structure:

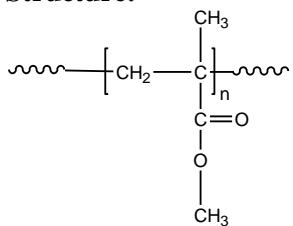


Composition:

Mn x 10 ³	PDI
171.5	1.09

Synthesis Procedure:

Syndiotactic Poly(methyl methacrylate) is obtained by living anionic polymerization using sec.BuLi as initiator end capped with a unit of diphenyl ethylene or few units of α -methylstyrene. The polymerization of MMA monomer is carried out in THF at -78°C in the presence of LiCl as additive. For further details please see the following references.⁽¹⁻⁴⁾. The polymerization scheme can be illustrated as follows:

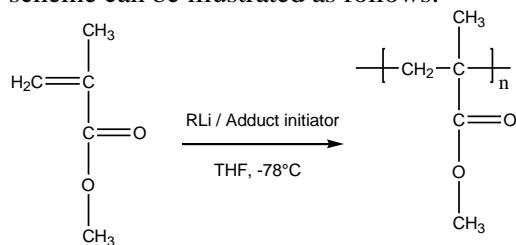

Characterization:


The molecular weight and polydispersity index (PDI) are obtained by size exclusion chromatography (SEC) in THF. SEC analysis was performed on a Varian liquid chromatograph equipped with refractive and UV light scattering detectors. Three SEC columns from Supelco (G6000-4000-2000 HXL) were used with triple detectors from Viscotek Co. ¹H NMR analysis was carried out on Varian instrument at 500MHz.

Thermal analysis of the samples was carried out using a differential scanning calorimeter (TA Q100) at a heating rate of 10°C/min. The inflection glass transition temperature (T_g) of the sample has been considered.

Solubility:

Poly(methyl methacrylate) is soluble in THF, CHCl_3 , toluene and dioxane. The polymer precipitates from hexanes, methanol and ethanol.


H NMR spectrum of the Sample:

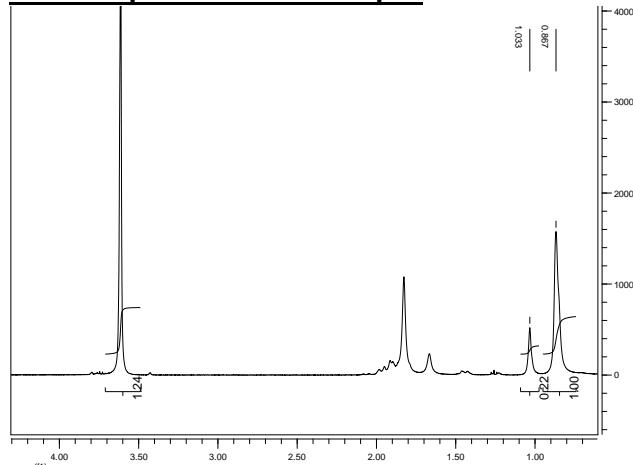


SEC elugram of the Sample:

Sample ID: P15007

Concentration	5.1347
Sample dn/dc	0.0890
Method File	PS99K-0927-0000.vcm
Column Set	3x PL 1113-6300
System	System 1

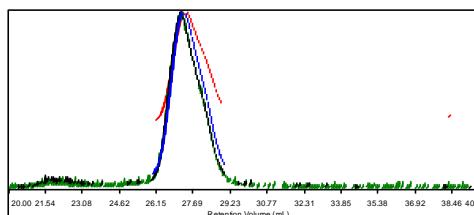

Sample	Mn	Mw	Mz	Mw/Mn	IV	Rh
2010-09-28_15:15:05_P15007_01.vdt	171,496	187,159	210,342	1.091	0.5117	14.89

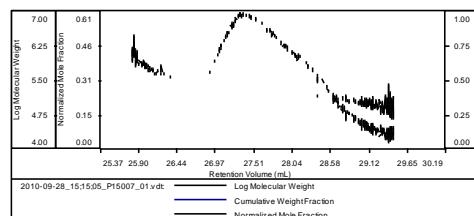

References for further information:

- (a) S. K. Varshney, R. Fayt, Ph. Teyssie, US Patent 5,629,393, 1997
(b) Ph. Bayard, R. Fayt, Ph. Teyssie and S. K. Varshney, Vuillemin B, Phillippe, H, US patent 5,677,387, 1997.(c) Ph. Bayard, R. Fayt, Ph. Teyssie and S. K. Varshney, B, Vuillemin, H. Phillippe, US patent 5,687,534, 1997.(d) S. K. Varshney, R. Fayt, Ph. Teyssie, US Patent 5,723,559, 1998. (e) Ph. Teyssie, S. K. Varshney, R. Jerome, R. Fayt US patent, 4,826,941., 1989.
- Ph. Teyssie, Ph. Bayard, R. Jerome, S. K. Varshney, and J. S. Wang, 35th IUPAC International Union of Pure & Applied Chemistry International Symposium on Macromolecules" 1994, 67.
- Ph. Teyssie, R. Fayt, J. P. Hautekeer, C. Jacobs, R. Jerome, L. Leemans and S. K. Varshney Makromolekular Chemie, Macromol. Symp., 1990, 32, 61-73.
- S. K. Varshney, J. P. Hautekeer, R. Fayt, R. Jerome, and Ph. Teyssie Macromolecules, 1990, 23, 2618-2622.