


Sample Name: Poly(methyl acrylate), RAFT-agent terminated

Sample #: P16025-MA-RAFT macroinitiator

Structure:

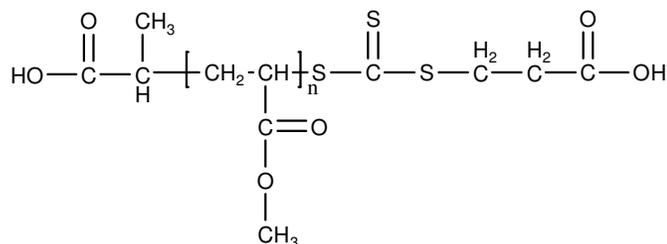

Composition:

$M_n \times 10^3$	PDI
21.0	1.16

Synthesis Procedure:

The poly(methyl acrylate) was prepared by RAFT controlled process of methyl acrylate monomer in 1,4-dioxane.

Characterization:

The molecular weight and polydispersity index (PDI) are obtained by size exclusion chromatography (SEC) in DMF. SEC analysis was performed on a Varian liquid chromatograph equipped with refractive and light scattering detectors.


Solubility:

Poly(methyl acrylate) is soluble in THF and DMF This polymer precipitates from methanol containing 10-50% water.

SEC elugram of the polymer:

P16025-1-MA

Conc (mg/mL)	15.7166
dn/dc (mL/g)	0.0600
Method	PS90k-May-25-2016-0000.vcm
Solvent	DMF w0.023M LiBr
Column	PSS

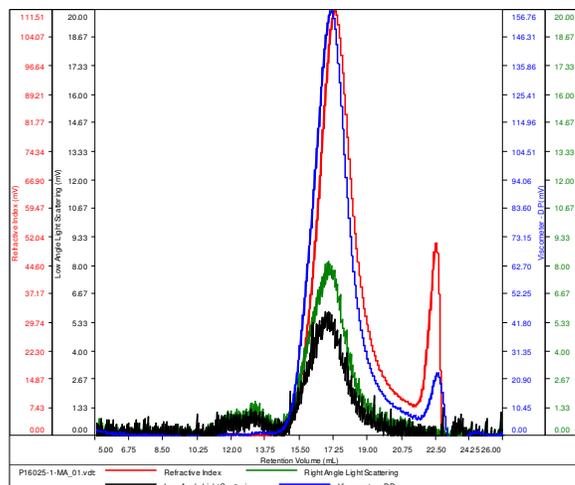

Sample	Mn	Mw	Mp	Mw/Mn	IV
P16025-1-MA_01.vcl	21,080	24,413	22,187	1.158	0.2482

References:

1. Ph. Teyssie, Ph. Bayard, R. Jerome, **S. K. Varshney**, and J. S. Wang, *35th IUPAC International Union of Pure & Applied Chemistry International Symposium on Macromolecules* 1994, 67.
2. R. Fayt, R. Forte, C. Jacobs, R. Jerome, T. Ouhadi, Ph. Teyssie and **S. K. Varshney**, *Macromolecules*, 1987, 20, 1442-1444.
3. Jerome, R. Forte, **S. K. Varshney**, R. Fayt, and Ph. Teyssie, "The Anionic Polymerization of Alkylacrylates: A Challenge" in the Recent Advances in Mechanistic and Synthetic Aspects of Polymerization: M. Fontanille and A. Guyot Ed., NATO ASI Series C 215, 101 (1987), CA Vol. 108, 12, 094992.
4. Ph. Teyssie, R. Fayt, C. Jacobs, R. Jerome, L. Leemans, and **S. K. Varshney** *Am. Chem. Soc., Polym. Prepr.* 1988, 28, 2, 52-53.