




Sample Name: P18480-20S  
20- arms Poly styrene

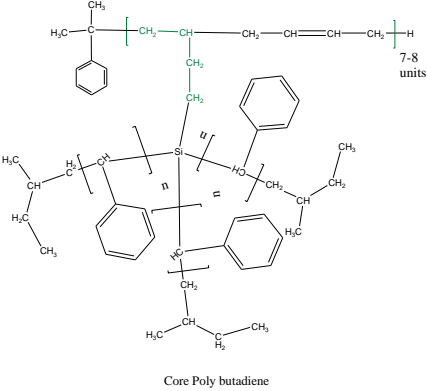


Mn x 10 <sup>3</sup> (total)	PDI
24.5	1.3
Mn of each arm: (1.2)	

Synthesis Procedure:

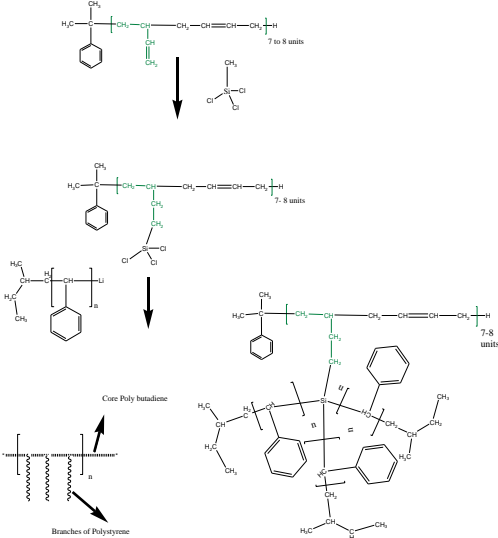


Linker : PBd:

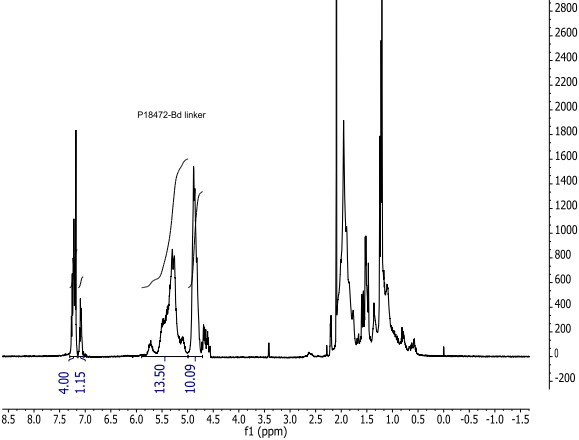

SEC of the Polymer: (eah branch of Polystyrene)  
Sample ID: P18480-S Branch


Concentration (mg/mL)	1.3189
Sample dn/dc (mL/g)	0.1850
Method File	PS80K-Feb10-2014-0000.vcm
Column Set	3x PL 1113-6300
System	System 1

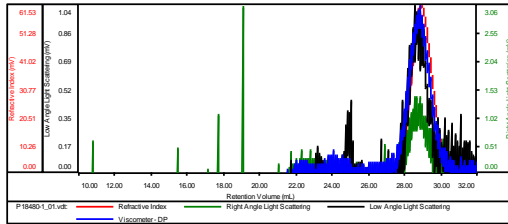

Sample	Mn	Mw	Mp	Mw/Mn	IV
P18480-1_01.vdt	1,238	1,380	1,007	1.115	0.0883

Sample ID: P18480-S Star

Concentration (mg/mL)	1.4615
Sample dn/dc (mL/g)	0.1850
Method File	PS80K-Feb10-2014-0000.vcm
Column Set	3x PL 1113-6300
System	System 1

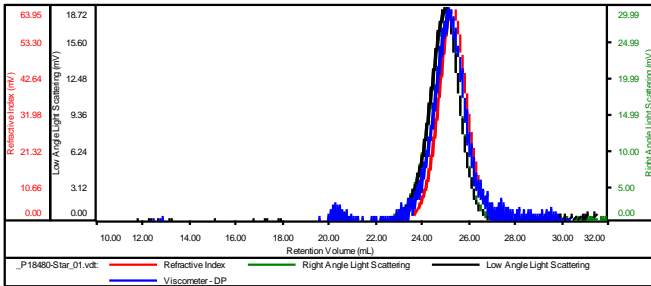

Sample	Mn	Mw	Mp	Mw/Mn	IV
_P18480-Star_01.vdt	24,405	32,479	27,668	1.331	0.1116