




Sample Name: P18480A-13S
13- arms Poly styrene

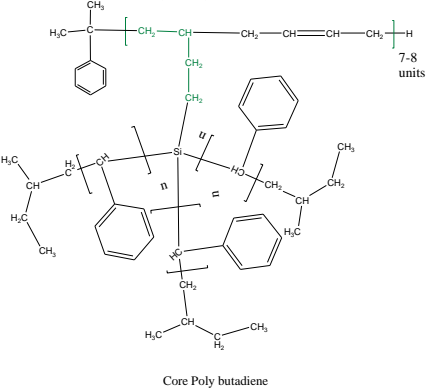


Mn x 10 ³ (total)	PDI
16.0	1.16
Mn of each arm: (1.2)	

Synthesis Procedure:

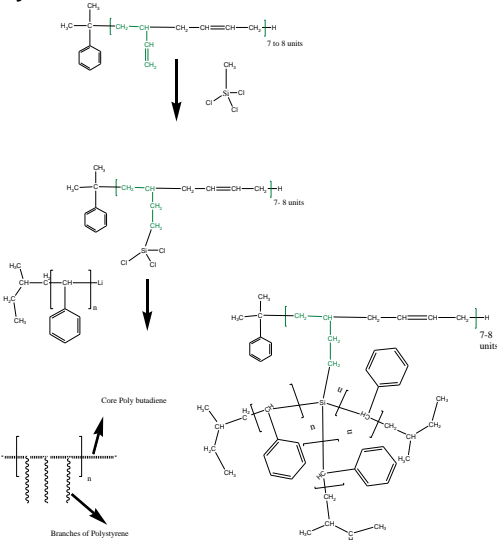


Linker : PBd:

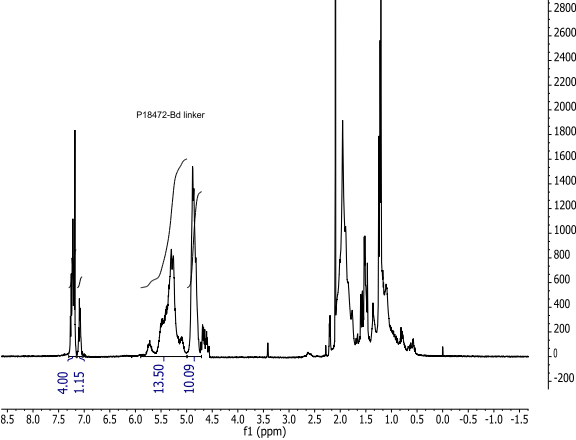


SEC of the Polymer: (eah branch of Polystyrene)
Sample ID: P18480-S Branch

Concentration (mg/mL)	1.3189
Sample dn/dc (mL/g)	0.1850
Method File	PS80K-Feb10-2014-0000.vcm
Column Set	3x PL 1113-6300
System	System 1

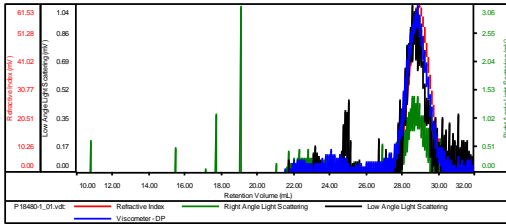


Sample	Mn	Mw	Mp	Mw/Mn	IV
P18480-S1.vdt	1,298	1,390	1,007	1.115	0.0683

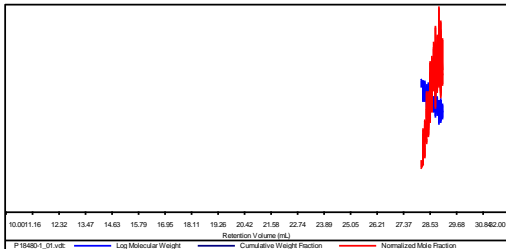

Sample ID: P18480A-S Star

Concentration (mg/mL)	4.9885
Sample dn/dc (mL/g)	0.1850
Method File	PS80K-Feb10-2014-0000.vcm
Column Set	3x PL 1113-6300
System	System 1

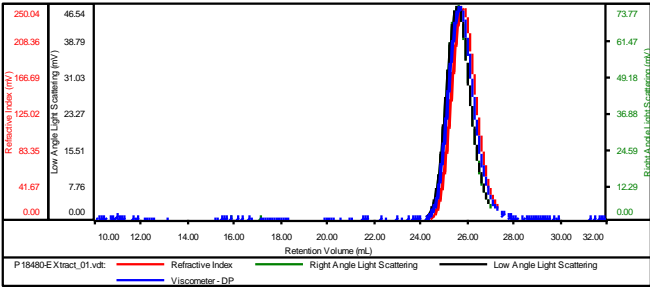

Sample	Mn	Mw	Mp	Mw/Mn	IV
P18480-Extract_01.vdt	16,270	18,827	18,022	1.157	0.1017

