


Sample Name: Poly(styrene-b-2-vinyl pyridine)

Sample #: P18548-S2VP

#### Structure:

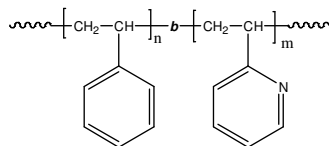


#### Composition:

Mn x 10 <sup>3</sup> S-b-2VP	PDI
58.5-b-67.0	1.15
T <sub>g</sub> for 2VP block: Not distinct 95°C for 100k homopolymer)	T <sub>g</sub> for PS block: 104 °C

#### Synthesis Procedure:

Poly(styrene-b-2-vinyl pyridine) is prepared by living anionic polymerization in THF at -78 °C in the presence of LiCl an additive. Polystyrene macroanions were end capped with a unit of diphenyl ethylene (DPE) before adding 2-vinylpyridine (2VP) monomer. For further details please see our published articles<sup>1,2</sup>. The scheme of the reaction is illustrated below:

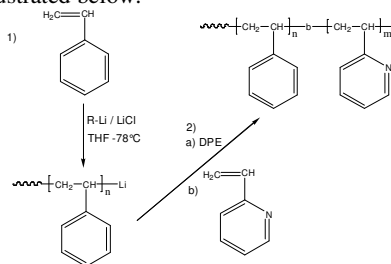


#### Characterization:

An aliquot of the anionic polystyrene block was terminated before addition of 2VP and analyzed by size exclusion chromatography (SEC) to obtain the molecular weight and polydispersity index (PDI). The Block copolymer composition was then calculated from <sup>1</sup>H-NMR spectroscopy by comparing the peak area of the 2VP proton at 8.2 ppm with the peak area of the aromatic protons of polystyrene at 6.3-7.2 ppm. The composition of the block copolymer can also be determined by titration in acetic acid/HClO<sub>4</sub> using crystal violet indicator. Copolymer PDI is determined by SEC.

Thermal analysis of the samples was carried out on a TA Q100 differential scanning calorimeter at a heating rate of 10°C/min. The midpoint of the slope change of the heat flow plot of the second heating scan was considered as the glass transition temperature (T<sub>g</sub>).


#### <sup>1</sup>H-NMR Spectrum of the Polymer

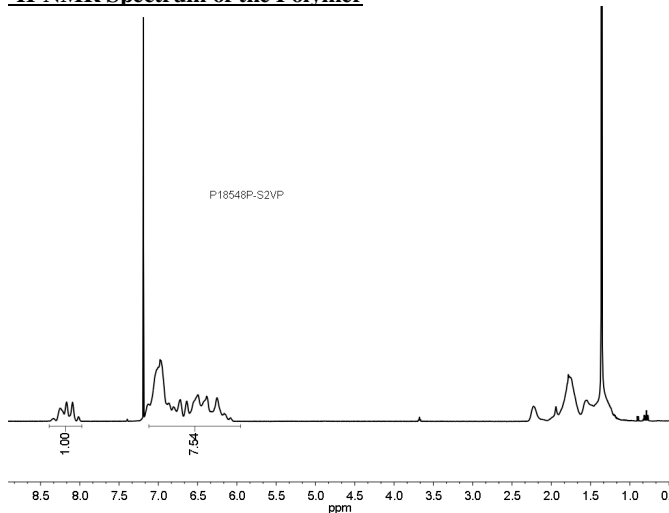

#### SEC:

Sample ID: P18548-S


Concentration (mg/mL)	3.4033
Sample dn/dc (mL/g)	0.1850
Method File	PS80K-March13-2014-0000.vcm
Column Set	3x PL 1113-6300
System	System 1

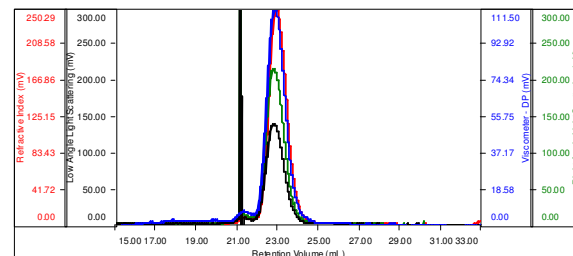

Sample	Mn	Mw	Mp	Mw/Mn	IV
P18548-S_01.vdt	58,676	61,154	60,553	1.042	0.6959


Sample ID: P18548-S2VP

Concentration (mg/mL)	3.2655
Sample dn/dc (mL/g)	0.1790
Method File	PS80K-March13-2014-0000.vcm
Column Set	3x PL 1113-6300
System	System 1

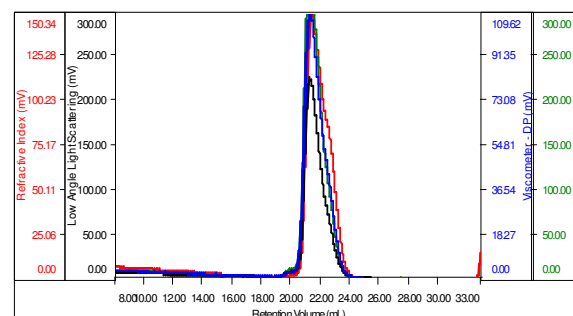

Sample	Mn	Mw	Mp	Mw/Mn	IV
P18548P-S2VP_01.vdt	125,731	144,123	168,880	1.146	0.9590

#### DSC thermogram for the polymer:

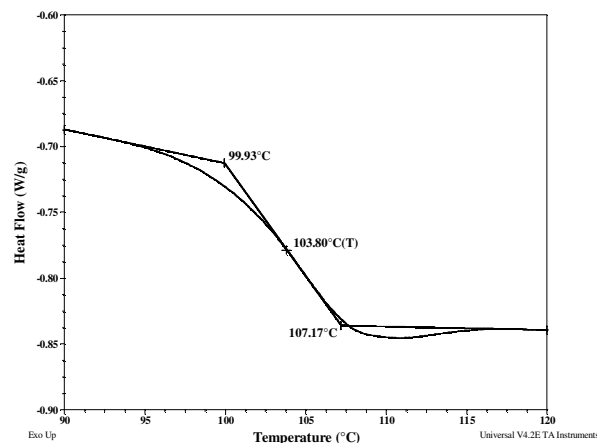

#### References:

- (1). S. K. Varshney, X. F. Zhong and A. Eisenberg Macromolecules, **1993**, 26, 701-706.
- (2). Z.Gao, S. K. Varshney, S. Wong, A. Eisenberg Macromolecules, **1994**, 27, 7923-7927.