


**Sample Name:**  
**ω-Hydroxy Terminated Polystyrene**

**Sample #: P18845- SOH**

**Structure:**

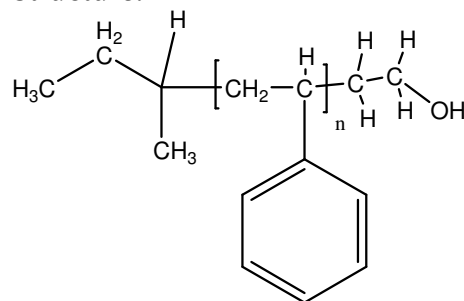

**Composition:**

Mn x 10 <sup>3</sup>	PDI
8.5	1.02
T <sub>g</sub> (°C)	80

**Synthesis Procedure:**

ω-hydroxy terminated polystyrene was prepared by living anionic polymerization using OH protected initiator.

**Characterization:**

The molecular weight and polydispersity index of this polymer were determined by size exclusion chromatography (SEC) using a Varian liquid chromatograph equipped with a UV and refractive index detector. Polymer functionality was determined by titration with NaOH solution using phenolphthalein as the indicator.

**Thermal analysis:**


Thermal analysis of the samples was carried out using a differential scanning calorimeter (TA Q100) at a heating rate of 10°C/min. The inflection glass transition temperature (T<sub>g</sub>) has been considered.

**Solubility:**


Polymer is soluble in toluene, THF, CHCl<sub>3</sub> and can be precipitated in water and cold methanol.

**SEC of Sample:**  
**Sample ID: P18845-SOH**

Concentration (mg/mL)	15.8481
Sample ch/dic (mL/g)	0.1850
Method File	PS80K-aug.st 12/2014/0000.vcm
Column Set	3x PL 11136300
Solvent	THF

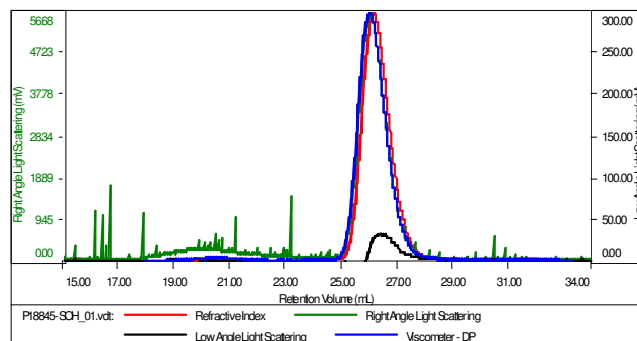

Sample	Mn	Mw	Mp	Mw/Mn	IV
P18845-SOH_01.vdt	8,512	8,744	8,755	1.027	0.0722

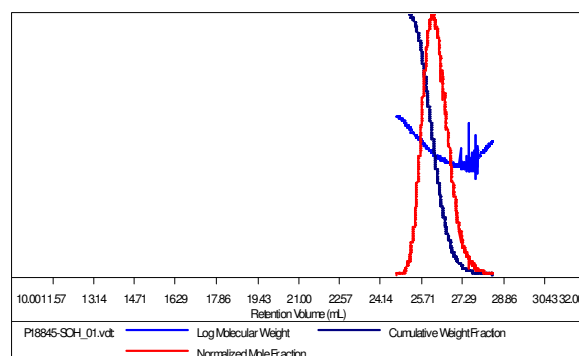

**DSC thermogram for the sample:**

