


Sample Name: Poly(neopentyl methacrylate)

Sample #: P18920X-NPMA

Structure:




Composition:

Mn x 10 ³	Mw/Mn
76.0	1.9

Synthesis Procedure:

Poly(neopentyl methacrylate) was obtained by living anionic polymerization of neopentyl methacrylate. The reaction scheme used for the polymer synthesis is shown below:

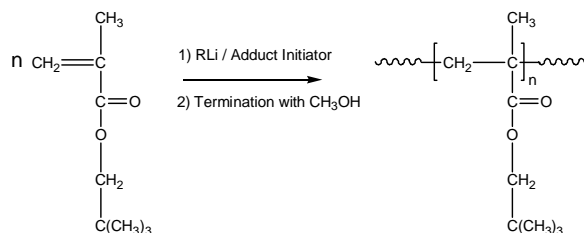

Characterization:

The molecular weight and polydispersity index (Mw/Mn) of poly(neopentyl methacrylate) were obtained by size exclusion chromatography (SEC).


Solubility:

Poly(neopentyl methacrylate) is soluble in THF, $CHCl_3$, toluene and dioxane. The polymer precipitates from hexanes, methanol and ethanol.

SEC elugram:

Sample ID: P18920x-NPMA

Concentration (mg/mL)	4.9014
Sample dn/dc (mL/g)	0.0840
Method File	PS80K-1028-2014-0000.vcm
Column Set	3x PL 11136300
Solvent	THF

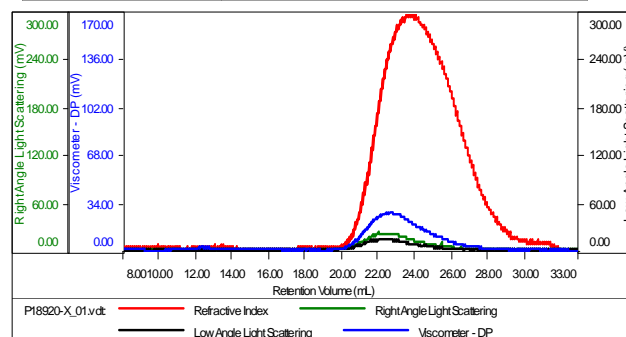

Sample	MW Number Average (Da)	MW Weight Average (Da)	MW at Peak (Da)	Polydispersity	Intrinsic Viscosity (dL/g)
P18920-X_01.vdt	75,882	146,151	137,627	1.926	0.4233