


Sample Name: Polyisoprene, *rich in 1,4-addition*

Sample #: P19013-lp



Composition:

Mn x 10 ³	Mw/Mn
6.0	1.03

Microstructure:

1,4-addition		1,2- & 3,4-addition
Cis-isomer	Trans-isomer	
89 %	11 %	—


Synthesis Procedure:

Polyisoprene was obtained by living anionic polymerization.


Characterization:

The microstructure of polymer was calculated from ¹H NMR data. Molecular weight and polydispersity index (M_w/M_n) of the polymer were determined by size exclusion chromatography (SEC).





Proton shifts in ¹H NMR:

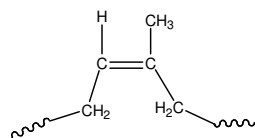


Cis 1,4 addition

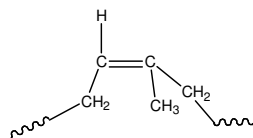

Trans 1,4 addition

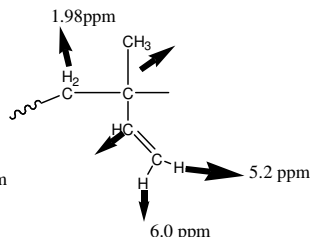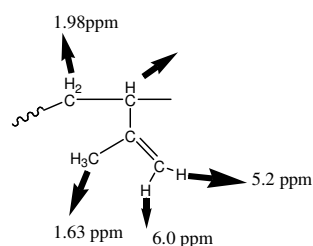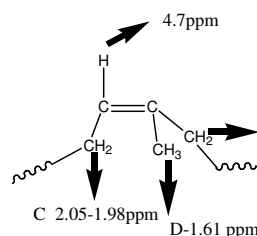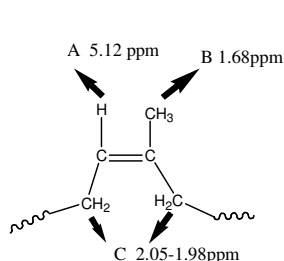


¹H NMR (500 MHz; CDCl₃) of polyisoprene:

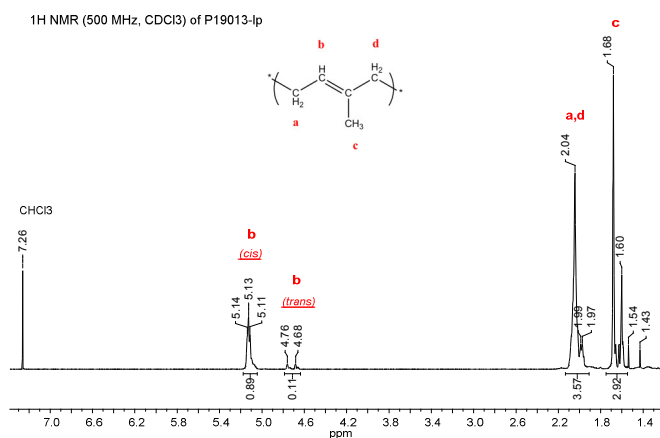

SEC elugram of polyisoprene:

Sample ID: P19013-PIP

Concentration (mg/mL)	6.6015
Sample dn/dc (mL/g)	0.1250
Method File	PS80K-NDV27-2014-0001.vcm
Column Set	3x PL 1113-6300
Solvent	THF

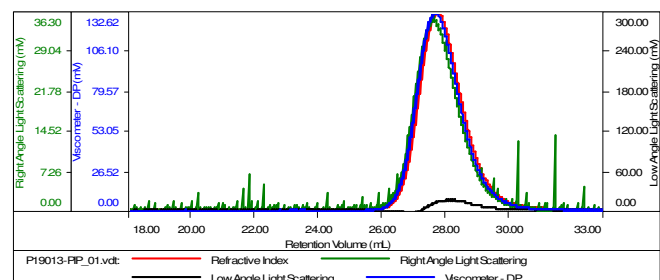

Sample	MW Number Average (Da)	MW Weight Average (Da)	MW at Peak (Da)	Polydispersity	Intrinsic Viscosity (dL/g)
P19013-PIP_01.vdt	6,003	6,198	6,152	1.032	0.7538