


Sample Name: Poly(styrene-co-4-chlorostyrene)
random copolymer

Sample # P19641A-S4ClSran

Structure:

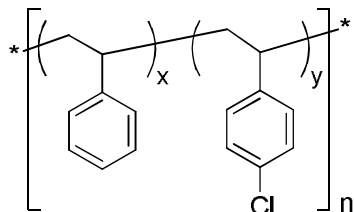

Composition:

$M_n \times 10^3$ (g/mol)	M_w/M_n
19.5	1.3
Content of poly(4-chlorostyrene):	7 mol%
T_g of PS-co-P4ClS:	103 °C

Synthesis procedure:

The copolymer was prepared by radical polymerization of styrene and 4-chlorostyrene in presence of TEMPO.

Characterization:

Molecular weight and polydispersity index (M_w/M_n) of the copolymer were obtained by size exclusion chromatography (SEC). Analysis of the copolymer by ^1H NMR spectroscopy did not reveal any presence of monomer impurities. Content of poly(4-chlorostyrene) in PS-co-P4ClS copolymer was determined by elemental analysis.

Thermal analysis:

Thermal analysis of the copolymer was performed on a TA Q100 differential scanning calorimeter (DSC) at a heating rate of 10°C/min. The midpoint of the slope change of the heat flow plot of the second heating scan was considered as the glass transition temperature (T_g).


Solubility:

PS-co-P4ClS is soluble in CHCl_3 , THF, DMF, toluene. The copolymer precipitates from hexane.

Elemental analysis of PS-co-P4ClS:


Sample: P19641A Lab ID: 2016-A-9367		Received: 2016-01-19		
Analysis	Method	Result	Basis	Sample Amount Used
C: Carbon	GLI Procedure ME-14	89.68 %	As Received	1.957 mg
Cl: Chlorine	GLI Procedure ME-4A	2.35 %	As Received	63.75 mg
H: Hydrogen	GLI Procedure ME-14	7.66 %	As Received	1.957 mg

^1H -NMR (500 MHz, CDCl_3) spectrum:

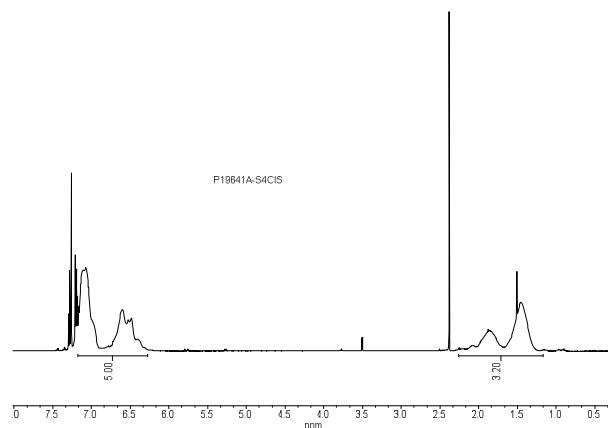


SEC elugram of the random copolymer:

Sample ID-PD19641A-4ClS	
Concentration (mg/mL)	4.0365
Sample divd: (mL/g)	0.1850
Method File	PS80K-June30-2015-0000.vcm
Column Set	3x PL 1113-6300
Solvent	THF

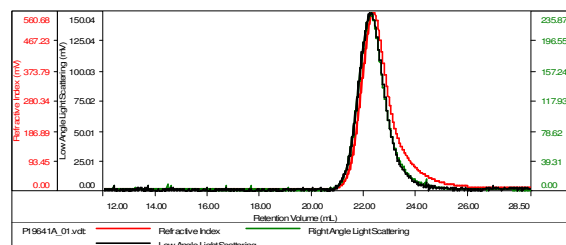

Sample	MW Number Average (Da)	MW Weight Average (Da)	MW at Peak (Da)	Polydispersity	Intrinsic Viscosity (dL/g)
P19641A_01.vct	19,379	25,177	27,592	1.299	0.6779

DSC thermogram of PS-co-P4ClS:

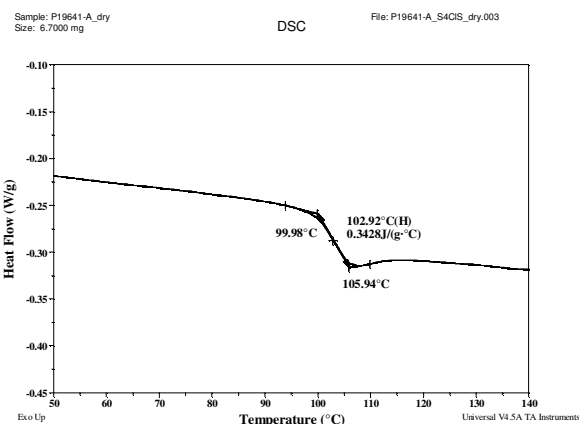

Reference: Thermal transition of T_g for S4ClSran copolymer ($M_n=19.5\text{--}22.5$ kDa).

4ClS:	7 mol%	8 mol%	19 mol%	35 mol%	36 mol%	54 mol%
T_g :	103°C	105°C	107°C	112°C	114°C	123°C