


Sample Name: Poly(neopentyl methacrylate)

Sample #: P19812-NPMA


Structure:

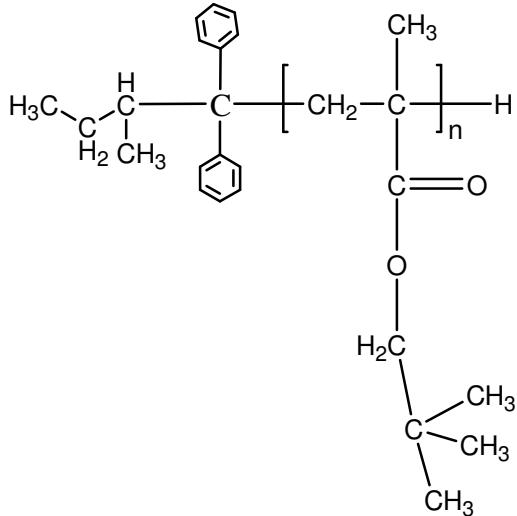

SEC elugram of the homopolymer:

Sample ID-P19812-NPMA

Concentration (mg/mL)	0.576
Sample dn/dc (mL/g)	0.0840
Method File	PS80K-March2016-0001.vcm
Column Set	3x PL 1113-6300
Solvent	THF

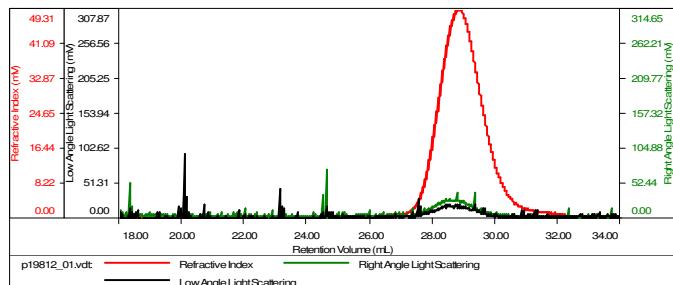

Sample	M _n (Da)	M _w (Da)	M _w /M _n	IV (dL/g)	R _h (nm)	Ret Vol (mL)
p19812_01.vdt	72,096	86,332	1.197	3.2294	20.79	28.813

Composition:

M _n × 10 ³ (g/mol)	M _w /M _n
72.0	1.19

Synthesis procedure:

The polymer was synthesized by anionic Process

Characterization:

The molecular weight and polydispersity index (M_w/M_n) of poly(neopentyl methacrylate) were obtained by size exclusion chromatography (SEC).

Solubility:

Poly(neopentyl methacrylate) is soluble in THF, chloroform, toluene, and dioxane. The polymer precipitates from hexanes, methanol, and ethanol.