


Sample Name: Poly(D,L-lactide)

Sample #: P20198A-LA (DL-Form)

Structure:

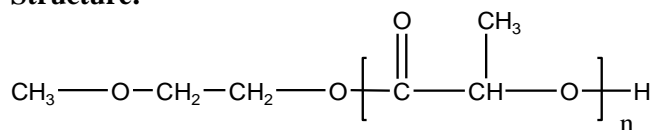


Composition:

Mn, g/mol	Mw, g/mol	PDI(Mw/Mn)
52,000	58,000	1.12

Synthesis Procedure:

The polymerization of 3,6-dimethyl-1,4-dioxane-2,5-dione was carried out in bulk.



Purification:

The polymeric solution was precipitated from CHCl_3 and/or acetone into a large excess of ether.

Solubility:

Poly(DL-lactide) is soluble in toluene, THF, CHCl_3 and CH_2Cl_2 . The polymer is insoluble in methanol, hexane and ether.


Characterization:

The molecular weight and polydispersity index (PDI) were obtained by size exclusion chromatography with a static light-scattering detector.

SEC elugram of the polylactide Sample:

Sample ID: P20198A -LA (DL form)

Concentration (mg/mL)	2.6025
Sample dn/dc (mL/g)	0.0450
Method File	PS80K-March6-2015-0000.vcm
Column Set	3x PL 1113-6300
Solvent	THF

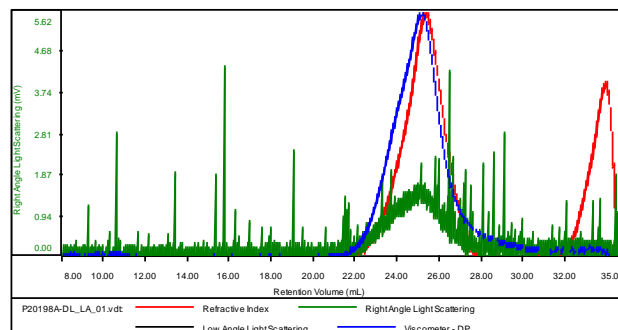

Sample	MW Number Average (Da)	MW Weight Average (Da)	MW at Peak (Da)	Polydispersity	Intrinsic Viscosity (dL/g)
P20198A-DL_LA_01.vdt	52,113	58,260	44,730	1.118	0.1708