


Sample Name: Poly(2-vinyl pyridine)

Sample #: P4081A-2VP

Structure:

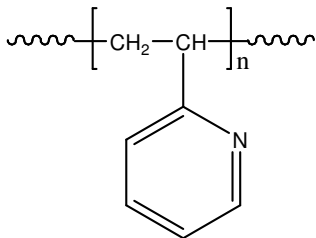

Composition:


Mn x 10 ³	PDI
12.0	1.08
By HNMR 14.0	
With respect to Polystyrene 9.0	

Synthesis Procedure:

Poly(2-vinyl pyridine) is obtained by living anionic polymerization of 2-vinyl pyridine using an adduct of Sec. butyllithium and diphenyl ethylene.

Polymerization is carried out in THF at -78 °C.

Polymerization reaction is terminated using degassed methanol. The reaction scheme is illustrated as follows:

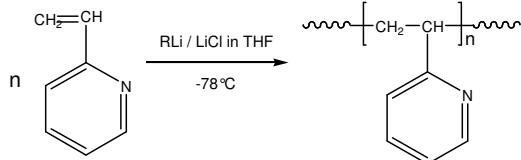

Characterization:

The molecular weight and polydispersity index (PDI) are obtained by size exclusion chromatography (SEC) in THF. SEC analysis was performed on a Varian liquid chromatograph equipped with refractive and UV light scattering detectors. Three SEC columns from Supelco (G6000-4000-2000 HXL) were used with triple detectors from Viscotek Co.

Thermal analysis was performed on TA Instruments Q100 differential scanning calorimeter (DSC) under a nitrogen atmosphere. The glass transition temperature (T_g) of the polymer was measured at a scan rate of 10°C/min shortly after creating thermal history of the sample.


Solubility:

Poly 2 vinylpyridine is soluble in DMF, THF, toluene, methanol, ethanol and CHCl₃. It precipitates from water and hexanes, ether.


SEC elugram of the polymer:

Sample ID: P4081


Concentration	4.2503
Sample dn/dc	0.1670
Method File	PS99K-0927-0000.vcm
Column Set	3x PL 1113-6300
System	System 1

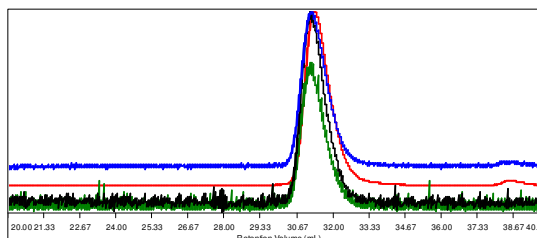

Sample	Mn	Mw	Mz	Mw/Mn	IV	Rh
2010-09-27_15:55:23_P4081_01.vdt	12,922	14,974	17,575	1.159	0.0925	3.62

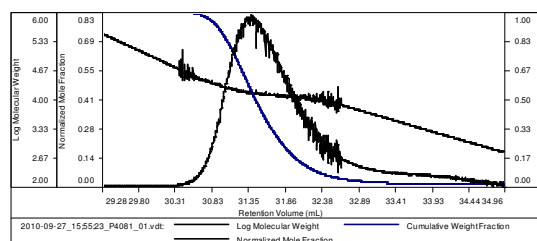

¹H NMR spectrum of the polymer:

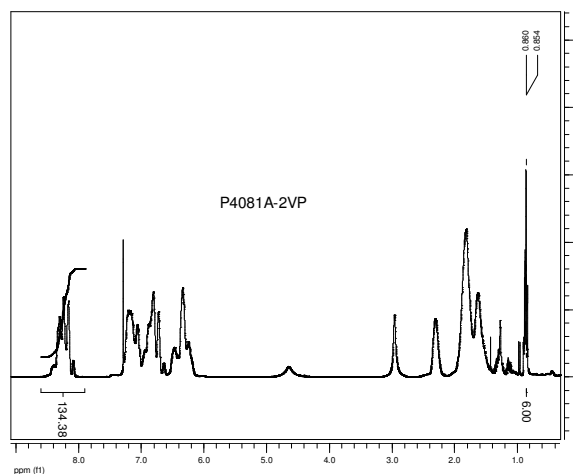

Relationship between T_g and Mn of P2VP:

