


Sample Name: Poly(t-butyl acrylate)

Sample #: P4906-tBuA

Structure:



Composition:

Mn x 10 ³	PDI
36.0	1.10

Synthesis Procedure:

Poly(t-butyl acrylate) is obtained by living anionic polymerization of t-butyl acrylate.¹⁻⁴

Characterization:

The molecular weight and polydispersity index (PDI) are obtained by size exclusion chromatography (SEC) in THF. SEC analysis was performed on a Varian liquid chromatograph equipped with refractive and UV light scattering detectors. Three SEC columns from Supelco (G6000-4000-2000 HXL) were used with triple detectors from Viscotek Co.

Thermal analysis of the samples was carried out using a differential scanning calorimeter (TA Q100) at a heating rate of 10°C/min. The inflection glass transition temperature (*T_g*) of the sample has been considered.

Solubility:


Poly(t-butyl acrylate) is soluble in THF, hexanes (low MW), toluene and CHCl₃. This polymer precipitates from ethanol and methanol containing 10-15% water.

***T_g* vs MW for selected poly t-butyl acrylate**

M _n × 10 ³	<i>T_g</i> (°C)	M _n × 10 ³	<i>T_g</i> (°C)
0.75	-15	11.6	28
1.4	-5	22	32
2	7	65	35
4.5	12	1128	38


SEC of Sample:

P 4906-tB u A

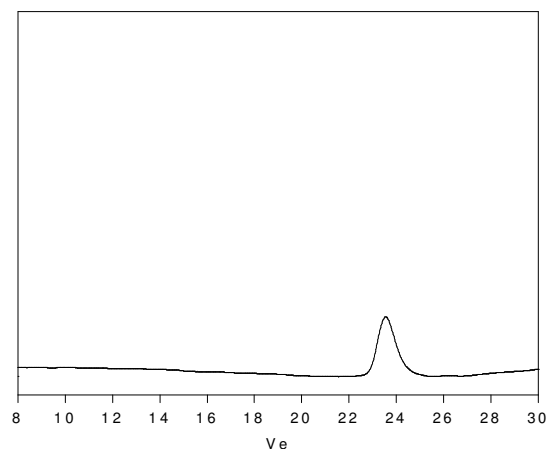

Size Exclusion Chromatography of Poly(t-butyl acrylate):
M_n=36000, M_w=39500, PDI=1.10

T_g of poly t-butyl acrylate as function of molecular weight

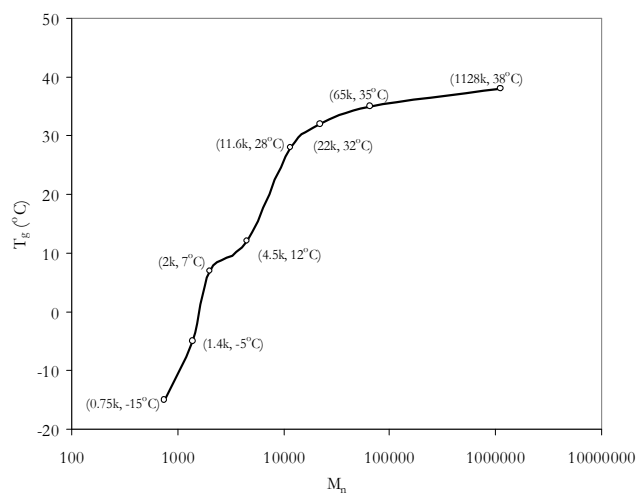

References:

1. Ph. Teyssie, Ph. Bayard, R. Jerome, **S. K. Varshney**, and J. S. Wang, *35th IUPAC International Union of Pure & Applied Chemistry International Symposium on Macromolecules* 1994, 67.
2. R. Fayt, R. Forte, C. Jacobs, R. Jerome, T. Ouhadi, Ph. Teyssie and **S. K. Varshney**, *Macromolecules*, 1987, 20, 1442-1444.
3. Jerome, R. Forte, **S. K. Varshney**, R. Fayt, and Ph. Teyssie, "The Anionic Polymerization of Alkylacrylates: A Challenge" in the Recent Advances in Mechanistic and Synthetic Aspects of Polymerization: M. Fontanille and A. Guyot Ed., NATO ASI Series C 215, 101 (1987), *CA Vol. 108*, 12, 094992.
4. Ph. Teyssie, R. Fayt, C. Jacobs, R. Jerome, L. Leemans, and **S. K. Varshney** *Am. Chem. Soc., Polym. Prepr.* 1988, 28, 2, 52-53