


Sample Name: Poly(N-isopropyl acrylamide) of Narrow molecular weights distribution

Sample #: P10505F7-NIPAM

Structure:




Composition:

Mn x 10 ³	PDI
65.0	1.15
Mv: 81.0	

Synthesis Procedure:


Poly(N-isopropyl acrylamide) is obtained by RAFT polymerization process.

Following catalyst was used:

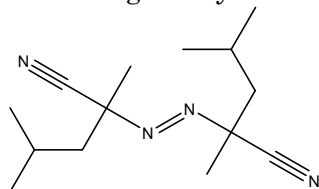

2,2-azobis (2,4-dimethyl valeronitrile)

RAFT reagent:

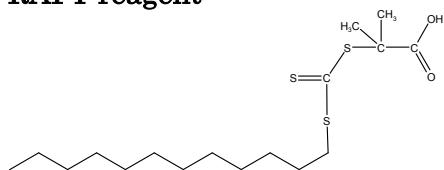

2-dodecylsulfanyl-2-methylpropionic acid

Characterization: The molecular weight and polydispersity index (PDI) were obtained by size exclusion chromatography (SEC) in THF and in DMF. SEC analysis was performed on a Varian liquid chromatograph equipped with refractive and UV light scattering detectors. Two SEC columns from Supelco (G6000-4000 HXL) were used with triple detectors from Viscotek Co.

Sample Preparation: Polymer sample for the GPC were prepared as reported in the literature (**Macromolecules, 2000,33,6738**). To avoid the effect of concentration and the amount of water present in the sample, on line triple detectors were used.

Viscosity measurement was carried out in a Ubbelohde viscometer at 25°C. Four solutions in methanol of different concentrations were measured. The intrinsic viscosity was obtained by extrapolation to c=0. From viscosity-molecular weight relationship $[\eta] = 2.99 \times 10^{-2} M^{0.64}$ (Makromolecular Chem. V180, P969, 1979), the viscosity average molecular weight was calculated accordingly.

DMF as eluent at 60 oC elution temperature was found efficient to avoid any adsorption of polymer


with the packing material of column. DMF containing LiBr as an additive was found efficient to avoid any adsorption effect of polymer. It was observed 0.05 to 0.1 M solution of LiBr in DMF was efficient to analyse polymer. In pure DMF with out any additive the molecular weight was found higher and Mw/Mn was broad.

Purification of polymer:

Unreacted monomer was removed by dissolving the product in cold water than warming the solution. The polymer separated out. This procedure was applied 2 times to remove the unreacted monomer. The obtained polymer was dissolved in acetone and fractionated from Hexane. After several fractionation to remove the low molecular weight fraction < 10% and to obtain fairly narrow molecular weight fraction polymer. Polymer was finally reprecipitated in cold hexane and dried at room temperature

SEC of the Polymer carried out in DMF

P10505F7-NIPAM

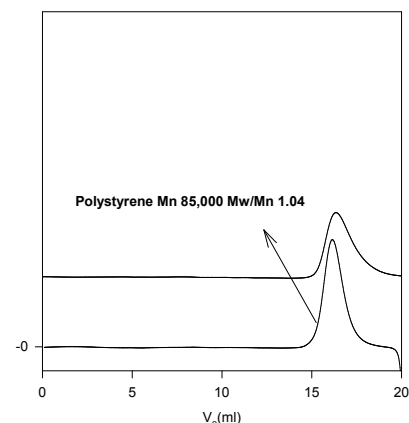

Size exclusion chromatography of N-Isopropyl Acrylamide in DMF/LiBr(0.05M) Molecular Weight Distribution with respect to Polystyrene Standards: Mn: 65,000 Mw: 74,500 Mw/Mn= 1.15

Thermogram for the sample

