


Sample Name: Poly(styrene-b-t-butyl acrylate)

Sample #: P745-StBuA

Structure:

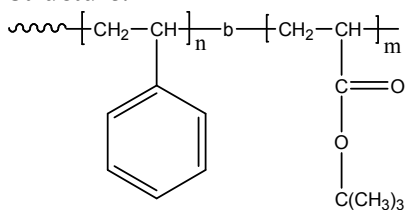

Composition:

Mn x 10 ³ S-b-BuA	PDI
1.9-B-31.9	1.49

Glass transition temperature at a glance

T _g for PS block	Not distinct
T _g for tBuA block	46°C

Synthesis Procedure:

Poly(styrene-b-t-butyl acrylate) is prepared by living anionic polymerization with sequence addition of styrene followed by t-butyl acrylate.

Characterization:

An aliquot of the polystyrene block was terminated before addition of methyl acrylate and analyzed by size exclusion chromatography (SEC) to obtain the molecular weight and polydispersity index (PDI). The final block copolymer composition was calculated from ¹H-NMR spectroscopy by comparing the peak area of the styrene protons at 6.3-7.2 ppm with the peak area of t-butyl acrylate protons at 1.43 ppm. Block copolymer PDI is determined by SEC.

Thermal analysis


Thermal analysis of the samples was carried out on a TA Q100 differential scanning calorimeter at a heating rate of 10°C/min. The midpoint of the slope change of the heat flow plot of the second heating scan was considered as the glass transition temperature (T_g).

Solubility:

Poly(styrene-b-t-butyl acrylate) is soluble in CH₂Cl₂, THF, Dioxane toluene and precipitated out from methanol/water.

SEC of the block copolymer:


P745-StBuA

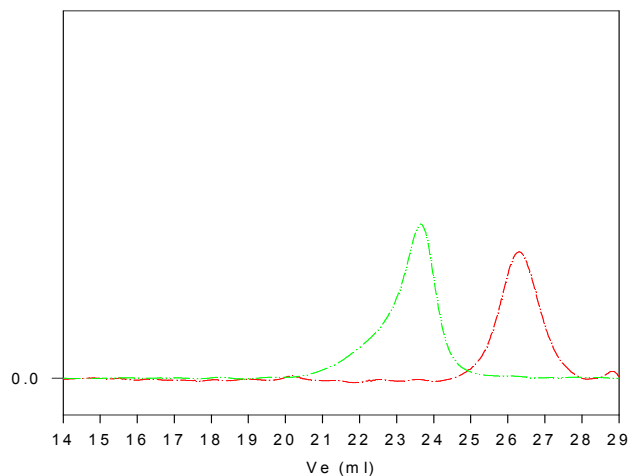

Size exclusion chromatography of polystyrene-b-poly(t-butyl acrylate)
Precursor of Polystyrene-b-Poly(acrylic acid) (P758-SAA):

Polystyrene, M_n=1900, M_w=2200 PI=1.16
Block Copolymer PS(1900)-b-PtBuA(31900), PI=1.49

Thermogram for tBuA block

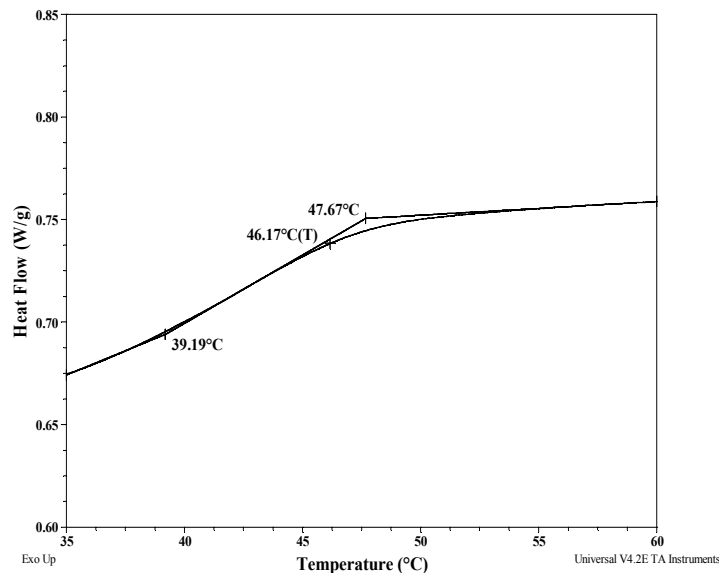

References:

Ph.Teyssie, R. Fayt, and **S. K. Varshney**, *Eur. Pat. Appl. Dec. 12, 1990. Eur. Pat.402204*

Patent Assignees-Norsolor S.A. France. CA Vol 114, 20, 186314.Catalyst for the the Anionic Living Polymerization (Meth)acrylates".

S. K. Varshney, R. Fayt and Ph. Teyssie *Eur. Pat. Appl. Dec. 12, 1990. Eur. Pat. 402219*

Patent Assignees- Norsolor S.A France. CA Vol 114, 22, 208036. Procedure and Anionic Polymerization Catalyst for Acrylic Monomers

Ph.Teyssie, R. Fayt, C. Jacobs, R. Jerome and **S. K. Varshney** "New Developments in the "Living" Anionic Polymerization of (Meth)Acrylic Esters" *CA Vol. 115, 135, 184032, Am.Chem.Soc.,Polym.Prepr.,1991, 31,1,299.*

