


**Sample Name: Deuterated Polystyrene  
(d<sub>8</sub>)- ethylene oxide (protonated)**

**Sample #: P8045-dPSEO**

**Structure:**

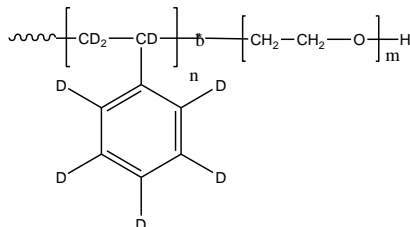

**Composition:**

Mn x 10 <sup>3</sup> (dPS-b-EO)	PDI
16.0-b-6.5	1.08

**Synthesis Procedure:**

Deuterated Poly(styrene-b-ethylene oxide) diblock copolymer is prepared by living anionic polymerization.


**Characterization:**

The molecular weight and polydispersity index (PDI) of the block copolymer are characterized by size exclusion chromatography (SEC). The composition of the block copolymer was calculated from <sup>1</sup>H-NMR by comparing the peak area of the phenyl polystyrene protons between 6.4 to 7.2 ppm (indicating about 1% protonated fraction) and the ethylene oxide protons at 3.65 ppm. This is given an approximate analysis. The yield of the polymer from the theoretical amount of deuterated styrene and protonated ethylene oxide monomer calculate also the compositions required.


**Solubility:**

The polymer is soluble in THF (at 35 °C), CHCl<sub>3</sub>, benzene, toluene, dioxane. Low molecular weight SEO with high contents of the polyethylene oxide block can also be solubilized in methanol and water.

**HNMR spectrum of the sample:**

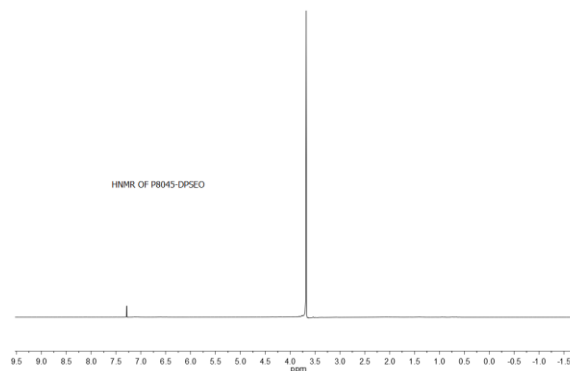


**DNMR spectrum of the polymer:**

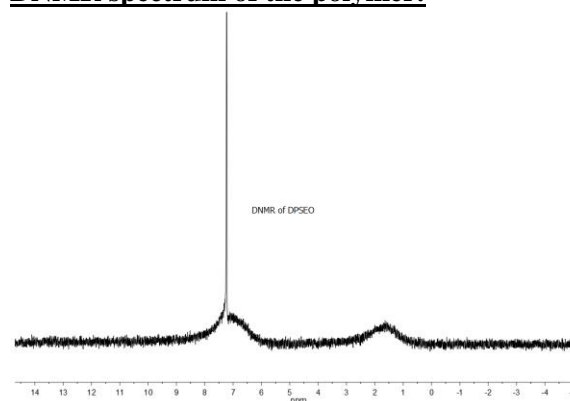

**SEC profile of the product:**

**P8045-dPSEO**

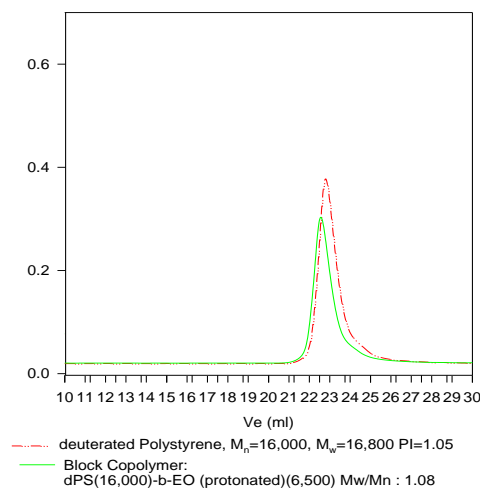


**References for further information:**

1. S. K. Varshney, R. Fayt, Ph. Teyssie, and J.P. Hautekeer US Patent 5,264,527 (1993)
2. S. K. Varshney, Jian-Xin Zhang US patent 7009,033 B3 2006.


## Thermal analysis of the sample # P8045-dPSEO:

Thermal analysis of the samples was carried out on a TA Q100 differential scanning calorimeter at a heating rate of 10°C/min. The midpoint of the slope change of the heat flow plot of the second heating scan was considered as the glass transition temperature ( $T_g$ ).

### Thermogram for the dPS block:

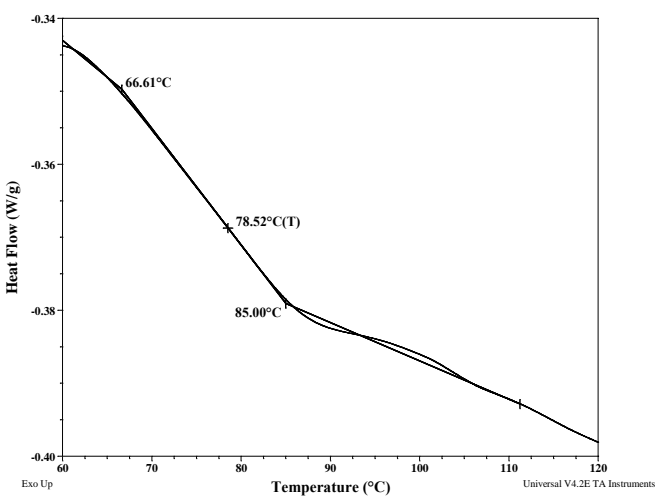

### For PEO block:

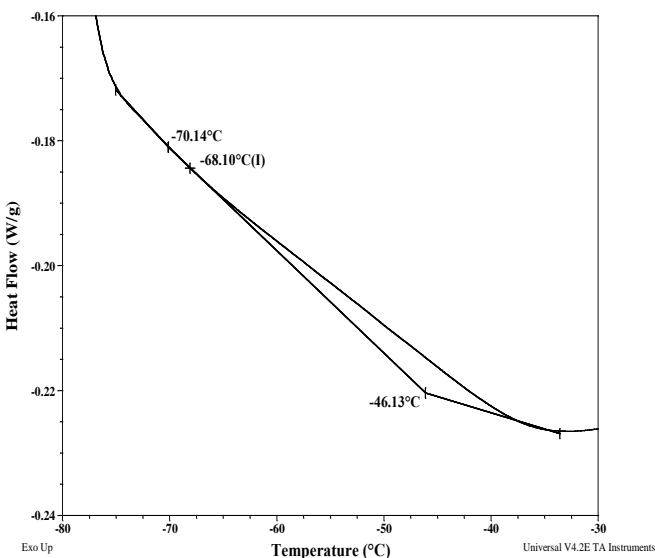

## Thermal analysis results at a glance

For PS block $T_g$ : 79°C		
For PEO block		
$T_g$ : -68°C	$T_m$ : 44°C	$T_c$ : Not found

### Melting curve for the PEO block

The melting temperature ( $T_m$ ) was taken as the maximum of the endothermic peak.

