


**Sample Name:** Poly(2-vinyl pyridine)

**Sample #:** P8098B-2VP

**Structure:**

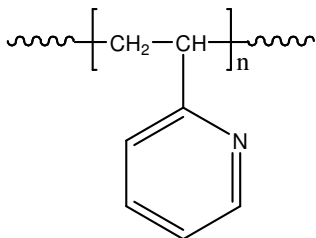


**Composition:**

$M_n \times 10^3$	PDI
1.2	1.25

**Synthesis Procedure:**

Poly(2-vinyl pyridine) is obtained by living anionic polymerization of 2-vinyl pyridine using an adduct of Sec. butyllithium and diphenyl ethylene-LiCl. Polymerization is carried out in THF at  $-78^\circ\text{C}$ . Polymerization reaction is terminated using degassed methanol. The reaction scheme is illustrated as follows:

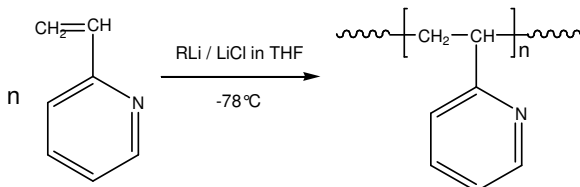

**Characterization:**

The molecular weight and polydispersity index (PDI) are obtained by size exclusion chromatography (SEC) in THF. SEC analysis was performed on a Varian liquid chromatograph equipped with refractive and UV light scattering detectors. Three SEC columns from Supelco (G6000-4000-2000 HXL) were used with triple detectors from Viscotek Co.


Thermal analysis was performed on TA Instruments Q100 differential scanning calorimeter (DSC) under a nitrogen atmosphere. The glass transition temperature ( $T_g$ ) of the polymer was measured at a scan rate of  $10^\circ\text{C}/\text{min}$  shortly after creating thermal history of the sample.

**Solubility:**

Poly 2 vinylpyridine is soluble in DMF, THF, toluene, methanol, ethanol and  $\text{CHCl}_3$ . It precipitates from water and hexanes, ether.

**SEC elugram of the polymer:**

P8098B-2VP

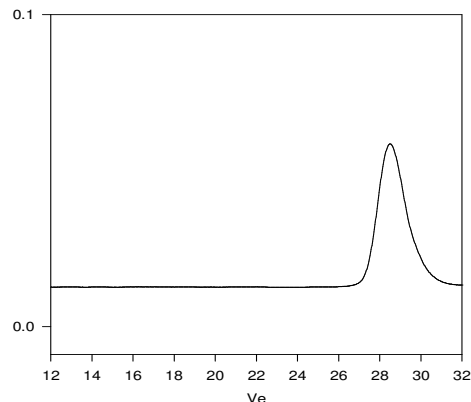


Size exclusion chromatography of poly(2-vinylpyridine) in THF

$M_n=1200$ ,  $M_w=1500$ ,  $PI=1.25$

$dn/dc$  in THF at  $35^\circ\text{C}$ :  $0.167\text{ml/g}$

$^1\text{H NMR } M_n: 1200$

**$^1\text{H NMR}$  spectrum of the Polymer:**

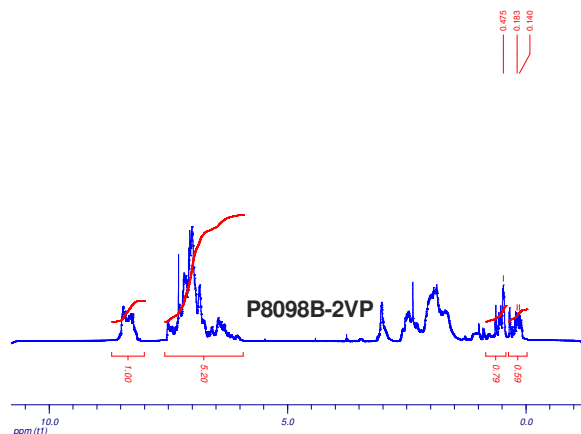

**Relationship between  $T_g$  and  $M_n$  of P2VP:**

