


Sample Name: Deuterated Poly(ethylene glycol)
Dihydroxy Terminated

Sample #: P8396-dPEO

Structure:



Composition:

Mn x 10 ³	PDI
17	1.15

Synthesis Procedure:

Deuterated Poly(ethylene glycol) is obtained by living anionic polymerization using α -wdipotassium alkoxide of ethylene glycol. Polymerization of freshly distilled deuterated ethylene oxide was carried out at room temperature for 24h followed by termination with acidic methanol. The obtained polymer was passed through neutral Al₂O₃ packed column and precipitated in ethyl ether at low temperature. Polymer was dried at room temperature for 24h.

Characterization:


The molecular weight and polydispersity index (PDI) are obtained by size exclusion chromatography.

Solubility:

Poly(ethyl glycol) is soluble in toluene, THF, water and CHCl₃. The polymer is insoluble in hexane, ether, isopropanol and cold ethanol.

SEC of Sample

P8396-dPEO

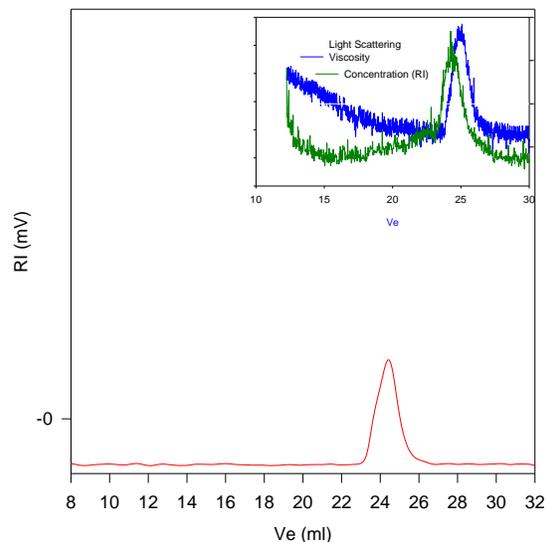

Size Exclusion Chromatography of deuterated poly ethylene glycol:

— $M_n = 17000$, $M_w = 19500$, $M_w/M_n = 1.15$
 dn/dc in THF at 35 °C: 0.62ml/g
In box Light Scattering profile using Viscotek detectors.