
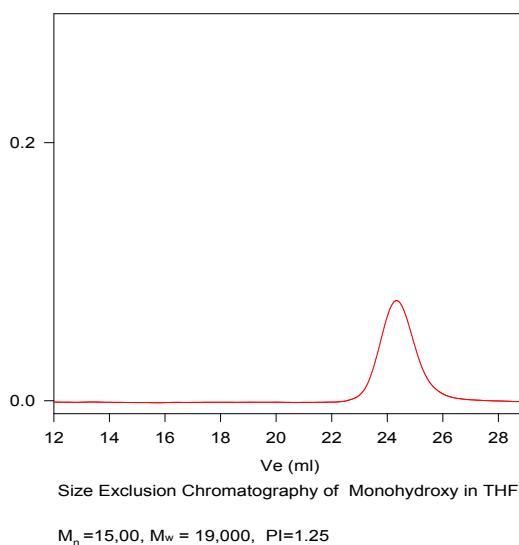


**Sample Name:** Poly(t-butyl acrylate)**SEC of Sample:****Sample #:** P8581-tBuA

This batch is obtained by GTP polymerization

**Structure:****Composition:**

$M_n \times 10^3$	PDI
15.0	1.25

**P8581-tBuA****Synthesis Procedure:**

Poly(t-butyl acrylate) is obtained by GTP process.

**Characterization:**

The molecular weight and polydispersity index (PDI) are obtained by size exclusion chromatography (SEC) in THF. SEC analysis was performed on a Varian liquid chromatograph equipped with refractive and UV light scattering detectors. Three SEC columns from Supelco (G6000-4000-2000 HXL) were used with triple detectors from Viscotek Co.


Thermal analysis of the samples was carried out using a differential scanning calorimeter (TA Q100) at a heating rate of  $10^\circ\text{C}/\text{min}$ . The inflection glass transition temperature ( $T_g$ ) of the sample has been considered.

**Solubility:**

Poly(t-butyl acrylate) is soluble in THF, hexanes (low MW), toluene and  $\text{CHCl}_3$ . This polymer precipitates from ethanol and methanol containing 10-15% water.

 **$T_g$  vs MW for selected poly t-butyl acrylate**

$M_n \times 10^3$	$T_g$ ( $^\circ\text{C}$ )	$M_n \times 10^3$	$T_g$ ( $^\circ\text{C}$ )
0.75	-15	11.6	28
1.4	-5	22	32
2	7	65	35
4.5	12	1128	38

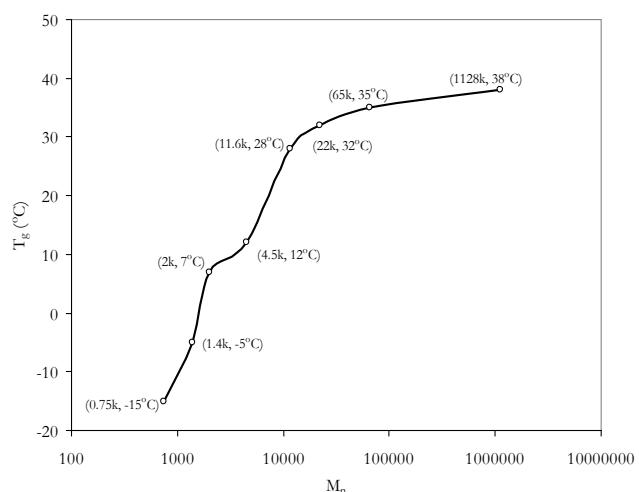**Tg of poly t-butyl acrylate as function of molecular weight****References:**

- Ph. Teyssie, Ph. Bayard, R. Jerome, **S. K. Varshney**, and J. S. Wang, *35th IUPAC International Union of Pure & Applied Chemistry International Symposium on Macromolecules* 1994, 67.
- R. Fayt, R. Forte, C. Jacobs, R. Jerome, T. Ouhadi, Ph. Teyssie and **S. K. Varshney**, *Macromolecules*, 1987, 20, 1442-1444.
- Jerome, R. Forte, **S. K. Varshney**, R. Fayt, and Ph. Teyssie, "The Anionic Polymerization of Alkylacrylates: A Challenge" in the Recent Advances in Mechanistic and Synthetic Aspects of Polymerization: M. Fontanaille and A. Guyot Ed., NATO ASI Series C 215, 101 (1987), CA Vol. 108, 12, 094992.
- Ph. Teyssie, R. Fayt, C. Jacobs, R. Jerome, L. Leemans, and **S. K. Varshney** *Am. Chem. Soc., Polym. Prepr.* 1988, 28, 2, 52-53