


Sample Name: Poly(t-butyl acrylate)

Sample #: P40883-tBuA

Structure:



Composition:

Mn x 10 ³	PDI
243.5	1.27

Synthesis Procedure:

Poly(t-butyl acrylate) is obtained by anionic process.

Characterization:

The molecular weight and polydispersity index (PDI) are obtained by size exclusion chromatography (SEC) in THF. SEC analysis was performed on a Varian liquid chromatograph equipped with refractive and UV light scattering detectors. Three SEC columns from Supelco (G6000-4000-2000 HXL) were used with triple detectors from Viscotek Co.


Solubility:

Poly(t-butyl acrylate) is soluble in THF, hexanes (low MW), toluene and CHCl₃. This polymer precipitates from ethanol and methanol containing 10-15% water.

SEC elugram of the Sample:


P40883-tBuA

Concentration (mg/mL)	2.1533
Sample dv/dc (mL/g)	0.0840
Method File	PS80K-4Dec2017-0000.vcm
Column Set	3x PL 1113-6300
Solvent	THF

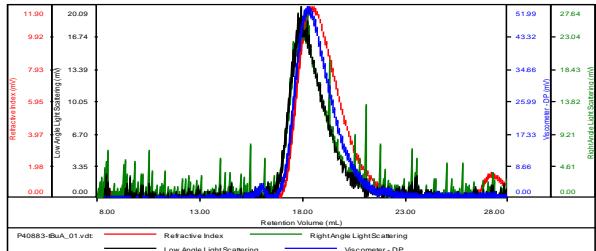

Sample	Mn (Da)	Mw (Da)	Mw/Mn	IV (dL/g)	Mp (Da)
P40883-tBuA_01.vdt	243,605	309,499	1.270	1.2578	295,657

Thermogram of tBuA:

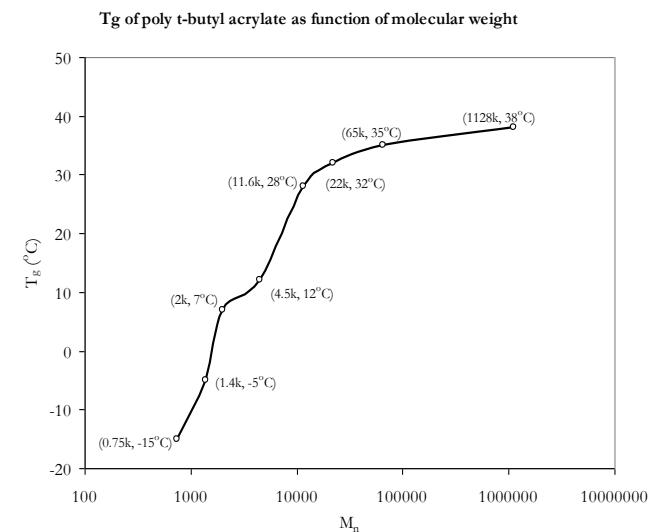

References:

- Ph. Teyssie, Ph. Bayard, R. Jerome, S. K. Varshney, and J. S. Wang, *35th IUPAC International Union of Pure & Applied Chemistry International Symposium on Macromolecules* 1994, 67.
- R. Fayt, R. Forte, C. Jacobs, R. Jerome, T. Ouhadi, Ph. Teyssie and S. K. Varshney, *Macromolecules*, 1987, 20, 1442-1444.
- Jerome, R. Forte, S. K. Varshney, R. Fayt, and Ph. Teyssie, "The Anionic Polymerization of Alkylacrylates: A Challenge" in the Recent Advances in Mechanistic and Synthetic Aspects of Polymerization: M. Fontanaille and A. Guyot Ed., NATO ASI Series C 215, 101 (1987), CA Vol. 108, 12, 094992.
- Ph. Teyssie, R. Fayt, C. Jacobs, R. Jerome, L. Leemans, and S. K. Varshney *Am. Chem. Soc., Polym. Prepr.* 1988, 28, 2, 52-53