


Sample: Poly(Styrene-*co*-Methyl Methacrylate),
 α -Hydroxy, ω -TEMPO-moiety terminated random copolymer

Sample # P60610C-SMMAranOHT

Structure:

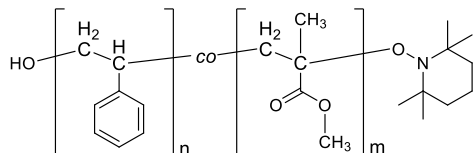


Composition:

$M_n \times 10^3$ (g/mol)	M_w/M_n (PDI)
8.5	1.19

Polystyrene content: 72%

Synthesis:

α -Hydroxy, ω -TEMPO-terminated poly(styrene-*co*-methyl methacrylate) was prepared by nitroxide-mediated radical polymerization at 135°C. The reaction scheme is shown below:

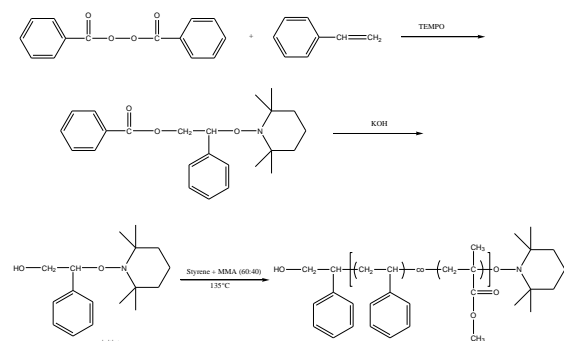


Characterization:

The molecular weight and polydispersity index (PDI) of the product was determined by size exclusion chromatography (SEC), using polystyrene as a standard. The ratio between polystyrene and poly(methyl methacrylate) in PS-PMMA copolymer was calculated from ^1H NMR spectroscopy by comparing the peak area of the PS phenyl protons at 6.5–7.3 ppm and the peak area of PMMA methyl protons at 2.6–3.6 ppm.

Solubility:

Poly(styrene-*co*-methyl methacrylate) is soluble in THF, DMF, toluene, and chloroform. It precipitates from methanol and hexanes.


^1H NMR spectrum of the copolymer in CDCl_3 :

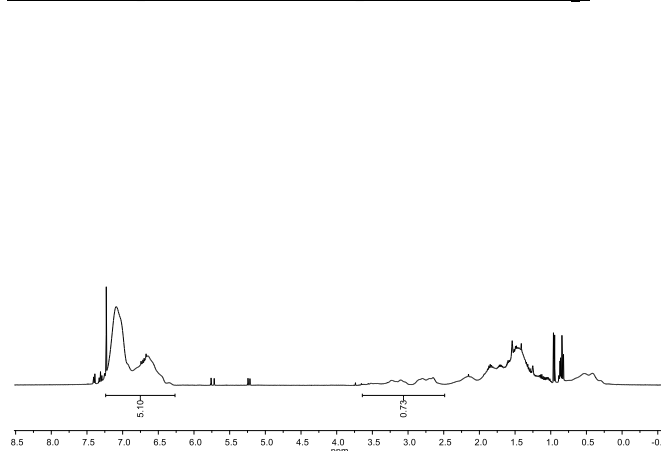

SEC elugram of the copolymer:

Agilent GPC/SEC Software

Chromatogram Plot P60610C-SMMAranOHT

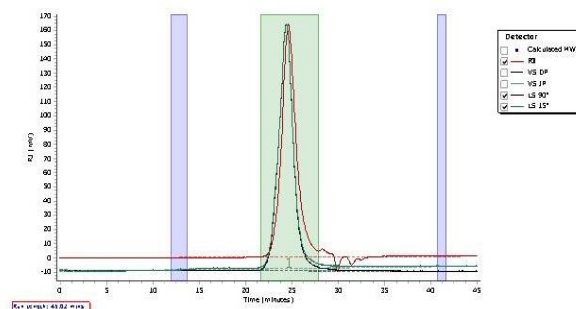

Molecular Weight Averages

Peak	M_p (g/mol)	M_n (g/mol)	M_w (g/mol)	M_z (g/mol)	M_z+1 (g/mol)	M_v (g/mol)	PDI
Peak 1	9870	8332	9941	11573	13360	11143	1.193