


Sample Name:

Poly (4-vinyl pyridine -b-t-butyl methacrylate)

Sample #: **P43691-4VPtBuMA**

Structure:

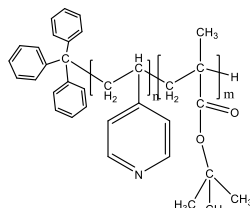

Composition:

Mn $\times 10^3$ 4VP-tBuMA	PDI
63.0-b-190.0	1.10

T _g for tBuMA block: 127 °C
T _g for 4VP block: 152 °C


Synthesis Procedure:

Poly(4VP-t-butyl methacrylate) is synthesized by anionic polymerization process. 4VP monomer was polymerized in Hexamethylphosphoramide (HMPTA) aprotic solvent, it selectively solvates cations and maintain solubility of living anions of Poly 4VP, avoid the agglomeration of anions in THF-HMPTA. tBuMA monomer was added after polymerization of 4VP and polymerization of tBuMA was carried out in ice water for 8h.

Characterization:

The product was characterized by size exclusion chromatography (SEC) and ¹H NMR analysis.


¹H NMR Spectrum of the block copolymer:

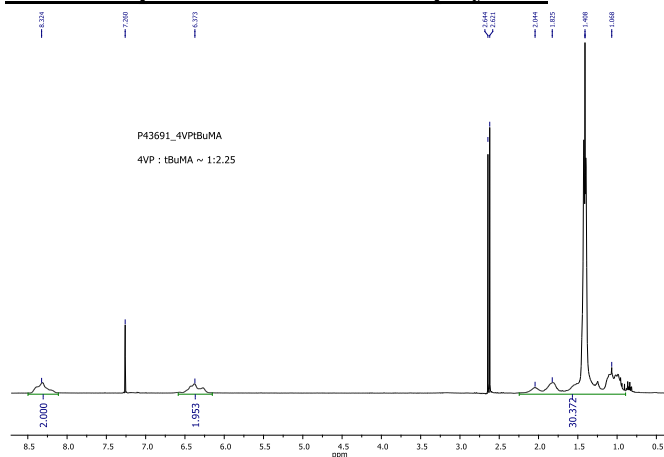

SEC elugram of the first Block:

P43691-4VP

dn/dc	0.1538
Flow Rate	0.7000
Solvent	DMF with LiBr
Method	Calibration_2020-11-25_PMMA-85K-0004.vcm

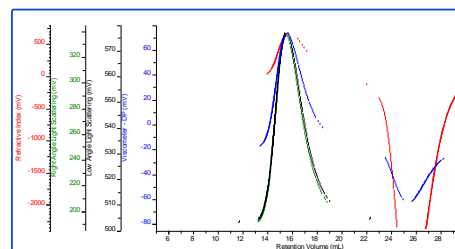


Sample	Mn	Mw	Mp	Mw/Mn
P43691-1_1_2022-03-12	62,686	70,314	70,436	1.122


SEC elugram of the polymer:

P43691-4VP-tBuMA

dn/dc	0.1098
Flow Rate	0.7000
Solvent	DMF with LiBr
Method	Calibration_2020-11-25_PMMA-85K-0004.vcm

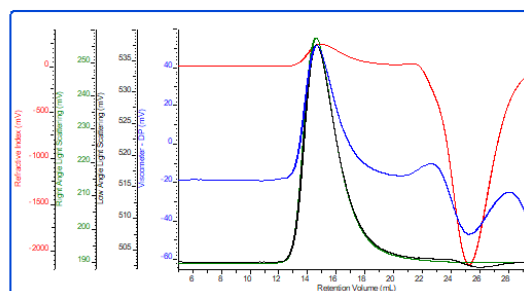

DSC Thermogram of the polymer:

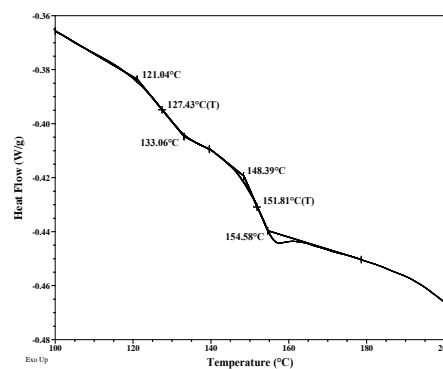

Reference:

S. K. Varshney, X. F. Zhong and A. Eisenberg
Macromolecules, 1993, 26, 701-706.