


Sample Name:
Poly(ethylene oxide-b-Iso butyl methacrylate)

Sample #: P43930A-EOisoBuMA

Structure:

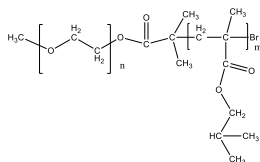


Composition:

Mn x 10 ³ PEO-b-IsoBuMA	PDI
5.0-b-5.0	1.35

Synthesis Procedure:

Poly(Ethylene oxide-iso butyl methacrylate) is prepared as shown in the scheme below:

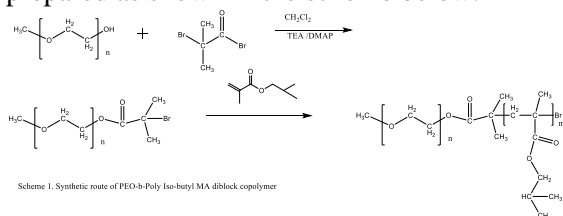

Scheme 1. Synthetic route of PEO-b-Poly(iso-butyl) MA diblock copolymer


Characterization:

Polymer composition was determined by H NMR taking the integration of PEG block at 3.66 ppm and methyl ester of PMMA block at 3.62 ppm. Molecular weights of the first block and the Mw/Mn of the final and the first block was determined by SEC in THF.


Solubility:

Poly(ethylene oxide -b- isoBuMA) is soluble in CHCl₃, THF, toluene. The polymer precipitated out from hexane.

H NMR spectrum of the PEGBr Mn of 5000:

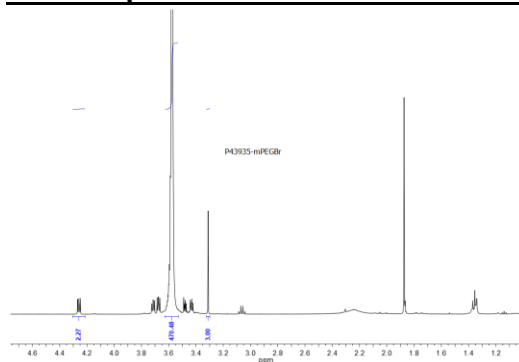


SEC profile of the PEG Sample:
P43935-EGOCH3Br

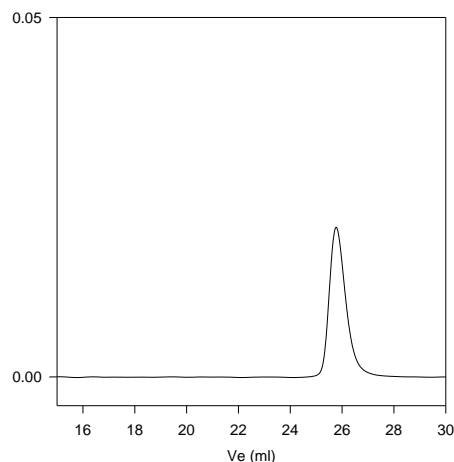


Size exclusion chromatography:

— Bromo terminated Poly(ethylene glycol methyl ether),
M_n=5,000, M_w=5,400, PI=1.06

¹H-NMR Spectrum of the block copolymer:

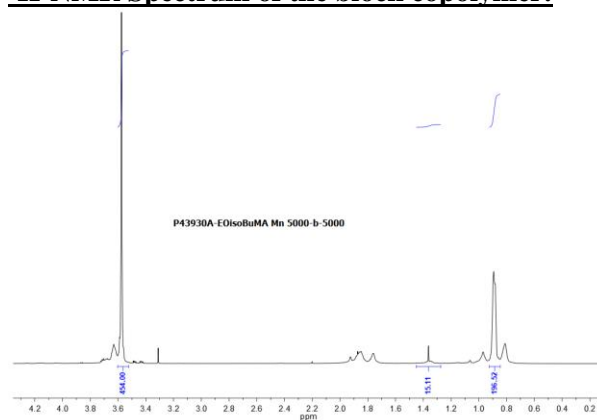

SEC of the block copolymer:

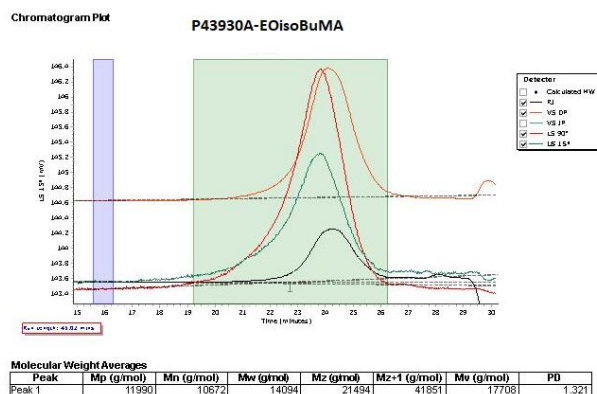

Peak	Mp (g/mol)	Mn (g/mol)	Mw (g/mol)	Mz (g/mol)	Mz+1 (g/mol)	Mv (g/mol)	PD
Peak 1	11990	10672	14094	21494	41851	17708	1.321