

# Product Profile

## Identification

**Product Name:** Poly(styrene-b-4-vinyl-pyridine)

**Product Lot Number:** P9855-R-S4VP

**CAS #:** 26222-40-2

**Product Chemical Architecture:**



**Composition:**

Composition (S-b-4VP)	44,000-b-50,000
4VP mole%	53.4
Mn (g/mole)	94,000
Mw (g/mole)	100,000
Mw/Mn	1.06
dn/dc (mL/g) in DMF at 35 °C	0.159

## Method of Synthesis

The polymer is synthesized by anionic polymerization process.

**Solubility in different solvents:**

THF	Depends on composition	DMF	√
Alcohol	Depends on composition	CHCl <sub>3</sub>	√
Toluene <sub>(hot)</sub>	X	Water	X


## Validation of Architecture

### A. Gel Permeation Chromatography (GPC), SEC Profile:

Molecular weights were determined by Malvern OmniSec Reveal & Resolve GPC/SEC System equipped with Triple detector (RI, Viscometer, RALS 90° and LALS 7°) and two columns (PSS, SDV, 8x300 mm). DMF with 0.023M LiBr was the eluent. The flow rate was 0.7 ml/min.

Polymer Source

Malvern Panalytical

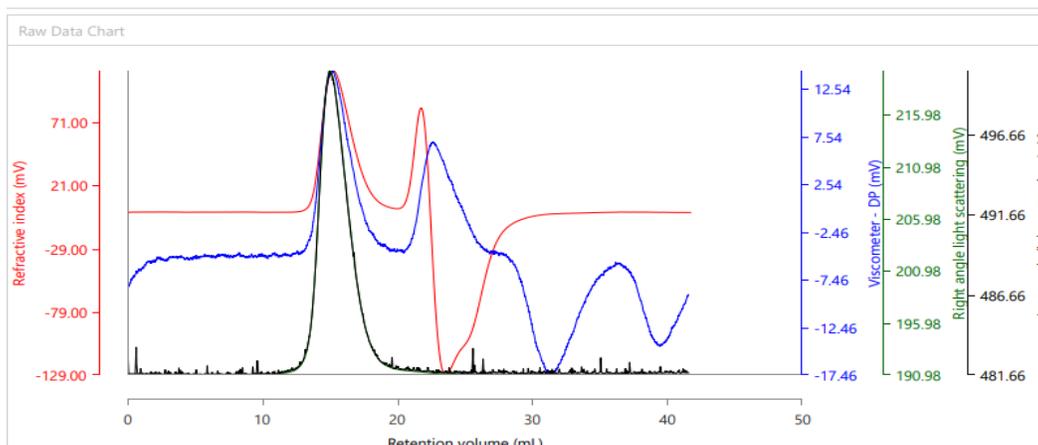

Injection Name	RV (mL)	Mn (g/mol)	Mw (g/mol)	Mp (g/mol)	Mz (g/mol)	Mw/Mn
P9855, Injection 1, Peak 1	15.25	94,260	99,611	98,826	109,291	1.057

**B. NMR ( $^1\text{H}$ NMR) of S4VP in  $\text{CDCl}_3$ , 500 MHz**

P9855-R  
Company Polymer Source  
1d\_proton\_16scans  $\text{CDCl}_3$  {D:\Polymer\_Source} PSource 41

