


**Sample Name:**

Poly(Dimethylsiloxane-b-2-methyloxazoline) diblock Copolymer

**Sample #:** P11477B-DMSMEOXZ

**Structure:**



**Composition:**


Mn x 10 <sup>3</sup>	PDI
5.0-b-1.5	1.25
Dp: 67-b-22	

**Purification of the Diblock copolymer:**


1. After the reaction DCM was removed under vacuum.
2. Product was dissolved in a mixture of methanol-acetone
3. Filter
4. Concentrate and precipitated in cold acetone at -78 oC.
5. Kept at -10 oC over night.
6. Decant the solution and recover the solid product.
7. Dried under vacuum over 24h at room temperature.

**Characterization Size exclusion chromatography (SEC):** Varian liquid chromatograph equipped with UV and refractive detector. SEC columns from Supelco were used with THF for the first block (PDMS) Since it can not be eluted in DMF and for the block copolymer in DMF containing 0.06M LiBr at 60 oC as the eluent. The molecular weights and the polydispersity indice were calculated. The chemical composition was extracted from proton NMR, which was recorded from Varian 500MHz instrument using CDCl<sub>3</sub> as solvent. The molecular weight of block was calculated based on the molecular weight of the first block and the chemical composition.

**HNMR of the Polymer:**

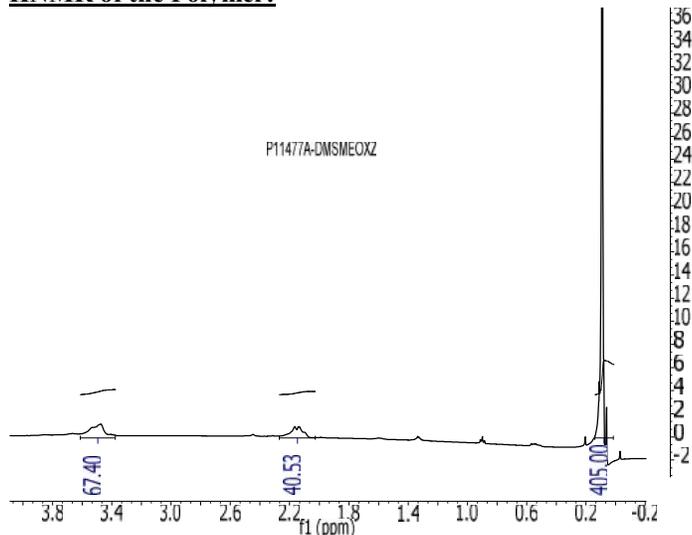

**P11477B-DMSMEOXZ**

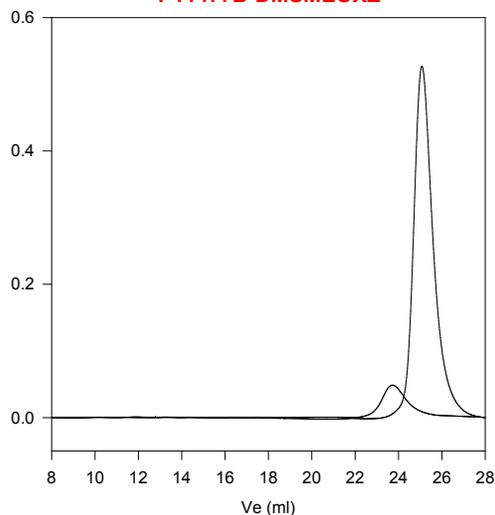

Size exclusion chromatography of poly(dimethylsiloxane-b-MEOXZ)

- PDMS, M<sub>n</sub>=5000, M<sub>w</sub>=6,000, M<sub>w</sub>/M<sub>n</sub>=1.18
- Poly(dimethylsiloxane-b-MEOXZ) eluted in presence of DMF
- M<sub>n</sub>: PDMS(5,000)-b-PMEOXZ(1,500) M<sub>w</sub>/M<sub>n</sub>=1.25